


GGB DX[®]

Marginally lubricated

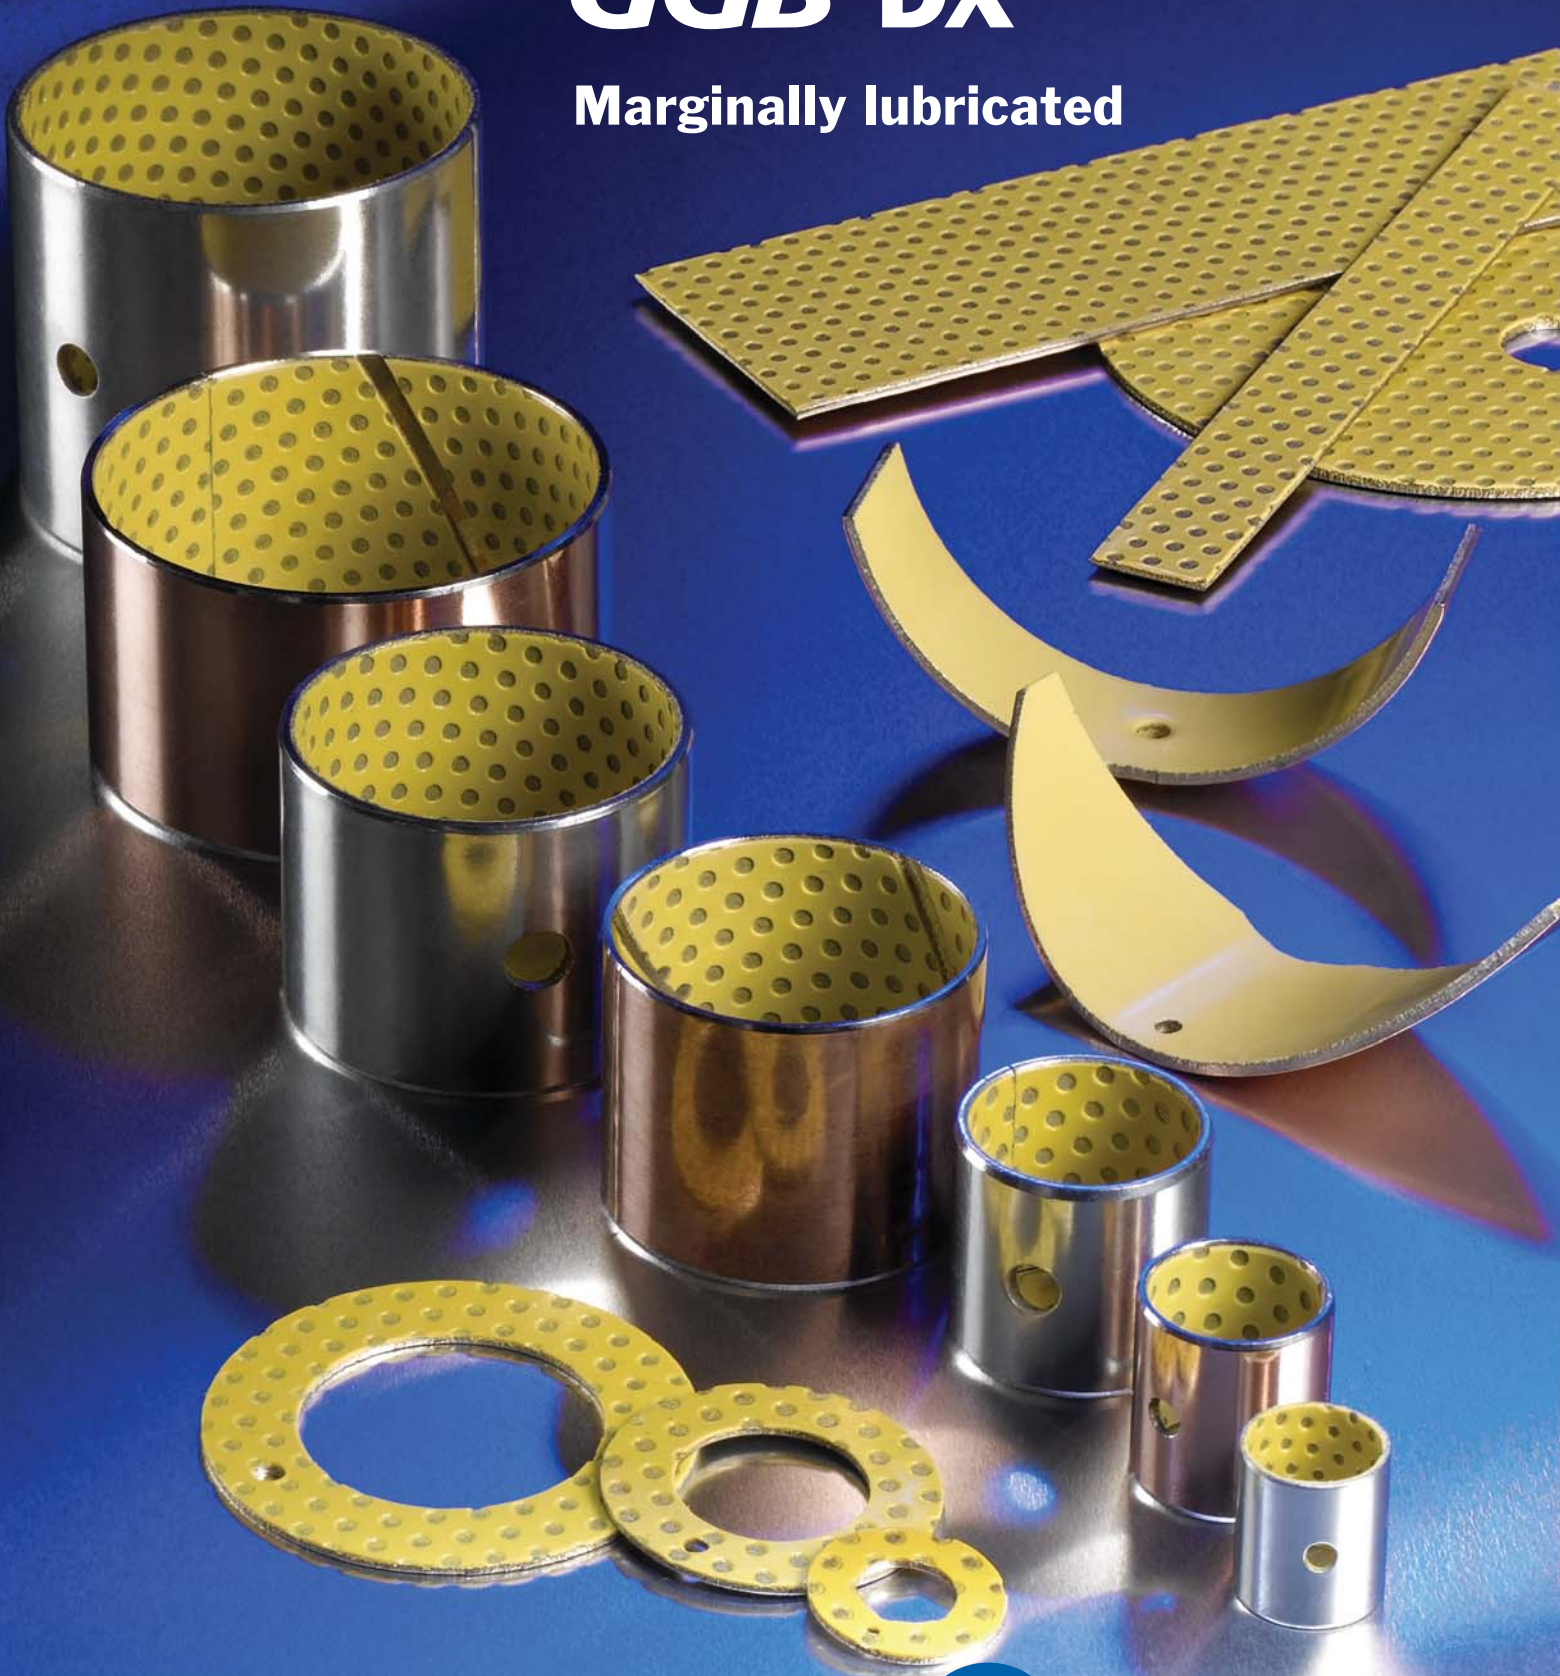

Designer's Handbook

 **GGB**
BEARING TECHNOLOGY

an EnPro Industries company

Quality

All the products described in this handbook are manufactured under DIN EN ISO 9001, ISO/TS 16949 and ISO 14001 approved quality management systems.

All Certificates can be downloaded as PDF files from our website www.ggbearings.com.

In addition GGB North America has been certified AS9100 revision B complying with the requirements of aerospace industry's quality management system for the manufacture of metal-backed bearings and filament wound bearings and washers.

AMERICA




FRANCE



GERMANY



BRAZIL

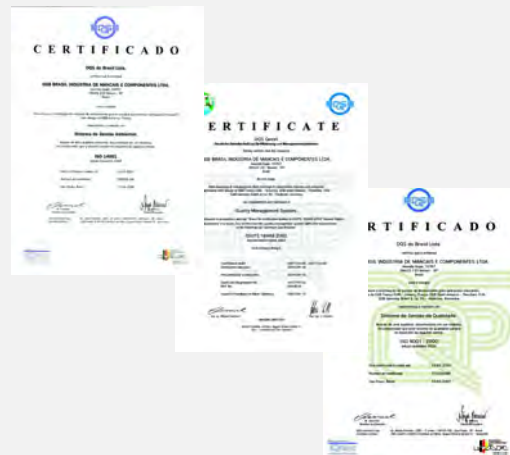

SLOVAKIA



CHINA



Formula Symbols and Designations

Formula Symbol	Unit	Designation
a_B	-	Bearing size factor
a_E	-	High load factor
a_Q	-	Speed/Load factor
a_S	-	Surface finish factor
a_T	-	Temperature application factor
B	mm	Nominal bush width
C	1/min	Dynamic load frequency
C_D	mm	Installed diametral clearance
C_{Dm}	mm	Diametral clearance machined
C_i	mm	Total number of dynamic load cycles
C_o	mm	ID chamfer length
C_T	-	OD chamfer length
D_H	mm	Housing Diameter
D_i	mm	Nominal bush/thrust washer ID
$D_{i,a}$	mm	Bush ID when assembled in housing
$D_{i,a,m}$	mm	Bush ID assembled and machined
D_J	mm	Shaft diameter
D_{Jm}	mm	Shaft diameter for machined bushes
D_o	mm	Nominal bush/thrust washer OD
d_D	mm	Dowel hole diameter
d_L	mm	Oil hole diameter
d_P	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F_i	N	Insertion force
f	-	Friction
H_a	mm	Depth of Housing Recess (e.g. for thrust washers)
H_d	mm	Diameter of Housing Recess (thrust washers)
L	mm	Strip length
L_H	h	Bearing service life
L_{RG}	h	Relubrication interval

Formula Symbol	Unit	Designation
n	1/min	Rotational speed
n_{osc}	1/min	Oscillating movement frequency
p	MPa	Specific load
p_{lim}	MPa	Specific load limit
$p_{sta,max}$	MPa	Maximum static load
$p_{dyn,max}$	MPa	Maximum dynamic load
Q	-	Total number of cycles
R	-	Number of lubrication intervals
R_a	µm	Surface roughness (DIN 4768, ISO/DIN 4287/1)
s_3	mm	Bush wall thickness
s_S	mm	Strip thickness
s_T	mm	Thrust washer thickness
T	°C	Temperature
T_{amb}	°C	Ambient temperature
T_{max}	°C	Maximum temperature
T_{min}	°C	Minimum temperature
v	-	Sliding speed
u	m/s	speed factor
W	mm	Strip width
$W_{u min}$	mm	Minimum usable strip width
α_1	1/10⁶K	Coefficient of linear thermal expansion parallel to surface
α_2	1/10⁶K	Coefficient of linear thermal expansion normal to surface
σ_c	MPa	Compressive Yield strength
λ	W/mK	Thermal conductivity
φ	°	Angular displacement
η	Ns/mm²	Dynamic Viscosity
Z_T	-	Total number of oscillating movements

Content

Quality	I	6 Bearing Assembly	21
Formula Symbols and Designations	II	6.1 Dimensions and Tolerances ..	21
1 Introduction	4	6.2 Tolerances for minimum clearance	21
1.1 Characteristics and Advantages	4	Grease lubrication	21
2 Structure	4	Fluid Lubrication	23
2.1 Basic Forms	5	Allowance for Thermal Expansion	23
3 Properties	6	6.3 Counterface Design	24
3.1 Physical Properties	6	6.4 Installation	25
3.2 Chemical Properties	6	Fitting of Bushes	25
4 Lubrication	7	Insertion Forces	25
4.1 Choice of Lubricant	7	Alignment	26
Grease	8	Sealing	26
Oil	8	Axial Location	26
Non lubricating fluids	8	Fitting of Thrust Washers	26
4.2 Friction	9	Slideways	27
4.3 Lubricated Environments	9	7 Machining	28
Lubrication	9	7.1 Machining Practice	28
4.4 Characteristics of Fluid Lubricated DX Bearings	10	7.2 Boring	28
4.5 Design Guidance for Fluid Lubricated Applications	10	7.3 Reaming	29
4.6 Wear Rate and Relubrication Intervals with Grease lubrication	12	7.4 Broaching	29
Fretting Wear	12	7.5 Vibrobroaching	30
5 Design Factors	13	7.6 Modification of components ..	30
5.1 Specific Load	13	7.7 Drilling Oil Holes	30
Specific Load Limit	13	7.8 Cutting Strip Material	30
5.2 Sliding Speed	14	7.9 Electroplating	31
Continuous Rotation	14	DX Components	31
Oscillating Movement	14	Mating Surfaces	31
5.3 pv Factor	15	8 Standard Products	32
5.4 Load	15	8.1 PM-DX cylindrical bushes	32
Type of Load	15	8.2 MB-DX cylindrical bushes	39
5.5 Temperature	17	8.3 DX Thrust Washers	44
5.6 Mating Surface	17	8.4 DX cylindrical bushes - Inch sizes	45
5.7 Bearing Size	18	8.5 DX Thrust Washers - Inch sizes	48
5.8 Estimation of Bearing Service Life with Grease Lubrication	18	8.6 DX Strip	49
5.9 Worked Examples	20	8.7 DX Strip - Inch sizes	49
		9 Data Sheet for bearing design	50

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DX[®] bearings. The information given, permits designers to establish the correct size of bearing required and the expected life and performance. GGB Research and Development services are available to assist with unusual design problems.

Complete information on the range of DX standard stock products is given together with details of other DX products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worthwhile to contact the Company should additional information be required.

Customers are advised to carry out prototype testing wherever possible.

1.1 Characteristics and Advantages

- DX provides maintenance free operation
- DX has a high pv capability
- DX exhibits low wear rate
- Seizure resistant
- Suitable for temperatures from -40 to +120 °C
- High static and dynamic load capacity
- Good frictional properties
- No water absorption and therefore dimensionally stable
- Compact and light
- Suitable for rotating, oscillating, reciprocating and sliding movements
- DX bearings are prefinished and require no machining after assembly

2 Structure

DX is a composite bearing material developed specifically to operate with marginal lubrication and consists of three bonded layers: a steel backing strip and a sintered porous bronze matrix, impregnated and overlaid with a pigmented acetal copolymer bearing material.

The steel backing provides mechanical strength and the bronze interlayer provides a strong mechanical bond for the lining. This construction promotes dimensional stability and improves thermal conductivity, thus reducing the temperature at the bearing surface.

DX is designed for use with grease lubrication and the bearing surface is normally provided with a uniform pattern of indents. These serve as a reservoir for the grease

and are designed to provide the optimum distribution of the lubricant over the bearing surface.

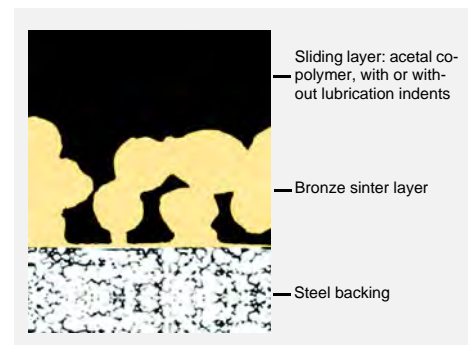


Fig. 1: DX-microsection

2.1 Basic Forms

Standard Components available from stock

These products are manufactured to International, National or GGB standard designs.

Metric and Imperial Sizes

- Cylindrical Bushes
 - PM pre finished metric range, not machinable in situ, for use with standard journals finished to h6-h8 limits.
 - MB machinable metric range, with an allowance for machining in situ.
 - Machinable inch range for use as supplied or after machining in situ.
- Thrust Washers
- Strip Material

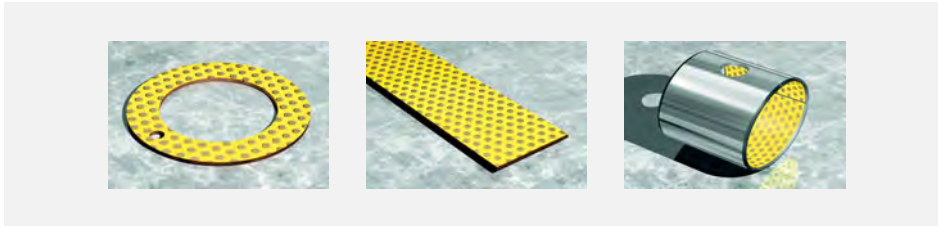


Fig. 2: Standard components

Non Standard Components not available from stock

These products are manufactured to customers' requirements with or without GGB recommendations, and include for example

- Modified Standard Components
- Half Bearings
- Flat Components
- Pressings
- Stampings



Fig. 3: Non standard components

3 Properties

3.1 Physical Properties

Characteristic		Symbol	Value DX	Unit	Comments
Physical Properties	Thermal Conductivity	λ	52	W/mK	
	Coefficient of linear thermal expansion				
	parallel to surface	α_1	11	1/10 ⁶ K	
	normal to surface	α_2	29	1/10 ⁶ K	
	Maximum Operating Temperature	T _{max}	120	°C	
	Minimum Operating Temperature	T _{min}	-40	°C	
Mechanical Properties	Compressive Yield Strength	σ_c	380	MPa	measured on disc 5 mm diameter x 2.45 mm thick.
	Maximum Load				
	Static	P _{sta,max}	140	MPa	
	Dynamic	P _{dyn,max}	70	MPa	
Electrical Properties	Volume resistivity of acetal lining		10 ¹⁵	Ωcm	

Table 1: Properties of DX

3.2 Chemical Properties

The following table provides an indication of the resistance of DX to various chemical media. It is recommended that the chemical resistance is confirmed by testing if possible.

+	Satisfactory: Corrosion damage is unlikely to occur.
o	Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.
-	Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.

	Chemical	%	°C	Rating
Strong Acids	Hydrochloric Acid	5	20	-
	Nitric Acid	5	20	-
	Sulphuric Acid	5	20	-
Weak Acids	Acetic Acid	5	20	-
	Formic Acid	5	20	-
Bases	Ammonia	10	20	o
	Sodium Hydroxide	5	20	o
Solvents	Acetone		20	+
	Carbon Tetrachloride		20	+
Lubricants and fuels	Paraffin		20	+
	Gasolene		20	+
	Kerosene		20	+
	Diesel fuel		20	+
	Mineral Oil		70	o
	HFA-ISO46 High Water fluid		70	o
	HFC-Water-Glycol		70	o
	HFD-Phosphate Ester		70	+
	Water		20	o
	Sea Water		20	-

Table 2: Chemical resistance of DX

4 Lubrication

4.1 Choice of Lubricant

DX must be lubricated. The choice of lubricant depends upon pv and the sliding speed and the stability of the lubricant under the operating conditions.

+	Recommended
o	Satisfactory
-	Not recommended
NA	Data not available

Manufacturer	Grade	Type		Rating
BP	Energrease LS2	Mineral	Lithium Soap	+
	Energrease LT2	Mineral	Lithium Soap	+
	Energrease FGL	Mineral	Non Soap	o
	Energrease GSF	Synthetic	NA	o
Century	Lacerta ASD	Mineral	Lithium/Polymer	o
	Lacerta CL2X	Mineral	Calcium	-
Dow Corning	Molykote 55M	Silicone	Lithium Soap	o
	Molykote PG65	PAO	Lithium Soap	+
	Molykote PG75	Synthetic/Mineral	Lithium Soap	+
	Molykote PG602	Mineral	Lithium Soap	o
Elf	Rolexa.1	Mineral	Lithium Soap	+
	Rolexa.2	Mineral	Lithium Soap	o
	Epexelf.2	Mineral	Lithium/Calcium Soap	o
Esso	Andok C	Mineral	Sodium Soap	o
	Andok 260	Mineral	Sodium Soap	o
	Cazar K	Mineral	Calcium Soap	-
Mobil	Mobilplex 47	Mineral	Calcium Soap	o
	Mobiltemp 1	Mineral	Non Soap	+
Rocol	BG622	White Mineral	Calcium Soap	o
	Sapphire	Mineral	Lithium Complex	o
	White Food Grease	White Oil	Clay	-
Shell	Albida R2	Mineral	Lithium Complex	+
	Axinus S2	Mineral	Lithium	o
	Darina R2	Mineral	Inorganic Non Soap	+
	Stamina U2	Mineral	Polyurea	o
	Tivela A	Synthetic	NA	+
Sovereign	Omega 77	Mineral	Lithium	o
	Omega 85	Mineral	Polyurea	-
Tom Pac	Tom Pac	NA	NA	o
Total	Aerogrease	Synthetic	NA	+
	Multis EP2	NA	Lithium	-

Table 3: Performance of greases

Grease

Grease lubrication is the recommended method of lubrication. The performance ratings of different types of grease are indicated in Table 3. For environmental temperatures above 50 °C the grease should

contain an anti-oxidant additive. Greases containing EP additives or significant additions of graphite or MoS₂ are not generally recommended for use with DX.

Oil

DX is not generally suitable for use with hydrocarbon oils operating above 115 °C. At these temperatures oxidation of the oil may produce a low concentration of labile residues, acid or free radical, which will cause depolymerisation of the DX acetal copolymer bearing lining. Such oxidation

can also occur after prolonged periods at lower temperatures. In practice, this means that DX is not recommended for use with recirculating oil systems or bath systems where sump temperatures of 70 °C or greater are possible.

Non lubricating fluids

Care must be taken when using DX with non lubricating fluids as indicated below.

Water

DX is only suitable for operation in water when the load and speed permit full hydro-

dynamic conditions to be established (see Fig. 7).

Water-Oil Emulsion

DX is suitable for use with 95/5 water/oil emulsions, however initial operation with

pure oil or grease is recommended before transferring to emulsion.

Shock-Absorber Oils

DX is not compatible with shock-absorber oils at operating temperature.

Petrol

With petrol as a lubricant at a pv factor of 0.21 MPa x m/s the wear rate of DX has been found to be about 4-5 times greater

than that of an initially greased bearing under the same pv conditions.

Kerosene and Polybutene

The wear rate of DX with these fluids has been found to be equivalent to that obtained with a light hydrocarbon oil.

Other Fluids

Polyester, polyethylene glycol and polyglycol lubricants give similar wear rates with DX to light hydrocarbon oil. With the glycol fluids however the operating temperature must not exceed 80 °C because the acetal lining of DX could then be attacked by these fluids.

In general, the fluid will be acceptable if it does not chemically attack the acetal lining or the porous bronze interlayer. Chemical resistance data are given in Table 2.

Where there is doubt about the suitability of a fluid, a simple test is to submerge a

sample of DX material in the fluid for two to three weeks at 15-20 °C above the operating temperature. The following will usually indicate that the fluid is not suitable for use with DX.

- A significant change in the thickness of the DX material.
- A visible change in the bearing surface from polished to matt.
- A visible change in the microstructure of the bronze interlayer.

4.2 Friction

Lubricated DX bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of lubricated DX depends upon

the actual operating conditions as indicated in section 4.3. Where frictional characteristics are critical to a design they should be established by prototype testing.

4.3 Lubricated Environments

The following sections describe the basics of lubrication and provide guidance on the application of DX in such environments.

Lubrication

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load and Speed
- Lubricant Viscosity and Flow

Hydrodynamic lubrication

Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film.
- Very low friction and no wear of the bearing or shaft since there is no contact.
- Coefficients of friction of 0.001 to 0.01.

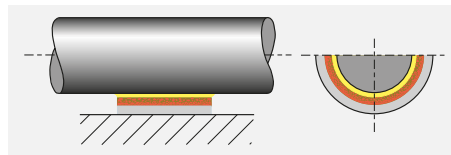


Fig. 4: Hydrodynamic lubrication

Hydrodynamic conditions occur when

$$(4.3.1) \quad p \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{MPa}]$$

$$p \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i}$$

Mixed film lubrication

Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Coefficients of friction of 0.01 to 0.10.
- Friction and wear depend upon the degree of hydrodynamic support developed.

- DX provides low friction and high wear resistance to support the boundary lubricated element of the load.

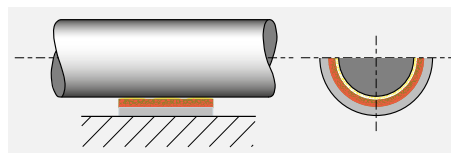


Fig. 5: Mixed film lubrication

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance.
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent properties of DX material minimises wear under these conditions.
- The dynamic coefficient of friction with DX is typically 0.02 to 0.1 under boundary lubrication conditions.

- The static coefficient of friction with DX is typically 0.03 to 0.15 under boundary lubrication conditions.

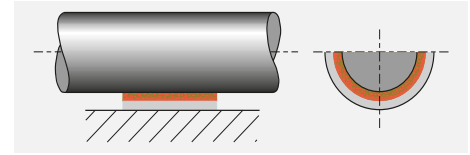


Fig. 6: Boundary lubrication

4.4 Characteristics of Fluid Lubricated DX Bearings

DX is particularly effective in the most demanding of lubricated applications

where full hydrodynamic operation cannot be maintained, for example:

• High load conditions

In highly loaded applications operating under boundary or mixed film conditions DX shows excellent wear resistance and low friction.

• Start up and shut down under load

With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions.

- DX minimises wear
- DX requires less start up torque than conventional metallic bearings.

• Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only. DX requires significantly less lubricant than conventional metallic bearings.

4.5 Design Guidance for Fluid Lubricated Applications

Fig. 7, Page 11 shows the three lubrication regimes discussed above plotted on a

graph of sliding speed vs the ratio of specific load to lubricant viscosity.

In order to use Fig. 7

- Using the formulae in Section 5
 - Calculate the specific load p
 - Calculate the shaft surface speed v

- Using the viscosity temperature relationships presented in Table 4.
 - Determine the viscosity in centipoise of the lubricant.

Note:

Viscosity is a function of the operating temperature. If the operating temperature of

the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

Area 1 of Fig. 7

- The bearing will operate with boundary lubrication.
- The pv factor will be the major determinant of bearing life.

If $epv/\eta \leq 0.2$ then

$$(4.5.1) \quad L_H = \frac{2000}{\left(\frac{epv}{\eta}\right)^{0.5}} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

If $0.2 < epv/\eta \leq 1.0$ then

$$(4.5.2) \quad L_H = \frac{1000}{\left(\frac{epv}{\eta}\right)} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

Area 2 of Fig. 7

- The bearing will operate with mixed film lubrication.
- pv factor is no longer a significant parameter in determining the bearing

Area 3 of Fig. 7

- The bearing will operate with hydrodynamic lubrication.

Area 4 of Fig. 7

- These are the most demanding operating conditions.
- The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both.
- These conditions may cause
 - excessive operating temperature
 - and/or high wear rate.

- DX bearing performance can be estimated from the following equations.
- The effective pv Factor epv can be estimated from Section 5.8.

If $epv/\eta > 1.0$ then

$$(4.5.3) \quad L_H = \frac{1000}{\left(\frac{epv}{\eta}\right)^2} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

epv see (5.8), page 18

- life.
- DX bearing performance will depend upon the nature of the fluid and the actual service conditions.

- Bearing wear will be determined only by the cleanliness of the lubricant and the frequency of start up and shut down.

- The bearing performance may be improved:
 - by use of unindented DX lining
 - by the addition of one or more grooves to the bearing
 - by shaft surface finish $R_a < 0.05 \mu m$.

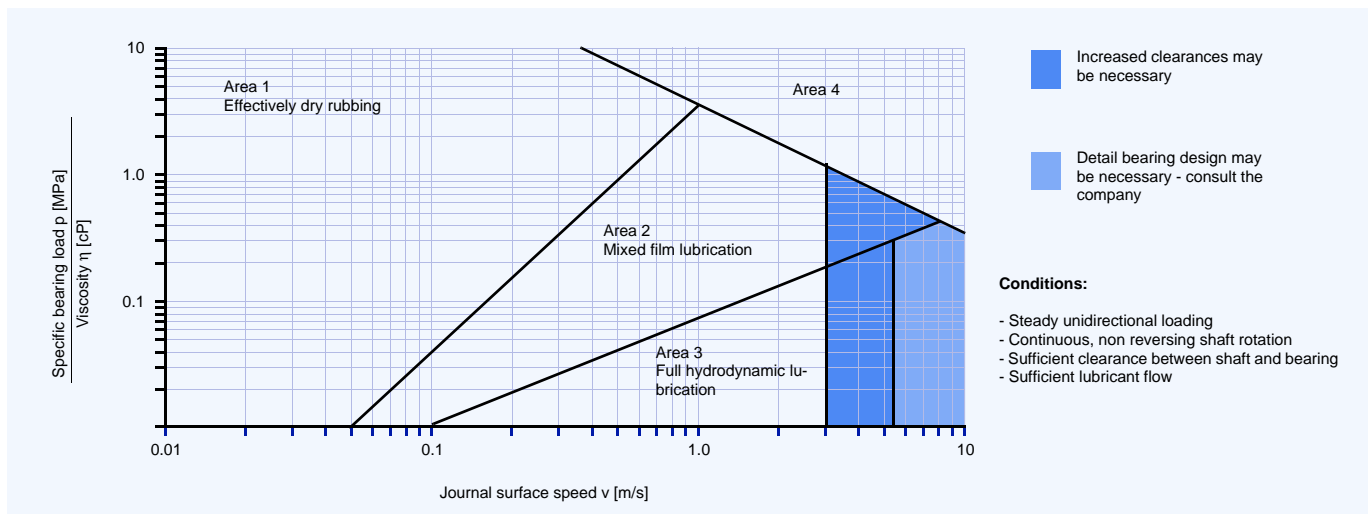


Fig. 7: Design guide for lubricated application

Temperature [°C]	Viscosity [cP]														
	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
Lubricant															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 4: Viscosity data

4.6 Wear Rate and Relubrication Intervals with Grease Lubrication

At specific bearing loads below 100 MPa a grease lubricated DX bearing shows only small bedding-in wear of about 0.0025 mm. This is followed by little wear during the early part of the bearing life until the lubricant becomes exhausted and the wear rate increases. If the bearing is regreased before the rate of wear starts to increase rapidly the material will continue to function satisfactorily with little wear. Fig. 8 shows the typical wear pattern.

Under specific loads above 100 MPa the initial bedding-in wear is greater, typically about 0.025 mm, followed by a decreasing wear rate until the bearing exhibits a similar wear/life relationship to that shown in Fig. 8.

The useful life of the bearing is limited by wear in the loaded area. If this wear exceeds 0.15 mm the grease capacity of the indents is reduced and more frequent regreasing of the bearing will be required.

Fretting Wear

Oscillating movements of less than the dimensions of the indent pattern may cause localised wear of the mating surface after prolonged usage. This will result in the indent pattern becoming transferred

onto the mating surface in contact with the DX bearing and may also give rise to fretting corrosion damage. In this situation DS™ material should be considered as an alternative to DX.

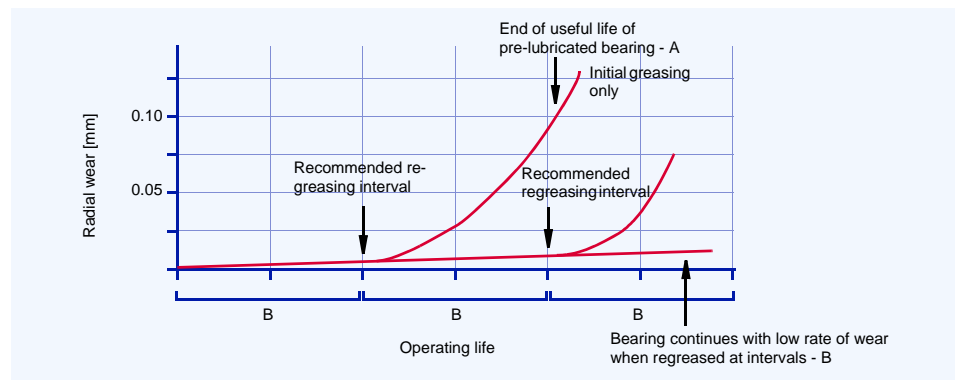


Fig. 8: Typical wear of DX

5 Design Factors

The main parameters when determining the size or calculating the service life for a DX bearing are:

- Specific Load Limit p_{lim} [MPa]
- pv Factor [MPa x m/s]
- Mating surface roughness R_a [μm]
- Mating surface material
- Temperature T [$^{\circ}\text{C}$]
- Other environmental factors eg. housing design, dirt, lubrication.

5.1 Specific Load

The specific load p is defined as the working load divided by the projected area of the bearing and is expressed in MPa.

Bushes

$$(5.1.1) \quad p = \frac{F}{D_i \cdot B} \quad [\text{MPa}]$$

Thrust Washers

$$(5.1.2) \quad p = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)} \quad [\text{MPa}]$$

Slide Plates

$$(5.1.3) \quad p = \frac{F}{L \cdot W} \quad [\text{MPa}]$$

Specific Load Limit

The maximum load which can be applied to a DX bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading and lubrication. It is highest under steady loads. The values of Specific Load Limit specified in Table 5 assume good alignment between the bearing and mating surface.

The Specific Load Limit for DX reduces for bearing operating temperatures in excess

of 40°C , falling to about half the values given in Table 5 for temperatures above 100°C .

Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit (Fig. 9, Page 14).

Load	Operating condition	Lubrication	p_{lim}
Steady	Intermittent or very slow (below 0.01 m/s) continuous rotation or oscillating motion	Grease or oil	140
Steady	Continuous rotation or oscillating motion	Grease or oil (boundary lubrication)	70
Steady or dynamic	Continuous rotation or oscillating motion	Oil (hydrodynamic lubrication)	45

Table 5: Specific load limit p_{lim} for DX

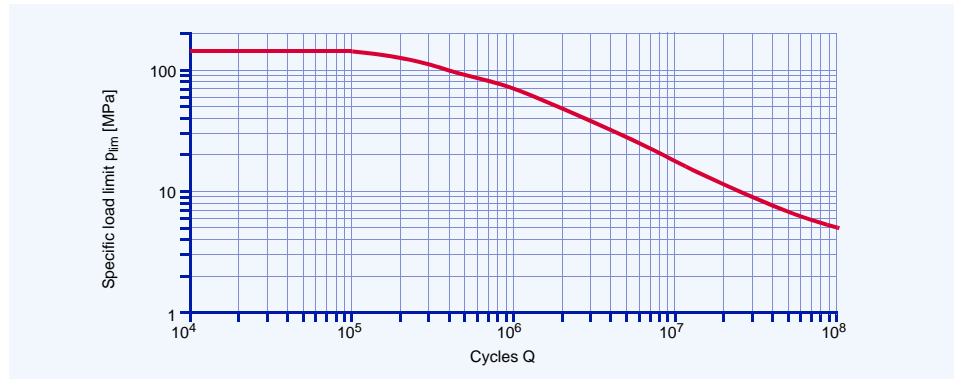


Fig. 9: DX specific load limits p_{lim} under dynamic loads or oscillating conditions

5.2 Sliding Speed

The sliding speed v [m/s] is calculated as follows:

Continuous Rotation

Bushes

$$(5.2.1) \quad v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} \quad [\text{m/s}]$$

Thrust Washers

$$(5.2.2) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot n \quad [\text{m/s}]$$

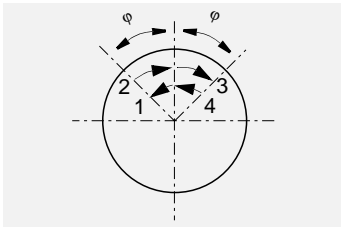


Fig. 10: Oscillating cycle φ

Oscillating Movement

Bushes

$$(5.2.3) \quad v = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

Thrust Washers

$$(5.2.4) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\varphi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

The maximum permissible effective pv factor (epv factor) for grease lubricated DX bearings is dependent upon the sliding

speed as shown in Fig. 11. For sliding speeds in excess of 2.5 m/s continuous oil lubrication is recommended.

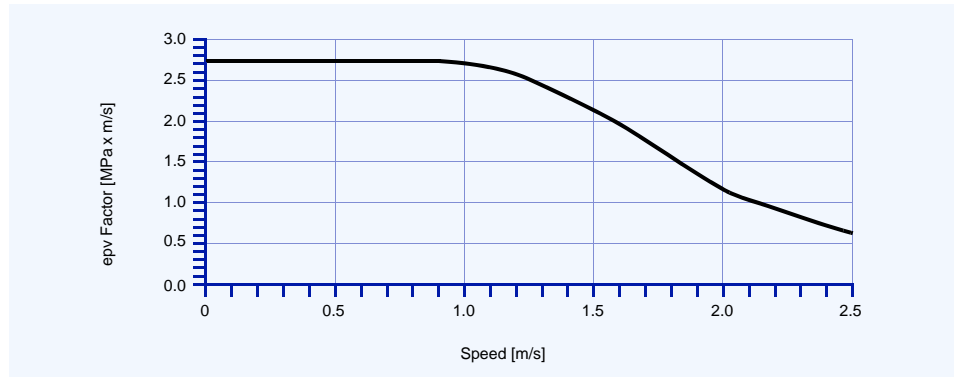


Fig. 11: Maximum epv factor for grease lubrication

5.3 pv Factor

The useful operating life of a DX bearing is governed by the pv factor, which is calculated as follows:

$$(5.3.1) \quad pv = p \cdot v \quad [\text{MPa} \times \text{m/s}]$$

5.4 Load

In addition to its contribution to the pv factor the type and direction of the applied load also affects the performance of a DX bearing. This is accommodated in the calcu-

lation of the bearing service life by the speed/load application factor a_Q shown in Figs. 14-16.

Type of Load

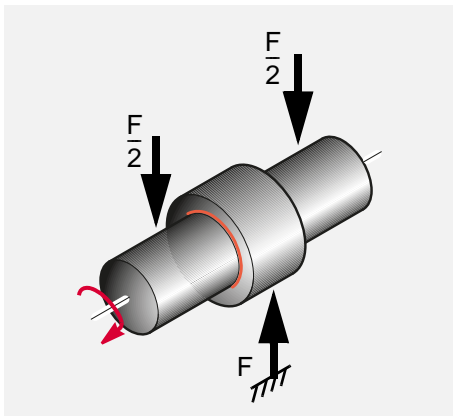


Fig. 12: Steady load, vertically downwards, bush stationary, shaft rotating. Lubricant drains to loaded area

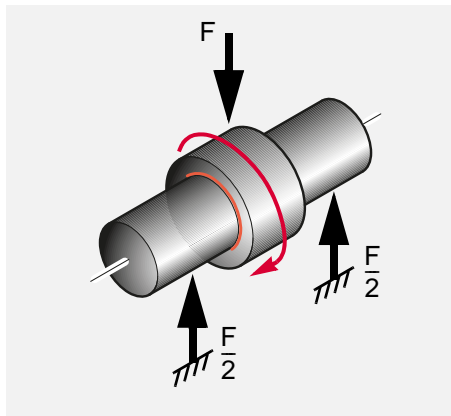


Fig. 13: Rotating load, shaft stationary, bush rotating. Lubricant drains away from loaded area

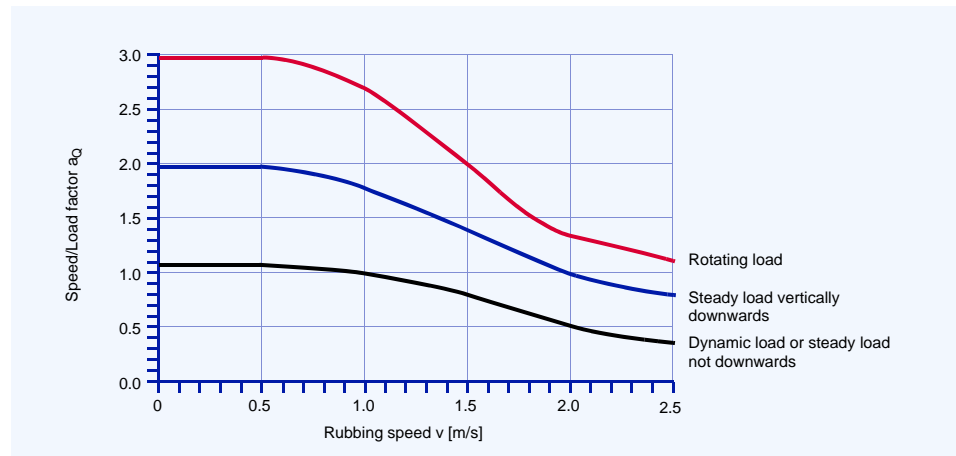


Fig. 14: Speed/Load factor a_Q for MB range bushes - unmachined

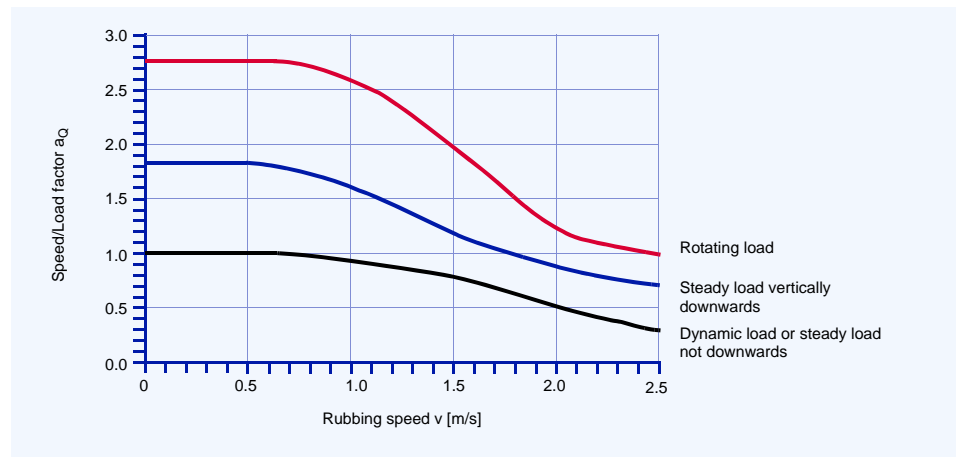


Fig. 15: Speed/Load factor a_Q for PM range and MB range bushes - machined

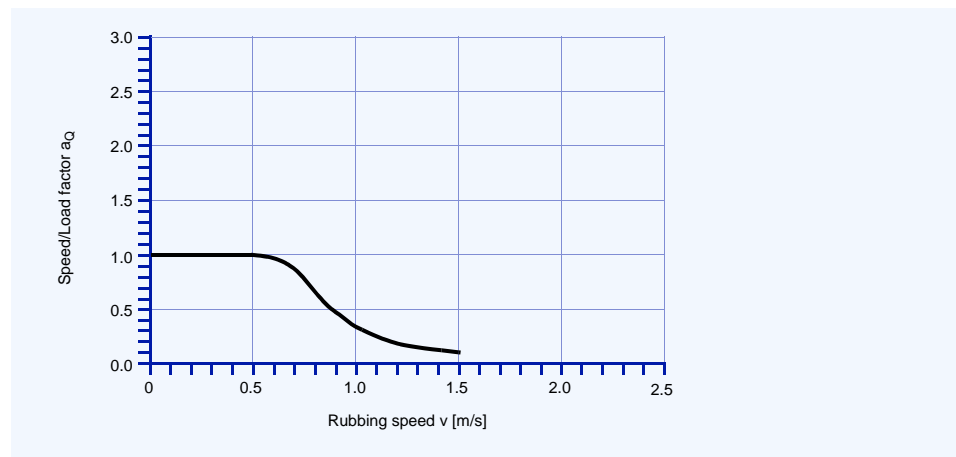


Fig. 16: Speed/Load factor a_Q for thrust washers

Note: $a_Q = 1$ for sideways

5.5 Temperature

The useful life of a DX bearing depends upon the operating temperature. The performance of grease lubricated DX decreases at bearing temperatures above 40 °C. This loss of performance is related to both material and lubricant effects.

For a given pv Factor the operating temperature of the bearing depends upon the

temperature of the surrounding environment and the heat dissipation properties of the housing.

In calculating the service life of DX these effects are accommodated by the application factor a_T shown in Fig. 17.

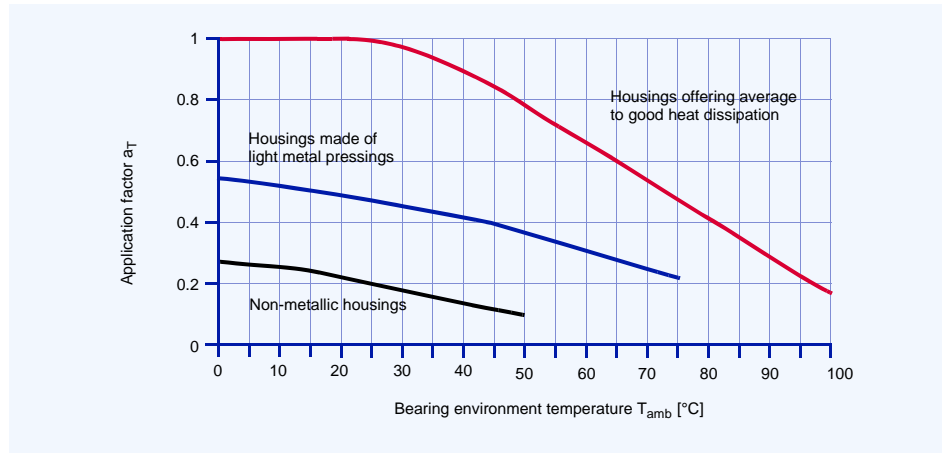


Fig. 17: DX application factor a_T

5.6 Mating Surface

The wear rate of DX is strongly dependent upon the roughness of the mating counterface. For optimum bearing performance the mating surface should be ground to

better than $0.4 \mu m R_a$. This effect is accommodated by the mating surface finish application factor a_S shown in Fig. 18.

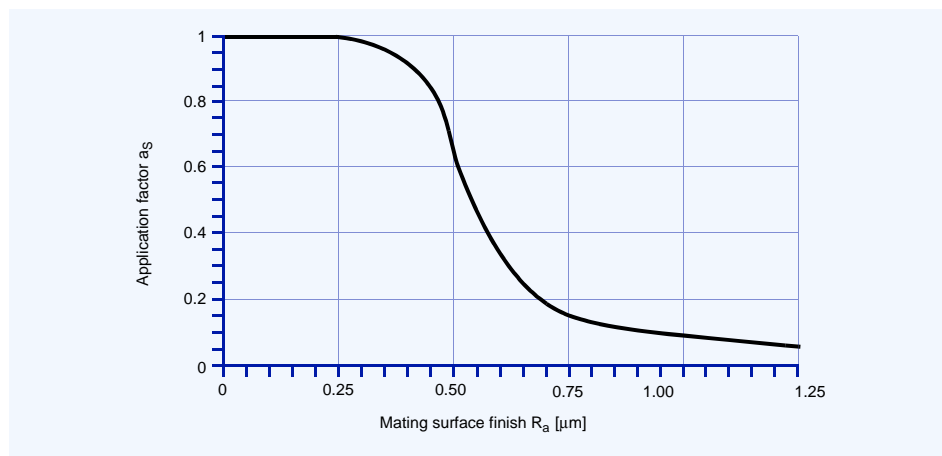


Fig. 18: DX application factor a_S

5.7 Bearing Size

Frictional heat generated at the bearing surface and dissipated through the shaft and housing depends both on the operating conditions (i.e. pv factor) and the bearing size.

For a give pv condition a large bearing will run hotter than a smaller bearing. The bearing size factor a_B shown in Fig. 19 takes account of this effect.

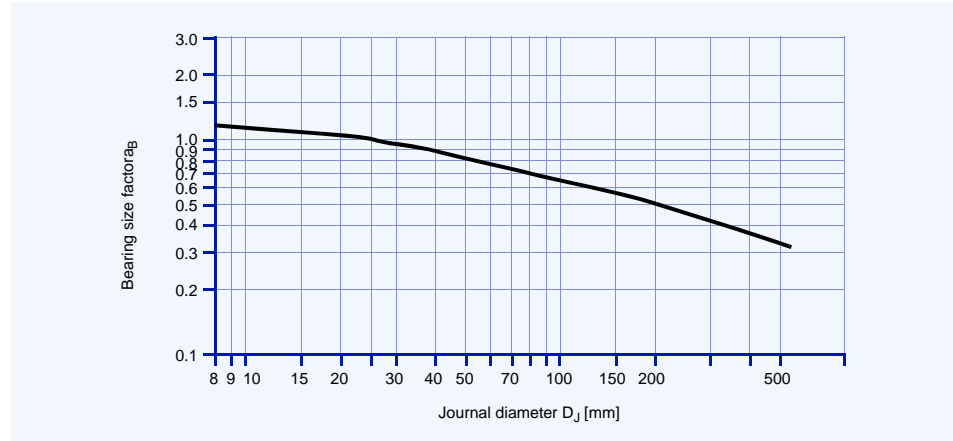


Fig. 19: Bearing size factor a_B

Note: $a_B = 1$ for slideways

5.8 Estimation of Bearing Service Life with Grease Lubrication

Calculation Parameters

Bushes		Thrust Washers		Slide Plates		Unit
Bearing diameter	D_i	Bearing outside diameter	D_o	Strip Length	L	[mm]
Bearing width	B	Bearing inside diameter	D_i	Strip Width	W	[mm]

Operating Conditions

Load	F	[N]
Rotational Speed (Continuous)	n	[1/min]
Oscillating Frequency	n_{osc}	[1/min]
Angular movement about mean position	φ	[°]
Specific Load Limit	see Table 5, Page 13	[MPa]
Application Factor a_Q	see Fig. 14-17, Page 16	[-]
Application Factor a_T	see Fig. 17, Page 17	[-]
Application Factor a_S	see Fig. 18, Page 17	[-]
Bearing Size Factor a_B	see Fig. 19, Page 18	[-]

Calculate p from the equations in 5.1 on Page 13.

Calculate v from the equations in 5.2 on Page 14.

Calculate pv from the equation in 5.3 on Page 15.

Calculate High Load Factor a_E

$$(5.8.1) \quad a_E = \frac{p_{lim}}{p_{lim} - p} \quad [-]$$

p_{lim} see Table 5, Page 13

Note:

If $a_E > 10000$, or $a_E < 0$, the bearing is overloaded.

Calculate Effective pv Factor epv

$$(5.8.2) \quad epv = \frac{a_E \cdot pv}{a_B} \quad [-]$$

Note:

Check that epv is less than the limit for the sliding speed v set in Fig. 11. If NOT,

increase the bearing length or use continuous lubrication.

Estimate Bearing Life

If $epv < 1.0$ then

$$(5.8.3) \quad L_H = \frac{3000}{epv} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

If $epv > 1.0$ then

$$(5.8.4) \quad L_H = \frac{3000}{(epv)^{2.4}} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

Estimate Re-greasing Interval

$$(5.8.5) \quad L_{RG} = \frac{L_H}{2} \quad [h]$$

Oscillating Motion and Dynamic Loads

Oscillating Motion

Calculate number of cycles

$$(5.8.6) \quad Z_T = L_{RG} \cdot n_{osc} \cdot 60 \cdot (R + 2) \quad [-]$$

Dynamic Loads

Calculate number of cycles

$$(5.8.7) \quad C_T = L_{RG} \cdot C \cdot 60 \cdot (R + 2) \quad [-]$$

where R = Number of times bearing is regreased during total life required.

Check that Z_T (or C_T) is less than the total number of cycles Q given in Fig. 9 for actual bearing specific load p .

If Z_T (or C_T) $> Q$ then life will be limited by fatigue after Q cycles.

If Z_T (or C_T) $< Q$ then life will be limited by wear after Z_T cycles.

If the estimated life or total cycles are insufficient or the regreasing intervals are too frequent, increase the bearing length or diameter, or consider drip feed or continuous oil lubrication, the quantity to be established by test.

5.9 Worked Examples

PM cylindrical Bush

Given			
Load Details	Steady Load	Inside Diameter D_i	40 mm
	Direction: down	Length B	30 mm
Shaft	Steel	Bearing Load F	15000 N
	ambient Temperature	Rotational Speed N	30 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	70 MPa	(Table 5, Page 13)	
Application Factor a_T	1.0	(Fig. 17, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 18, Page 17)	
Bearing Size Factor a_B for ϕ 40	0.98	(Fig. 19, Page 18)	
Application Factor for PM bush a_Q	1.8	(Fig. 15, Page 16)	

Calculation	Ref	Value
Specific Load p [MPa]	(5.1.1), page 13	$p = \frac{F}{D_i \cdot B} = \frac{15000}{40 \cdot 30} = 12.5$
Sliding Speed v [m/s]	(5.2.1), page 14	$v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} = \frac{40 \cdot \pi \cdot 30}{60000} = 0.063$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{p_{lim}}{p_{lim} - p} = \frac{70}{70 - 12.5} = 1.22$
epv Factor [-]	(5.8.3), page 19	$epv = \frac{a_E \cdot p \cdot v}{a_B} = \frac{1.22 \cdot 12.5 \cdot 0.063}{0.98} = 0.98$
Life L_H [h] for $epv < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epv} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.98} \cdot 1.8 \cdot 1.0 \cdot 0.98 = 5400$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{5400}{2} = 2700$

PM cylindrical Bush

Given			
Load Details	Steady Load	Inside Diameter D_i	90 mm
	Direction: up	Length B	60 mm
Shaft	Steel	Bearing Load F	45000 N
	Temperature 80 °C	Rotational Speed N	20 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit p_{lim} at 80 °C	46.7 MPa	(Table 5, Page 13)	
Application Factor a_T	0.4	(Fig. 17, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 18, Page 17)	
Bearing Size Factor a_B for ϕ 40	0.70	(Fig. 19, Page 18)	
Application Factor for PM bush a_Q	1.0	(Fig. 15, Page 16)	

Calculation	Ref	Value
Specific Load p [MPa]	(5.1.1), page 13	$p = \frac{F}{D_i \cdot B} = \frac{45000}{90 \cdot 60} = 8.33$
Sliding Speed v [m/s]	(5.2.1), page 14	$v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} = \frac{90 \cdot \pi \cdot 20}{60000} = 0.094$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{p_{lim}}{p_{lim} - p} = \frac{46.7}{46.7 - 8.33} = 1.22$
epv Factor [-]	(5.8.3), page 19	$epv = \frac{a_E \cdot p \cdot v}{a_B} = \frac{1.22 \cdot 8.33 \cdot 0.094}{0.70} = 1.36$
Life L_H [h] for $epv < 1$	(5.8.3), page 19	$L_H = \frac{3000}{(epv)^{2.4}} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{1.36^{2.4}} \cdot 1.0 \cdot 0.4 \cdot 0.98 = 562$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{562}{2} = 281$

Thrust washer

Given			
Load Details	Steady Load	Inside Diameter D_i	26 mm
	Direction: down	Outside Diameter D_o	44 mm
Shaft	Steel	Bearing Load F	10000 N
	ambient Temperature	Rotational Speed N	10 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	70 MPa	(Table 5, Page 13)	
Application Factor a_T	1.0	(Fig. 17, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 18, Page 17)	
Bearing Size Factor a_B for ϕ 35	0.90	(Fig. 19, Page 18)	
Application Factor for Thrust washers a_Q	1.0	(Fig. 16, Page 16)	

Calculation	Ref	Value
Specific Load p [MPa]	(5.1.2), page 13	$p = \frac{4 \cdot F}{\pi \cdot (D_o^2 - D_i^2)} = \frac{4 \cdot 10000}{\pi \cdot (44^2 - 26^2)} = 10.11$
Sliding Speed v [m/s]	(5.2.2), page 14	$v = \frac{D_o + D_i}{2} \cdot \pi \cdot n = \frac{44 + 26}{2} \cdot \pi \cdot 10 = \frac{60 \cdot 10^3}{60 \cdot 10^3} = 0.018$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{p_{lim}}{p_{lim} - p} = \frac{70}{70 - 10.11} = 1.169$
epv Factor [-]	(5.8.2), page 19	$epv = \frac{a_E \cdot p \cdot v}{a_B} = \frac{1.169 \cdot 10.11 \cdot 0.018}{0.90} = 0.236$
Life L_H [h] for $epv < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epv} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.236} \cdot 1.0 \cdot 1.0 \cdot 0.98 = 12460$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{12460}{2} = 6230$

Slideways

Given			
Load Details	Steady Load	Length L	50 mm
	Direction: down	Width W	20 mm
Mating Surface	Steel ($R_a = 0.3 \mu\text{m}$)	Bearing Load F	20000 N
	Temperature 80 °C	Stroke	15 mm
	good heat conditions	Frequency	10 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim} at 80 °C	93 MPa	(Table 5, Page 13)	
Application Factor a_T	0.4	(Fig. 17, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 18, Page 17)	
Bearing Size Factor a_B	1.0	(Fig. 19, Page 18)	
Application Factor for Slideways a_Q	1.0	(Fig. 16, Page 16)	

Calculation	Ref	Value
Specific Load p [MPa]	(5.1.3), page 13	$p = \frac{F}{L \cdot W} = \frac{20000}{50 \cdot 20} = 20$
Sliding Speed v [m/s]		$v = \frac{15 \cdot 2 \cdot 10}{60 \cdot 10^3} = 0.005$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{p_{lim}}{p_{lim} - p} = \frac{93}{93 - 20} = 1.27$
epv Factor [-]	(5.8.2), page 19	$epv = \frac{a_E \cdot p \cdot v}{a_B} = \frac{1.27 \cdot 20 \cdot 0.005}{1.0} = 0.127$
Life L_H [h] for $epv < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epv} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.127} \cdot 1.0 \cdot 0.4 \cdot 0.98 = 9260$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{9260}{2} = 4630$

6 Bearing Assembly

6.1 Dimensions and Tolerances

For optimum performance it is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

6.2 Tolerances for minimum clearance

Grease lubrication

The minimum clearance required for satisfactory performance of DX depends upon the pv factor, the sliding speed and the environmental temperature, any one or combination of which may reduce the diametral clearance in operation due to inward thermal expansion of the DX polymer lining. It is therefore necessary to compensate for this.

Fig. 20 shows the minimum diametral clearance plotted stepped against journal diameter at an ambient 20 °C. Where the stepped lines show a change of clearance for a given journal diameter, the lower value is used.

The superimposed straight lines indicate the minimum permissible diametral clear-

ance for various values of pvu (Fig. 20), where pv is calculated as in 5.3 on Page 15, and u is a sliding speed factor for speeds in excess of 0.5 m/s given in Fig. 21.

If the clearance indicated for a pvu factor lies below the stepped lines the recommended standard shaft may be used. If above, the shaft size must be reduced to obtain the clearance indicated on the vertical axis of the relevant figure.

Under slow speed and high load conditions it may be possible to achieve satisfactory performance with diametral clearances less than those indicated. But adequate prototype testing is recommended in such cases.

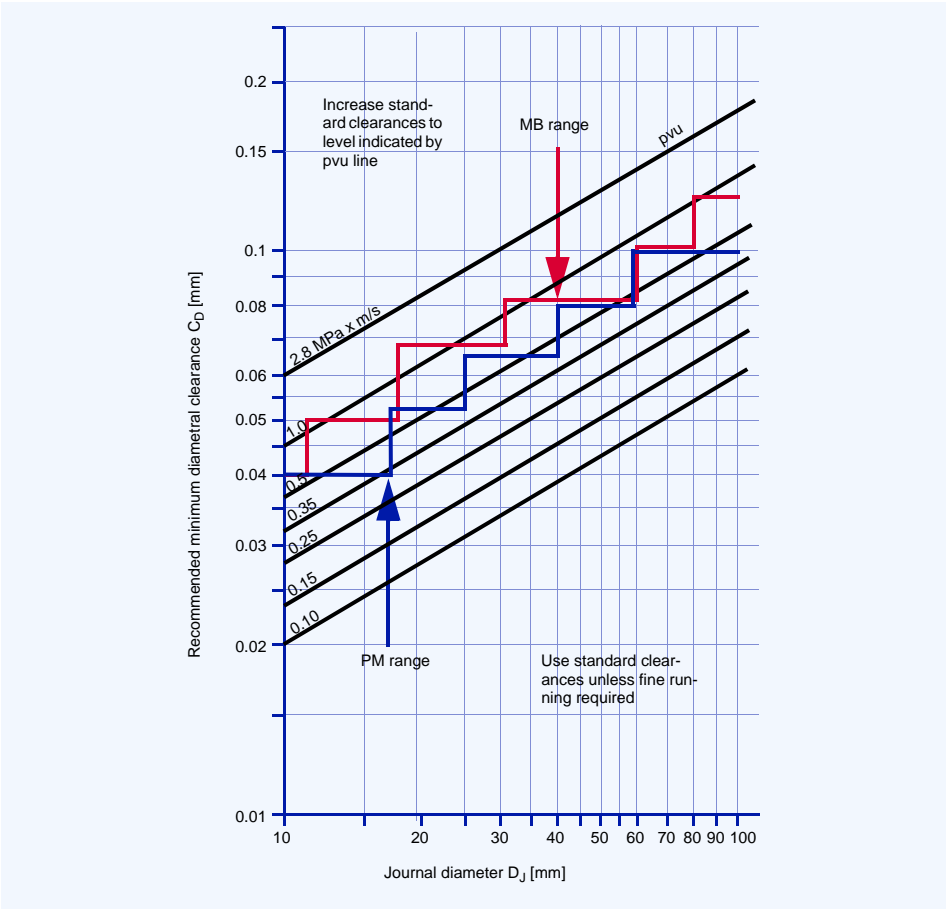


Fig. 20: Minimum clearance for PM prefinished and MB machinable metric range machined to H7 bore

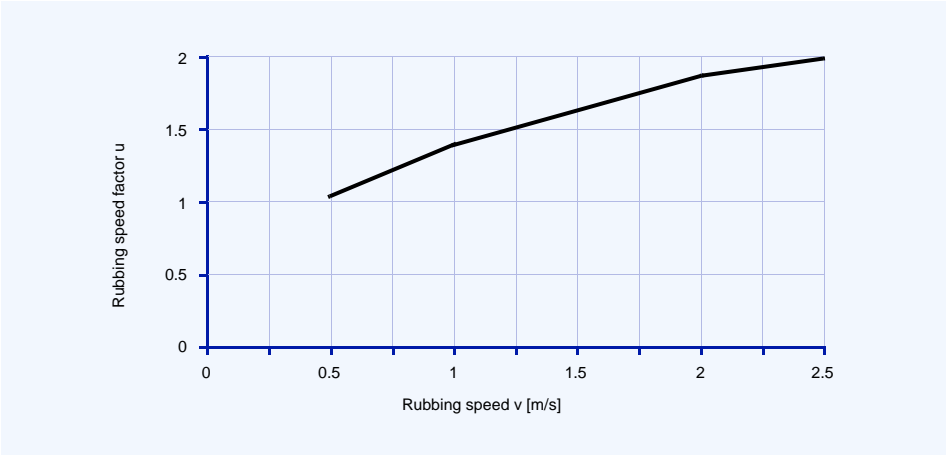


Fig. 21: Rubbing speed factor u

Fluid Lubrication

The minimum clearance required for journal bearings operating under hydrodynamic or mixed film conditions for a range of shaft rotational speeds and diameters is

shown in Fig. 22. It is recommended that the bearing performance under minimum clearance conditions be confirmed by testing if possible.

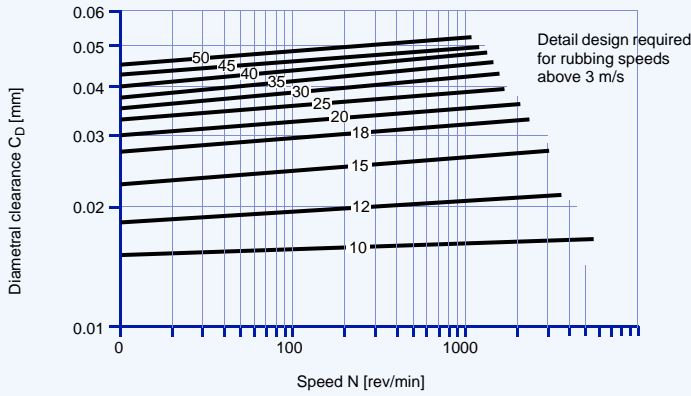


Fig. 22: DX minimum clearances - bush diameters D_i 10-50 mm

Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 23 to

compensate for the inward thermal expansion of the bearing lining.

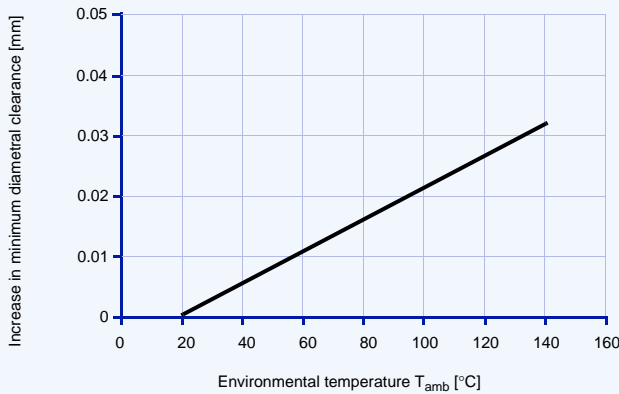


Fig. 23: Recommended increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 6, in order to give an increased inter-

ference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 23.

Housing material	Reduction in housing diameter per 100 °C rise	Reduction in shaft diameter per 100 °C rise
Aluminium alloys	0.1%	0.1% + values from Fig. 23
Copper base alloys	0.05%	0.05% + values from Fig. 23
Steel and cast iron	Nil	values from Fig. 23
Zinc base alloys	0.15%	0.15% + values from Fig. 23

Table 6: Allowance for high temperature

6.3 Counterface Design

DX bearings may be used with all conventional mating surface materials. Hardening of steel journals is not required unless abrasive dirt is present or if the projected bearing life is in excess of 2000 hours, in which cases a minimum shaft hardness of 350 HB is recommended.

A ground surface finish of better than $0.4 \mu\text{m } R_a$ is recommended. The final direction of machining of the mating surface should preferably be the same as the direction of motion relative to the bearing in service.

DX is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings stainless steel or hard chromium plated mild steel, alterna-

tively WH shaft sleeves (Standard programme available) are recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DX bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft polymer lining of the DX must be removed.

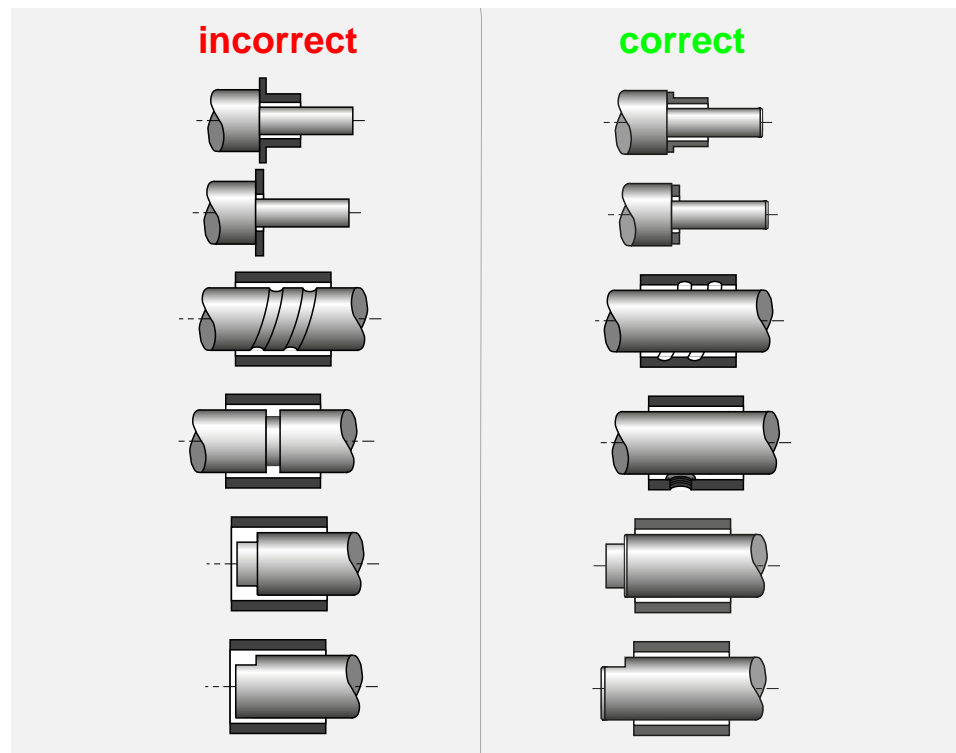


Fig. 24: Counterface design

6.4 Installation

Important Note

Care must be taken to ensure that the DX lining material is not damaged during the installation.

Fitting of Bushes

The bush is inserted into its housing with the aid of a stepped mandrel, preferably made from case hardened mild steel, as shown in Fig. 25. The following should be noted to avoid damage to the bearing:

- Housing diameter is as recommended
- 15-30° lead-in chamfer on housing
- edges of lead-in chamfer are deburred
- The bush must be square to the housing
- Light smear of oil on bush OD

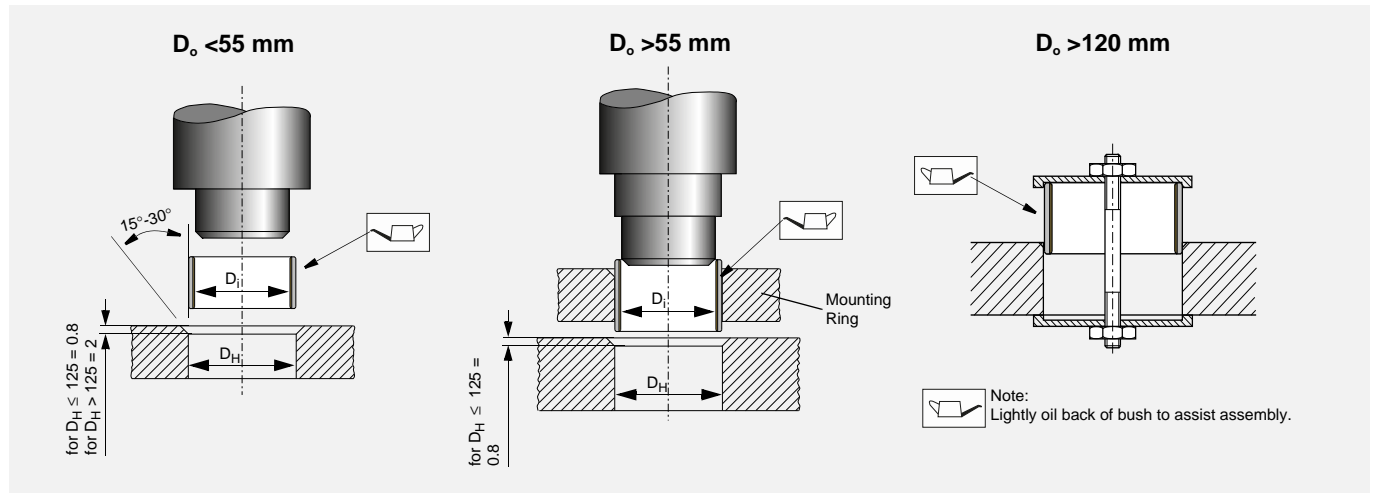


Fig. 25: Fitting of bushes

Insertion Forces

Fig. 26 gives an indication of the maximum insertion force required to correctly install standard DX bushes.

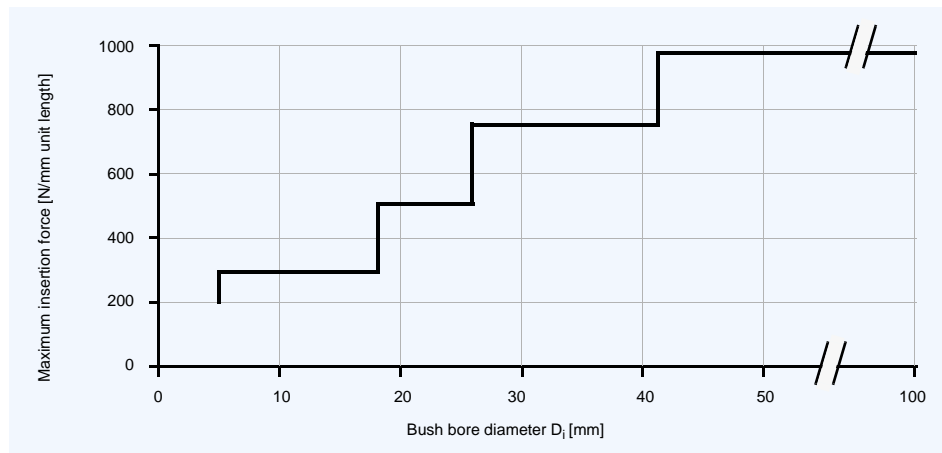


Fig. 26: Maximum insertion force F_i

Alignment

Accurate alignment is an important consideration for all bearing assemblies. With DX bearings misalignment over the length of a

bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 27.

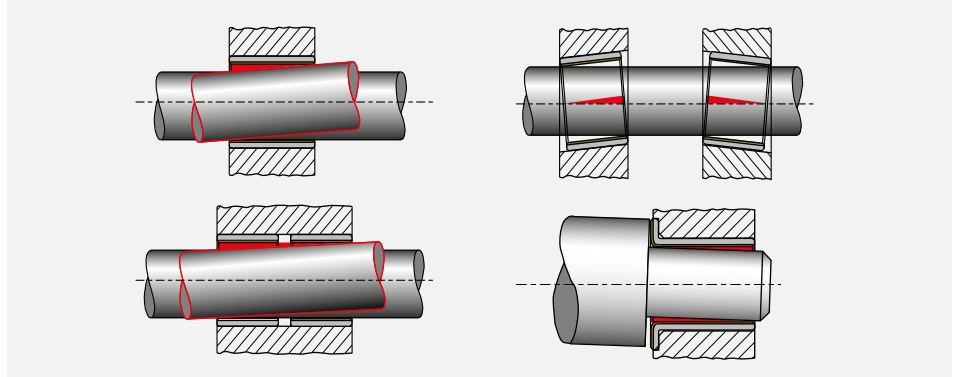


Fig. 27: Alignment

Sealing

While DX can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly abrasive material

entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 28 should be provided.

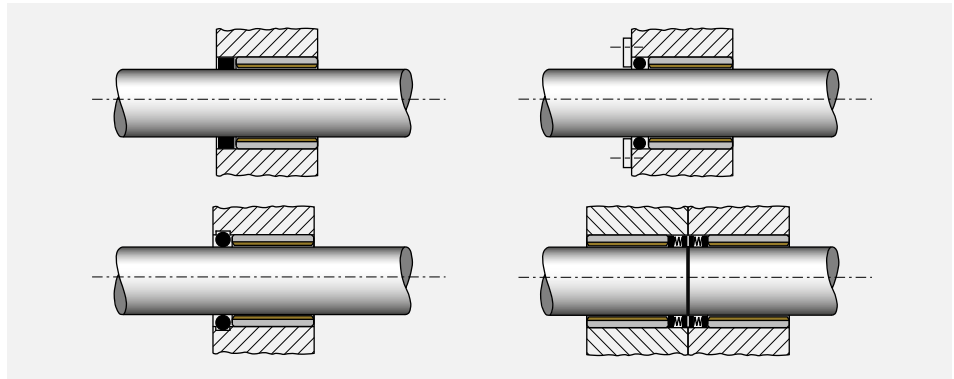


Fig. 28: Recommended sealing arrangements

Axial Location

Where axial location is necessary, it is generally advisable to fit DX thrust washers in conjunction with DX bushes, even when the axial loads are low. Experience has

shown that fretting debris from unsatisfactory locating surfaces can enter an adjacent DX bush and adversely affect the bearing life and performance.

Fitting of Thrust Washers

DX thrust washers should be located on the outside diameter in a recess as shown in Fig. 29. The inside diameter must be clear of the shaft in order to prevent contact with the steel backing of the DX material. The recess diameter should be 0.125 mm larger than the washer diameter and the depth as given in the product tables.

If there is no recess for the thrust washer one of the following methods of fixing may be used:

- two dowel pins
- two screws
- adhesive.

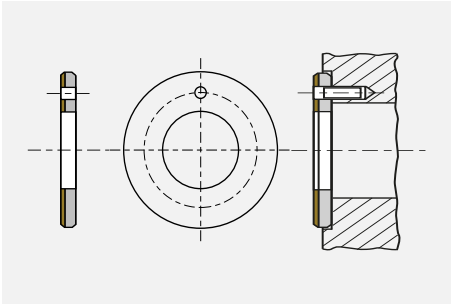


Fig. 29: Installation of Thrust-Washer

Important Note

- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DX must not be heated above 130 °C
- Contact adhesive manufacturers for guidance on the selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive
- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing.

Slideways

DX strip material for use as slideway bearings should be installed using one of the following methods:

- countersunk screws
- adhesives
- mechanical location.

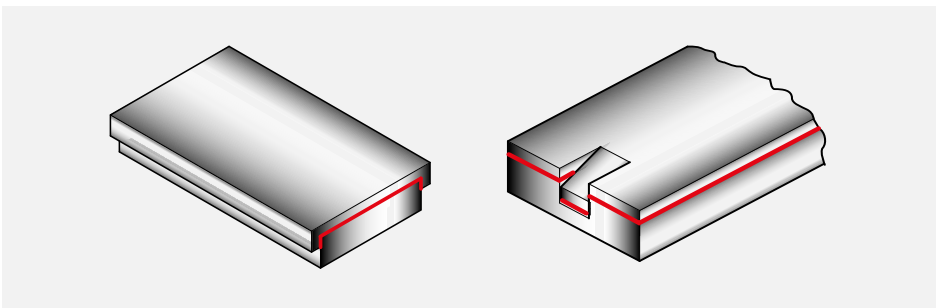


Fig. 30: Mechanical location of DX slideways

7 Machining

7.1 Machining Practice

The acetal copolymer lining of DX has good machining characteristics and can be treated as a free cutting brass in most respects. The indents in the bearing surface may lead to the formation of burrs or whiskers due to the resilience of the lining material, but this can be avoided by using machining methods which remove the lining as a ribbon, rather than a narrow thread.

When machining DX it is recommended that not more than 0.125 mm is removed from the lining thickness in order to ensure that the lubricant capacity of the indents remaining after machining is not significantly reduced.

Boring, reaming and broaching are all suitable machining methods for use with DX. The recommended tool material is high speed steel or tungsten carbide.

7.2 Boring

Fig. 31 illustrates a recommended boring tool which should be mounted with its axis at right angles to the direction of feed.

The essential characteristic required in the boring tool is a tip radius greater than 1.5 mm, which combined with a side rake of 30° will produce the ribbon effect required.

Cutting speeds should be high, the optimum between 2.0 and 4.5 m/s. The feed should be low, in the range 0.05/0.025 mm for cuts of 0.125 mm, the lower feeds being used with the higher cutting speeds.

Satisfactory finishes can usually be obtained machining dry and an air blast may facilitate swarf removal. The use of coolant is not detrimental.

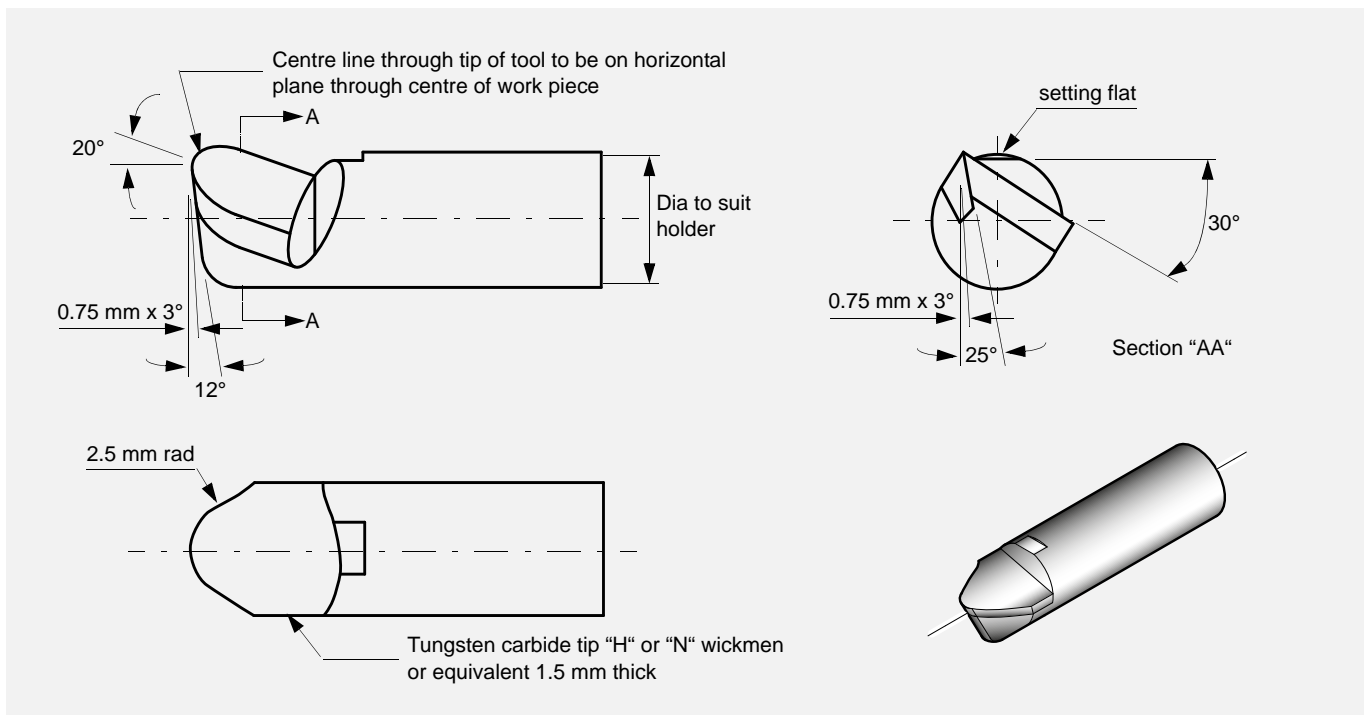


Fig. 31: Boring tool for DX

7.3 Reaming

MB-DX-bushes can be reamed satisfactorily by hand with a straight-fluted expanding reamer. For best results the reamer should be sharp, the cut 0.025-0.050 mm

and the feed slow. Where hand reaming is not desired machining speeds of about 0.05 m/s are recommended with the cuts and feeds as for boring.

7.4 Broaching

Fig. 32 shows broaches suitable for finishing MB-DX-bushes up to 65 mm diameter.

The broach should be used dry, at a speed of 0.1-0.5 m/s.

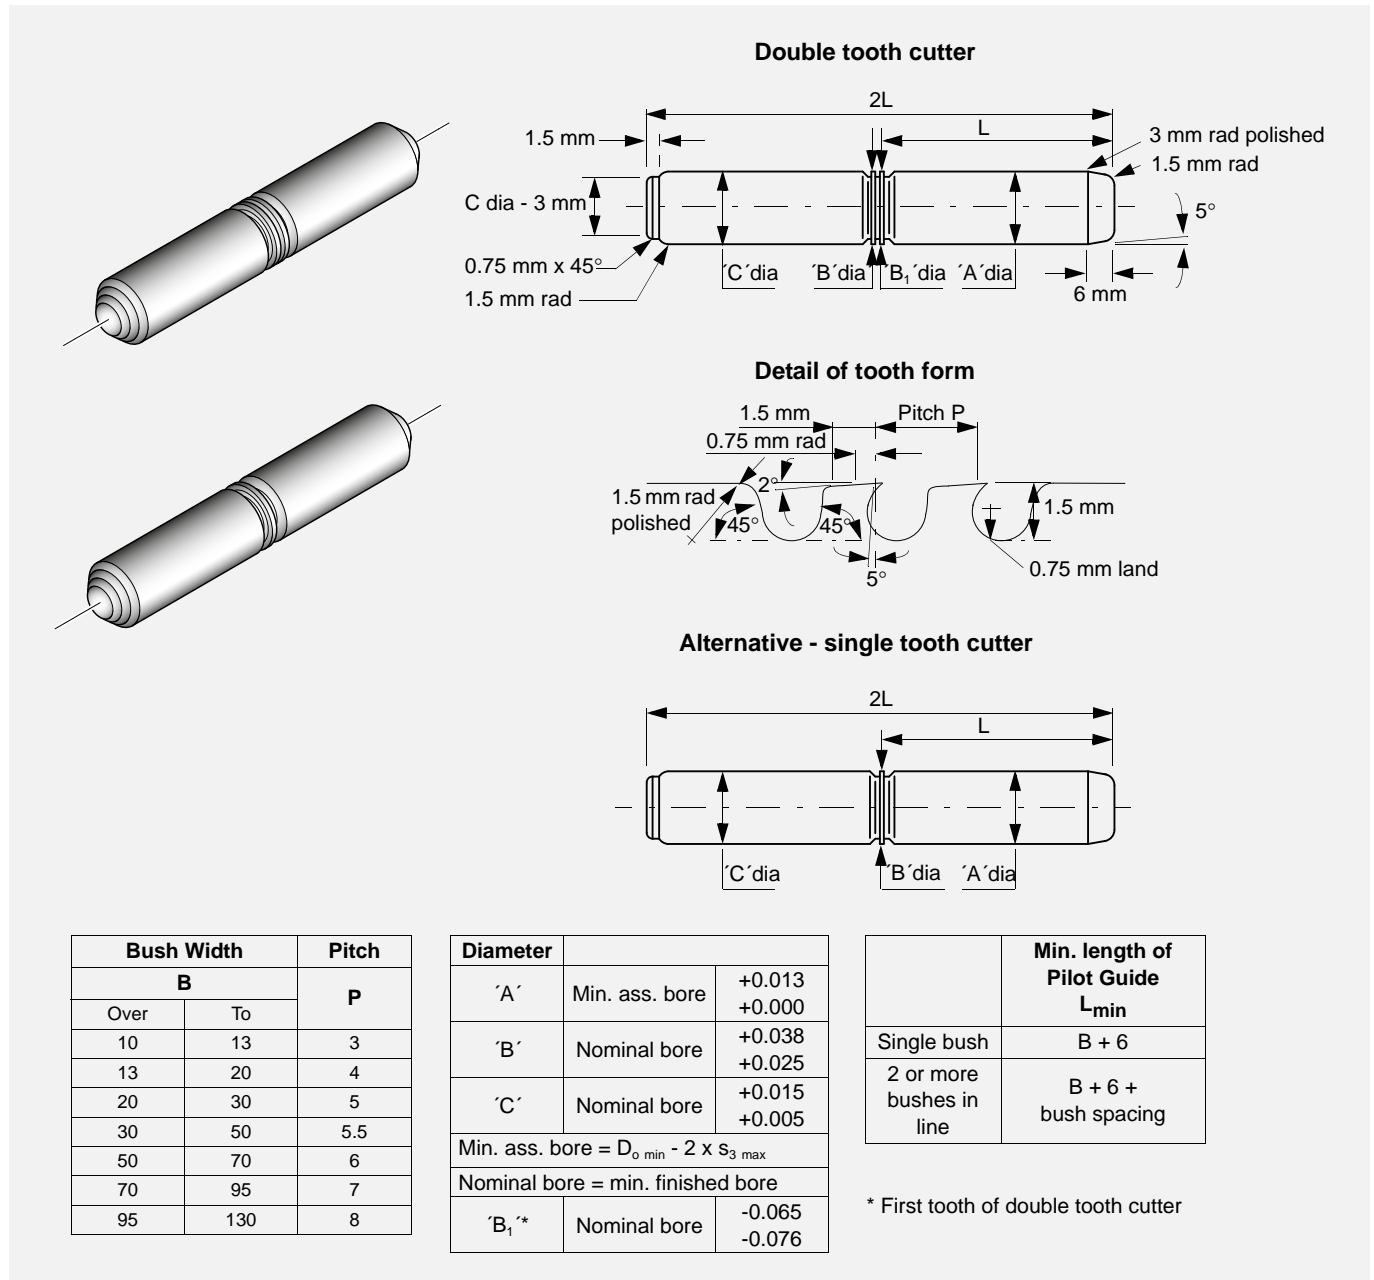


Fig. 32: Suitable broaches for MB-DX

Use the single tooth version where the bush is less than 25 mm long, and the double tooth broach for longer bushes or for two or more bushes together.

If it is necessary to make up a special form of broach the following points should be noted:

- Adequate provision should be made for locating the bush by providing a pilot to suit the bore of the bush when pressed home. A rear support shoulder should locate in the broached bore of the bush after cutting. Alternatively, special guides may be provided external to the workpiece.
- If two bushes are to be broached in line, then the pilot guide and rear support should be longer than the distance between the two bushes.
- For large bushes it may be necessary to provide axial relief along the length of the pilot guide and rear support, in order to reduce the broaching forces.
- Unless a guided broach is used, the tool will follow the initial bore alignment of the bush, broaching cannot improve concentricity and parallelism unless external guides are used.

In general owing to the variation in wall thickness of large diameter bushes, broaching is not suitable for finishing bores

of more than 60 mm diameter unless external guides are used.

7.5 Vibrobroaching

This technique may also be used. A single cutter is propelled with progressive reciprocating motion with a vibration frequency of typically 50 Hz. The cutter should have a primary rake of 1.5° for 0.5 mm. A cut of

0.25 mm on diameter may be made at an average cutting speed of 0.15 m/s to give a surface finish of better than $0.8 \mu\text{m } R_a$, which is acceptable.

7.6 Modification of components

The modification of DX bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the polymer lining side in order to avoid burrs. When cutting is done from the steel side,

the minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

7.7 Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

7.8 Cutting Strip Material

DX strip material may be cut to size by any one of the following methods. Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs.

- Using side and face cutter, or slitting saw, with the strip held flat and securely on a horizontal milling machine.
- Cropping
- Guillotine (For widths less than 90 mm only)
- Water-jet cutting, Laser cutting

7.9 Electroplating

DX Components

To provide corrosion protection the mild steel backing of DX may be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081-2
- cadmium ISO 2081-2
- nickel ISO 1456-8
- hard chromium ISO 1456-8.

For the harder materials if the specified plating thickness exceeds approximately 5 μm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.


Mating Surfaces

DX can be used against hard chrome plated materials and care should be taken to ensure that the recommended shaft

sizes and surface finish are achieved after the plating process.

8 Standard Products

8.1 PM-DX cylindrical bushes

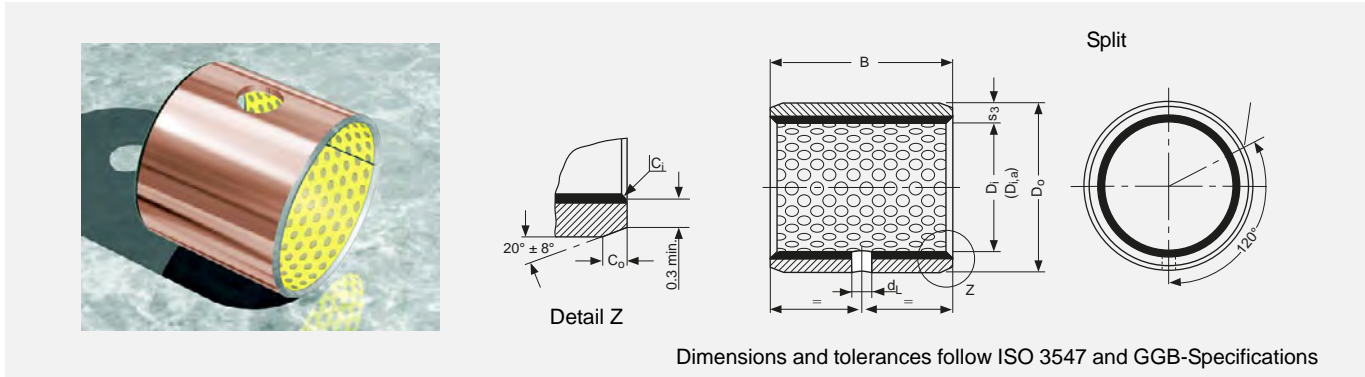

All dimensions in mm

Outside Co and Inside Ci chamfers

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s ₃	C ₀ (a)		C _i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C₀ machined or rolled at the opinion of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s ₃ max. min.	Width B max. min.	Shaft-ø D _J [h8]		Housing-ø D _H [H7]		Bush-ø D _{i,a} Ass. in H7 housing max. min.	Clearance C _D max. min.	Oil hole-ø d _L		
	D _i	D _o			max. min.	max. min.	max. min.	max. min.					
PM0808DX	8	10	0.980 0.955	8.25	8.000	10.015	8.105	0.127	No hole				
PM0810DX				7.75						7.978	10.000	8.040	0.040
PM0812DX				10.25						9.75	10.000	10.108	0.130
PM1010DX	10	12		12.25	10.000	12.018	10.108	0.130		0.040			
PM1012DX				11.75							9.75	12.000	10.040
PM1015DX				15.25							14.75	12.000	10.040
PM1020DX	12	14		20.25	12.000	14.018	12.108	0.135		0.040			
PM1210DX				19.75							11.75	14.000	12.040
PM1212DX				10.25							9.75	14.000	12.040
PM1215DX	12	14		15.25	12.000	14.018	12.108	0.135		0.040			
PM1220DX				14.75							11.75	14.000	12.040
PM1225DX				20.25							19.75	14.000	12.040
PM1415DX	14	16		25.25	14.000	16.018	14.108	0.135		0.040			
PM1420DX				24.75							13.973	16.000	14.040
PM1425DX				15.25							14.75	16.000	14.040
PM1508DX	15	17	8.25	15.000	17.018	15.108	0.135	0.040					
PM1510DX			7.75						14.973	17.000	15.040		
PM1510DX			10.25						9.75	17.000	15.040		

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Wall thickness S ₃ max. min.	Width B max. min.	Shaft-ø D _J [h8]		Housing-ø D _H [H7]		Bush-ø D _{i,a} Ass. in H7 housing max. min.	Clearance C _D max. min.	Oil hole-ø d _L		
	D _i	D _o			max. min.	max. min.	max. min.	max. min.					
PM1512DX	15	17	0.980 0.955	12.25	15.000	14.973	17.018	15.108	15.040	0.135 0.040	4		
PM1515DX				11.75									
PM1520DX				15.25									
PM1525DX				14.75									
PM1615DX	16	18	0.980 0.955	20.25	16.000	15.973	18.018	16.108	16.040	0.135 0.040		4	
PM1620DX				19.75									
PM1625DX				25.25									
PM1815DX				24.75									
PM1820DX	18	20	0.980 0.955	15.25	18.000	17.973	20.021	18.111	18.040	0.135 0.040			4
PM1825DX				14.75									
PM2010DX				20.25									
PM2015DX				19.75									
PM2020DX	20	23	1.475 1.445	25.25	20.000	19.967	23.021	20.131	20.050	0.164 0.050	6		
PM2025DX				24.75									
PM2030DX				30.25									
PM2215DX				29.75									
PM2220DX	22	25	1.475 1.445	15.25	22.000	21.967	25.021	22.131	22.050	0.164 0.050		6	
PM2225DX				14.75									
PM2230DX				20.25									
PM2415DX				19.75									
PM2420DX	24	27	1.475 1.445	25.25	24.000	23.967	27.021	24.131	24.050	0.164 0.050			6
PM2425DX				24.75									
PM2430DX				30.25									
PM2515DX				29.75									
PM2520DX	25	28	1.970 1.935	15.25	25.000	24.967	28.021	25.131	25.050	0.188 0.060	6		
PM2525DX				14.75									
PM2530DX				20.25									
PM283130DX				19.75									
PM2820DX	28	31	1.970 1.935	30.25	28.000	27.967	31.025	28.135	28.050	0.168 0.050		6	
PM2825DX				29.75									
PM2830DX				20.25									
PM3020DX				19.75									
PM3025DX	30	34	1.970 1.935	25.25	30.000	29.967	32.025	28.155	28.060	0.188 0.060			6
PM3030DX				24.75									
PM3040DX				30.25									
				29.75									
	40.25												
				39.75									

For stock availability please contact your local sales representative

8 Standard Products

Part No.	Nominal Diameter		Wall thickness S_3	Width B	Shaft- \varnothing D_J [h8]		Housing- \varnothing D_H [H7]		Bush- \varnothing $D_{i,a}$ Ass. in H7 housing	Clearance C_D	Oil hole- \varnothing d_L							
	D_i	D_o			max. min.	max. min.	max. min.	max. min.										
PM3220DX	32	36	1.970 1.935	20.25	32.000 31.961	36.025 36.000	32.155 32.060	0.194 0.060	6									
PM3230DX				19.75														
PM3235DX				30.25														
PM3240DX				29.75														
PM3520DX	35	39		35.25						35.000 34.961	39.025 39.000	35.155 35.060	0.194 0.060	6				
PM3530DX				34.75														
PM3535DX				40.25														
PM3540DX				39.75														
PM3550DX	20.25	36.000 35.961		40.025 40.000											36.155 36.060	0.194 0.060	6	
PM3635DX	19.75																	
PM3720DX	30.25																	
PM4020DX	29.75																	
PM4030DX	40		44		35.25	40.000 39.961	44.025 44.000	40.155 40.060	0.194 0.060									6
PM4040DX					34.75													
PM4050DX					40.25													
PM4520DX					39.75													
PM4525DX	45		50		50.25					45.000 44.961	50.025 50.000	45.195 45.080	0.234 0.080	8				
PM4530DX					49.75													
PM4540DX					20.25													
PM4545DX					19.75													
PM4550DX		25.25																
PM5030DX		24.75																
PM5040DX	50	55	30.25	50.000 49.961	55.030 55.000										50.200 50.080	0.239 0.080	8	
PM5045DX			29.75															
PM5050DX			40.25															
PM5060DX			39.75															
PM5520DX	55	60	45.25			55.000 54.954	60.030 60.000	55.200 55.080	0.246 0.080									8
PM5525DX			44.75															
PM5530DX			50.25															
PM5540DX			49.75															
PM5550DX			60.25															
PM5560DX			59.75															

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Wall thickness S_3	Width B		Shaft- \varnothing D_J [h8]		Housing- \varnothing D_H [H7]		Bush- \varnothing $D_{i,a}$ Ass. in H7 housing	Clearance C_D	Oil hole- \varnothing d_L
	D_i	D_o		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.			
PM6030DX	60	65	2.460 2.415	30.25	h8	60.000	59.954	65.030 65.000	60.200 60.080	0.246 0.080	8	
PM6040DX				29.75								
PM6050DX				40.25								
PM6060DX				39.75								
PM6070DX				50.25								
PM6530DX	65	70	2.450 2.384	49.75	h8	65.000	64.954	70.030 70.000	65.262 65.100	0.308 0.100		
PM6540DX				60.25								
PM6550DX				59.75								
PM6560DX				70.25								
PM6570DX				69.75								
PM7030DX	70	75	2.450 2.384	30.25	h8	70.000	69.954	75.030 75.000	70.262 70.100	0.308 0.100		
PM7040DX				29.75								
PM7045DX				40.25								
PM7050DX				39.75								
PM7060DX				45.25								
PM7065DX	44.75											
PM7070DX	75	80	2.450 2.384	50.25	h8	75.000	74.954	80.030 80.000	75.262 75.100	0.313 0.100		
PM7080DX				49.75								
PM7540DX				60.25								
PM7560DX				59.75								
PM7580DX				80.25								
PM8040DX	80	85	2.450 2.384	79.75	h8	80.000	79.954	85.035 85.000	80.267 80.100	0.313 0.100		
PM8050DX				40.50								
PM8060DX				39.50								
PM8080DX				50.50								
PM80100DX				49.50								
PM8530DX	85	90	2.450 2.384	60.50	h8	85.000	84.946	90.035 90.000	85.267 85.100	0.321 0.100		
PM8540DX				59.50								
PM8560DX				80.50								
PM8580DX				79.50								
PM85100DX				100.50								

For stock availability please contact your local sales representative

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3	Width B		Shaft- \varnothing D_J [h8]		Housing- \varnothing D_H [H7]		Bush- \varnothing $D_{i,a}$ Ass. in H7 housing	Clearance C_D	Oil hole- \varnothing d_L
	D_i	D_o		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.			
PM9040DX	90	95	2.450 2.384	40.50	90.000	95.035	90.000	95.035	90.267	0.321 0.100	9.5	
PM9060DX				39.50								
PM9080DX				60.50								
PM9090DX				59.50								
PM90100DX				80.50								
PM9560DX	95	100		79.50	95.000	100.035	95.000	100.035	95.267			
PM95100DX				90.50								
PM10040DX	100	105		89.50	100.000	105.035	99.946	105.000	100.267			
PM10050DX				100.50								
PM10060DX				99.50								
PM10080DX				60.50								
PM10095DX				59.50								
PM100115DX				50.50								
PM10560DX				105								110
PM10565DX	60.50											
PM105110DX	64.50											
PM105115DX	110.50											
PM11050DX	110	115		109.50	110.267	115.035	110.100	115.000	110.267			
PM11060DX				115.50								
PM110100DX				114.50								
PM110110DX			50.50									
PM110115DX			49.50									
PM11550DX	115	120	59.50	115.000	120.035	114.946	120.000	115.267				
PM11570DX			70.50									
PM12060DX			69.95									
PM120100DX	120	125	60.50	120.000	125.040	119.946	125.000	120.280				
PM120110DX			59.50									
PM12560DX	125	130	109.50	125.000	130.040	124.937	130.000	125.280				
PM125100DX			60.50									
PM125110DX			59.50									
PM13050DX	130	135	100.50	130.000	135.040	129.937	135.000	130.280				
PM13060DX			99.50									
PM13080DX			110.50									
PM130100DX			109.50									
PM130100DX			50.50									

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Wall thickness S ₃	Width B		Shaft-ø D _J [h8]		Housing-ø D _H [H7]		Bush-ø D _{i,a} Ass. in H7 housing	Clearance C _D	Oil hole-ø d _L			
	D _i	D _o		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.						
PM13560DX	135	140	2.435 2.380	60.50	h8	H7	135.000 134.937	140.040 140.000	135.280 135.130	0.343 0.130	No hole				
PM13580DX				59.50								80.50			
PM14050DX	140	145		50.50								60.50	140.000	145.040	140.280
PM14060DX				49.50								59.50	139.937	145.000	140.130
PM14080DX				60.50								80.50			
PM140100DX				79.50								79.50			
PM15050DX				100.50								99.50			
PM15060DX	150	155		50.50								60.50	150.000	155.040	150.280
PM15080DX				49.50								59.50	149.937	155.000	150.130
PM150100DX				60.50								80.50			
PM16050DX				79.50								79.50			
PM16060DX				100.50								99.50			
PM16080DX	160	165		50.50								60.50	160.000	165.040	160.280
PM160100DX				49.50								59.50	159.937	165.000	160.130
PM17050DX				60.50								80.50			
PM17060DX				79.50								79.50			
PM17080DX				100.50								99.50			
PM170100DX	170	175		50.50								60.50	170.000	175.040	170.280
PM18050DX				49.50								59.50	169.937	175.000	170.130
PM18060DX				60.50								80.50			
PM18080DX				79.50								79.50			
PM180100DX				100.50								99.50			
PM18050DX	180	185		50.50								60.50	180.000	185.046	180.286
PM19050DX				49.50								59.50	179.937	185.000	180.130
PM19060DX				60.50								80.50			
PM19080DX				79.50								79.50			
PM190100DX				100.50								99.50			
PM190120DX	190	195		119.50								50.50	190.000	195.046	190.286
PM20050DX			49.50	59.50	189.928	195.000	190.130								
PM20060DX			60.50	80.50											
PM20080DX			79.50	79.50											
PM200100DX			100.50	99.50											
PM200120DX	200	205	119.50	50.50	200.000	205.046	200.286								
PM20060DX			49.50	59.50	199.928	205.000	200.130								
PM20080DX			60.50	80.50											
PM200100DX			79.50	79.50											
PM200120DX			100.50	99.50											



For stock availability please contact your local sales representative

8 Standard Products

Part No.	Nominal Diameter		Wall thickness S_3	Width B		Shaft- \emptyset D_J [h8]		Housing- \emptyset D_H [H7]		Bush- \emptyset $D_{I,a}$ Ass. in H7 housing	Clearance C_D	Oil hole- \emptyset d_L
	D_I	D_O		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.			
PM22050DX	220	225	2.435 2.380	50.50	220.000 219.928	225.046 225.000	220.286 220.130	h8	H7	0.358 0.130	No hole	
PM22060DX				49.50								
PM22080DX				60.50								
PM220100DX				59.50								
PM220120DX				80.50								
PM24050DX	240	245		50.50	240.000 239.928	245.046 245.000	240.286 240.130					
PM24060DX				49.50								
PM24080DX				60.50								
PM240100DX				59.50								
PM240120DX				80.50								
PM25050DX	250	255		50.50	250.000 249.928	255.052 255.000	250.292 250.130					
PM25060DX				49.50								
PM25080DX				60.50								
PM250100DX				59.50								
PM250120DX				80.50								
PM26050DX	260	265		50.50	260.000 259.919	265.052 265.000	260.292 260.130					
PM26060DX				49.50								
PM26080DX				60.50								
PM260100DX				59.50								
PM260120DX				80.50								
PM28050DX	280	285	50.50	280.000 279.919	285.052 285.000	280.292 280.130						
PM28060DX			49.50									
PM28080DX			60.50									
PM280100DX			59.50									
PM280120DX			80.50									
PM30050DX	300	305	50.50	300.000 299.919	305.052 305.000	300.292 300.130						
PM30060DX			49.50									
PM30080DX			60.50									
PM300100DX			59.50									
PM300120DX			80.50									

For stock availability please contact your local sales representative

8.2 MB-DX cylindrical bushes

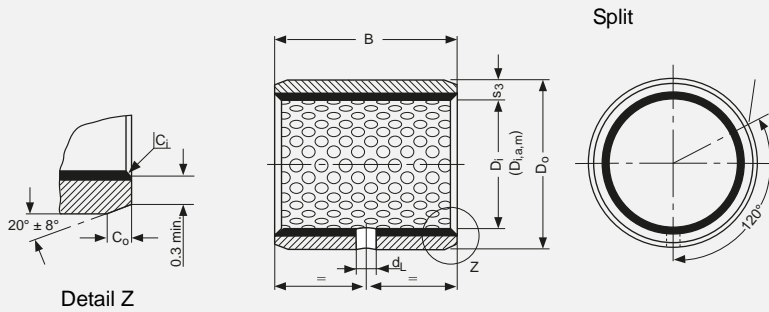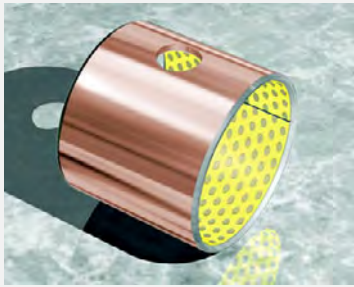

Dimensions and tolerances follow ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C_o and Inside C_i chamfers

Wall thickness s ₃	C _o (a)		C _i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s ₃	C _o (a)		C _i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_o machined or rolled at the opinion of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

* recommended machining depth see page 28

Part No.	Nominal Diameter		Wall thickness s ₃	Width B	Shaft-∅ D _{Jm} [d8]	Housing-∅ D _H [H7]	Bush-∅ D _{i,a,m} Ass. in H7 housing*	Clearance C _{Dm}	Oil hole-∅ d _L
	D _i	D _o							
MB0808DX	8	10	1.108 1.082	8.25	7.960 7.938	10.015 10.000	8.015 8.000	0.077 0.040	No hole
MB0810DX				7.75					
MB0812DX				10.25 9.75					
MB1010DX	10	12		10.25	9.960 9.938	12.018 12.000	10.018 10.000	0.080 0.040	3
MB1012DX				9.75					
MB1015DX				12.25 11.75					4
MB1020DX	12	14		20.25 19.75	11.950 11.923	14.018 14.000	12.018 12.000	0.095 0.050	4
MB1210DX				10.25 9.75					
MB1212DX				12.25 11.75					
MB1215DX	14	16		15.25 14.75	13.950 13.923	16.018 16.000	14.018 14.000	0.095 0.050	4
MB1220DX				20.25 19.75					
MB1225DX				25.25 24.75					
MB1415DX	14	16		15.25 14.75	13.950 13.923	16.018 16.000	14.018 14.000	0.095 0.050	4
MB1420DX				20.25 19.75					
MB1425DX				25.25 24.75					
MB1510DX	15	17	10.25 9.75	14.950 14.923	17.018 17.000	15.018 15.000	0.095 0.050	3	
MB1512DX			12.25 11.75						
MB1515DX			15.25 14.75					4	
MB1525DX	15	17	25.25 24.75	14.950 14.923	17.018 17.000	15.018 15.000	0.095 0.050	4	

For stock availability please contact your local sales representative

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_{Jm} [d8]	Housing- \varnothing D_H [H7]	Bush- \varnothing $D_{i,a,m}$ Ass. in H7 housing*	Clearance C_{Dm}	Oil hole- \varnothing d_L
	D_i	D_o							
MB1615DX	16	18	1.108 1.082	15.25	15.950 15.923	18.018 18.000	16.018 16.000	0.095 0.050	4
MB1620DX				20.25					
MB1625DX				19.75					
MB1815DX	18	20		25.25					
MB1820DX				24.75					
MB1825DX				15.25					
MB2010DX	20	23	14.75	19.935 19.902	23.021 23.000	20.021 20.000	0.119 0.065		
MB2015DX			10.25						
MB2020DX			9.75						
MB2025DX			15.25						
MB2030DX			14.75						
MB2215DX			20.25						
MB2220DX	22	25	19.75	21.935 21.902	25.021 25.000	22.021 22.000	0.119 0.065		
MB2225DX			25.25						
MB2230DX			24.75						
MB2415DX			30.25						
MB2420DX	24	27	29.75	23.935 23.902	27.021 27.000	24.021 24.000	0.119 0.065		
MB2425DX			15.25						
MB2430DX			14.75						
MB2515DX			20.25						
MB2520DX	25	28	19.75	24.935 24.902	28.021 28.000	25.021 25.000	0.119 0.065		
MB2525DX			25.25						
MB2530DX			24.75						
MB2820DX			30.25						
MB2825DX	28	32	29.75	27.935 27.902	32.025 32.000	28.021 28.000	0.119 0.065		
MB2830DX			20.25						
MB3020DX			19.75						
MB3030DX	30	34	2.108 2.072	29.935 29.902	34.025 34.000	30.021 30.000	0.119 0.065		
MB3040DX			30.25						
			29.75						
				40.25					
				39.75					

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Wall thickness S_3	Width B	Shaft- \varnothing D_{Jm} [d8]	Housing- \varnothing D_H [H7]	Bush- \varnothing $D_{i,a,m}$ Ass. in H7 housing*	Clearance C_{Dm}	Oil hole- \varnothing d_L				
	D_i	D_o								max. min.	max. min.	max. min.	max. min.
MB3220DX	32	36	2.108 2.072	20.25	d8	H7	31.920 31.881	36.025 36.000	32.025 32.000	6			
MB3230DX				19.75									
MB3235DX				30.25									
MB3240DX				29.75									
MB3240DX	35.25												
MB3240DX	34.75												
MB3240DX	40.25												
MB3240DX	39.75												
MB3520DX	35	39		20.25							34.920 34.881	39.025 39.000	35.025 35.000
MB3530DX				19.75									
MB3550DX				30.25									
MB3720DX	37	41		29.75							36.920 36.881	41.025 41.000	37.025 37.000
MB4020DX	40	44	20.25	39.920 39.881	44.025 44.000	40.025 40.000	0.144 0.080						
MB4030DX			19.75										
MB4040DX			30.25										
MB4050DX			29.75										
MB4520DX	45	50	40.25	44.920 44.881	50.025 50.000	45.025 45.000							
MB4530DX			19.75										
MB4540DX			30.25										
MB4545DX			29.75										
MB4550DX			45.25										
MB5040DX	50	55	44.75	49.920 49.881	55.030 55.000	50.025 50.000							
MB5060DX			49.75										
MB5520DX			50.25										
MB5525DX	55	60	49.75	54.900 54.854	60.030 60.000	55.030 55.000	0.176 0.100						
MB5530DX			20.25										
MB5540DX			19.75										
MB5550DX			25.25										
MB5560DX			24.75										
MB6030DX			30.25										
MB6040DX	60	65	29.75	59.900 59.854	65.030 65.000	60.030 60.000							
MB6060DX			40.25										
MB6070DX			39.75										
MB6070DX			60.25										
MB6070DX			59.75										
MB6070DX			69.75										

For stock availability please contact your local sales representative

8 Standard Products


Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_{Jm} [d8]	Housing- \varnothing D_H [H7]	Bush- \varnothing $D_{i,a,m}$ Ass. in H7 housing*	Clearance C_{Dm}	Oil hole- \varnothing d_L						
	D_i	D_o								max. min.	max. min.	max. min.	max. min.	max. min.	
MB6540DX	65	70	2.634 2.568	40.25	64.900 64.854	70.030 70.000	65.030 65.000	0.176 0.100	8						
MB6550DX				39.75						50.25					
MB6560DX				49.75						60.25					
MB6570DX				59.75						70.25					
MB7040DX	70	75		40.25	69.900 69.854	75.030 75.000	70.030 70.000			0.176 0.100	8				
MB7050DX				39.75								50.25			
MB7065DX				49.75								65.25			
MB7070DX				59.75								70.25			
MB7080DX	69.75	80.25													
MB7540DX	75	80		40.25	74.900 74.854	80.030 80.000	75.030 75.000					0.176 0.100	8		
MB7560DX				39.75					60.25						
MB7580DX				59.75					80.25						
MB8040DX	80	85		40.50	79.900 79.854	85.035 85.000	80.030 80.000		0.176 0.100					8	
MB8060DX				39.50											60.50
MB8080DX				59.50						80.50					
MB80100DX				79.50						100.50					
MB8530DX	85	90		99.50	84.880 84.826	90.035 90.000	85.035 85.000			0.176 0.100	8				
MB8540DX				30.50											40.50
MB8560DX				29.50											60.50
MB8580DX				39.50								80.50			
MB85100DX			79.50	100.50											
MB9040DX	90	95	99.50	89.880 89.826	95.035 95.000	90.035 90.000	0.209 0.120	9.5							
MB9060DX			40.50						60.50						
MB9090DX			39.50						90.50						
MB90100DX			59.50						100.50						
MB9560DX	95	100	99.50	94.880 94.826	100.035 100.000	95.035 95.000			0.209 0.120			9.5			
MB95100DX			60.50							100.50					
MB10050DX	100	105	99.50	99.880 99.826	105.035 105.000	100.035 100.000				0.209 0.120	9.5				
MB10060DX			50.50										60.50		
MB10080DX			49.50										80.50		
MB10095DX			59.50										95.50		
MB10100DX			79.50				115.50								
MB10115DX			114.50												

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Wall thickness S_3	Width B	Shaft- \varnothing D_{Jm} [d8]	Housing- \varnothing D_H [H7]	Bush- \varnothing $D_{i,a,m}$ Ass. in H7 housing*	Clearance C_{Dm}	Oil hole- \varnothing d_L			
	D_i	D_o								max. min.	max. min.	max. min.
MB10560DX	105	110	2.634 2.568	60.50	d8	H7		0.209 0.120	9.5			
MB105110DX				59.50						104.880	110.035	105.035
MB105115DX				110.50						104.826	110.000	105.000
MB11060DX	110	115		114.50						109.880	115.035	110.035
MB110115DX				60.50						109.826	115.000	110.000
MB11550DX				59.50						114.880	120.035	115.035
MB11570DX	115	120	114.50	114.826	120.000	115.000						
MB12060DX			50.50	119.880	125.040	120.035						
MB120100DX	120	125	49.50	119.826	125.000	120.000						
MB125100DX			70.50	124.855	130.040	125.040						
MB13050DX	130	135	69.50	124.792	130.000	125.000	0.248 0.145	No hole				
MB13060DX			60.50	129.855	135.040	130.040						
MB130100DX			59.50	129.792	135.000	130.000						
MB13560DX	135	140	100.50	134.855	140.040	135.040						
MB13580DX			99.50	134.792	140.000	135.000						
MB14060DX			60.50	139.855	145.040	140.040						
MB140100DX	140	145	59.50	139.792	145.000	140.000						
MB15060DX			100.50	149.855	155.040	150.040						
MB15080DX	150	155	99.50	149.792	155.000	150.000						
MB150100DX			60.50									

For stock availability please contact your local sales representative

8.3 DX Thrust Washers


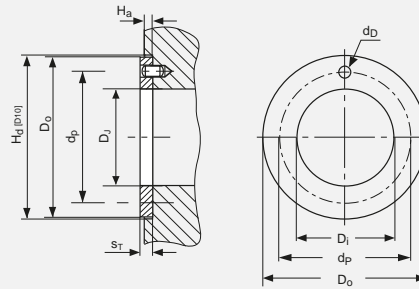


All dimensions in mm

Part No.	Inside- ϕ D_i		Outside- ϕ D_o		Thickness s_T	Dowel hole		Recess depth H_d
	max.	min.	max.	min.		ϕd_p	PCD- ϕd_p	
WC08DX	10.25	10.00	20.00	19.75	1.58 1.49	No hole	No hole	1.20 0.95
WC10DX	12.25	12.00	24.00	23.75		1.875	18.12	
WC12DX	14.25	14.00	26.00	25.75		2.375	20.12	
WC14DX	16.25	16.00	30.00	29.75			2.125	
WC16DX	18.25	18.00	32.00	31.75		3.375	22.12	
WC18DX	20.25	20.00	36.00	35.75			3.125	
WC20DX	22.25	22.00	38.00	37.75		4.375		
WC22DX	24.25	24.00	42.00	41.75			4.125	
WC24DX	26.25	26.00	44.00	43.75		4.375		
WC25DX	28.25	28.00	48.00	47.75			4.125	
WC30DX	32.25	32.00	54.00	53.75		2.60		
WC35DX	38.25	38.00	62.00	61.75			2.51	
WC40DX	42.25	42.00	66.00	65.75		1.70		
WC45DX	48.25	48.00	74.00	73.75			1.45	
WC50DX	52.25	52.00	78.00	77.75	1.70	35.12		
WC60DX	62.25	62.00	90.00	89.75		1.45	34.88	
							38.12	37.88
						43.12	42.88	
						50.12	49.88	
						54.12	53.88	
						61.12	60.88	
						65.12	64.88	
						76.12	75.88	

For stock availability please contact your local sales representative

8.4 DX cylindrical bushes - Inch sizes

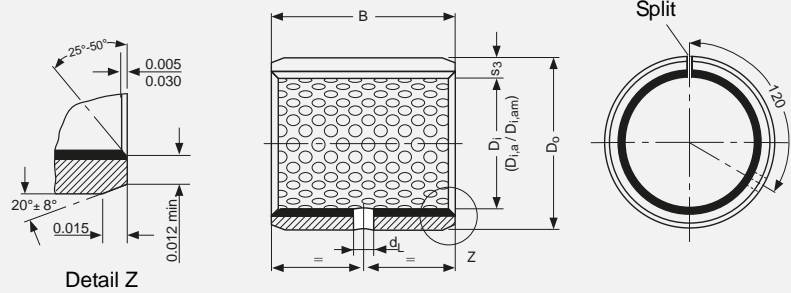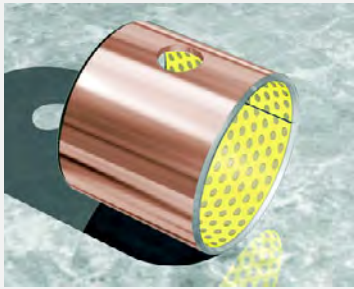

All dimensions in inch

Part No.	Nominal Diameter		Housing- ϕ D_H [BS 1916 H7]	As supplied					Machined in situ			Oil hole- ϕ d_L		
	D_i	D_o		Wall Thickness s_3	Width B	Shaft- ϕ D_J	Bush- ϕ $D_{i,a}$ Ass. in an H7 housing	Clearance C_D	Shaft- ϕ D_{Jm} [BS 1916 d8]	Bush- ϕ $D_{i,am}$ Machined in situ to BS 1916 H7	Clearance C_{Dm}			
			max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.				
06DX06	3/8	15/32	0.4694 0.4687	0.0510 0.0500	0.385 0.365	0.3648 0.3639	0.3694 0.3667	0.0055 0.0019	0.3734 0.3725	0.3756 0.3750	0.0031 0.0016	No hole		
06DX08					0.510 0.490									
06DX12					0.760 0.740									
07DX08	7/16	17/32	0.5319 0.5312		0.510 0.490	0.4273 0.4263	0.4319 0.4292	0.0056 0.0019	0.4355 0.4345	0.4382 0.4375	0.0037 0.0020		5/32	
07DX12					0.760 0.740									
08DX06					1/2									19/32
08DX08	0.510 0.490													
08DX10	0.635 0.615													
08DX14	0.885 0.865													
09DX08	9/16	21/32	0.6569 0.6562		0.510 0.490	0.5522 0.5512	0.5569 0.5542	0.5605 0.5595	0.5632 0.5625	0.0045 0.0025				
09DX12					0.760 0.740									
10DX08					5/8									23/32
10DX10	0.635 0.615													
10DX12	0.760 0.740													
10DX14	0.885 0.865													
11DX14	11/16	25/32	0.7820 0.7812	0.885 0.865	0.6770 0.6760	0.6820 0.6792	0.0060 0.0022	0.6855 0.6845	0.6882 0.6875					
12DX08	3/4	7/8	0.8758 0.8750	0.0669 0.0657	0.510 0.490	0.7390 0.7378	0.7444 0.7412	0.0066 0.0022	0.7475 0.7463			0.7508 0.7500		
12DX12				0.760 0.740										
12DX16				1.010 0.990										

For stock availability please contact your local sales representative

8 Standard Products


Part No.	Nominal Diameter		Housing- ϕ D_H [BS 1916 H7]	As supplied					Machined in situ			Oil hole- ϕ d_L
				Wall Thickness s_3	Width B	Shaft- ϕ D_J	Bush- ϕ $D_{i,a}$ Ass. in an H7 housing	Clearance C_D	Shaft- ϕ $D_{j,m}$ [BS 1916 d8]	Bush- ϕ $D_{i,am}$ Machined in situ to BS 1916 H7	Clearance C_{Dm}	
	D_i	D_o		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.		
14DX12	$7/8$	1	1.0008 1.0000	0.0669 0.0657	0.760	0.8639 0.8627	0.8694 0.8662	0.0067 0.0023	0.8725 0.8713	0.8758 0.8750	0.0045 0.0025	$1/4$
14DX14					0.885							
14DX16					1.010							
16DX12	1	$1/8$	1.1258 1.1250		0.760	0.9888 0.9876	0.9944 0.9912	0.0068 0.0024	0.9975 0.9963	1.0008 1.0000		
16DX16					1.010							
16DX24					1.510							
18DX12	$1/8$	$19/32$	1.2822 1.2812	0.0824 0.0810	0.760	1.1138 1.1126	1.1202 1.1164	0.0076 0.0026	1.1225 1.1213	1.1258 1.2500		
18DX16					0.740							
20DX12					1.010							
20DX16	$1/4$	$13/32$	1.4072 1.4062		0.990	1.2387 1.2371	1.2452 1.2414	0.0081 0.0027	1.2470 1.2454	1.2510 1.2500		
20DX20					1.260							
20DX28					1.240							
22DX16	$3/8$	$17/32$	1.5322 1.5312	1.760	1.3635 1.3619	1.3702 1.3664	0.0083 0.0029	1.3720 1.3704	1.3760 1.3750			
22DX22				1.010								
22DX28				0.990								
24DX16	$1/2$	$121/32$	1.6572 1.6562	0.0980 0.0962	1.010	1.4884 1.4868	1.4952 1.4914	0.0084 0.0030	1.4970 1.4954	1.5010 1.5000		
24DX20					0.990							
24DX24					1.260							
24DX32					1.240							
26DX16	$5/8$	$125/32$	1.7822 1.7812		2.010	1.6133 1.6117	1.6202 1.6164	0.0085 0.0031	1.6220 1.6204	1.6260 1.6250		
26DX24					1.990							
28DX16					1.010							
28DX24	$3/4$	$115/16$	1.9385 1.9375		0.990	1.7383 1.7367	1.7461 1.7415	0.0094 0.0032	1.7470 1.7454	1.7510 1.7500		
28DX28					1.510							
28DX32					1.490							
30DX16					1.760							
30DX30	$7/8$	$21/16$	2.0637 2.0625		1.740	1.8632 1.8616	1.8713 1.8665	0.0097 0.0033	1.8720 1.8704	1.8760 1.8750		
30DX36				2.010								
32DX16				1.990								
32DX24	2	$23/16$	2.1887 2.1875	1.510	1.9881 1.9863	1.9963 1.9915	0.0100 0.0034	1.9960 1.9942	2.0012 2.0000			
32DX32				1.490								
32DX40				2.010								
				1.990								

For stock availability please contact your local sales representative

Part No.	Nominal Diameter		Housing- ϕ D_H [BS 1916 H7]	As supplied					Machined in situ			Oil hole- ϕ d_L								
				Wall Thickness s_3	Width B	Shaft- ϕ D_J	Bush- ϕ $D_{i,a}$ Ass. in an H7 housing	Clearance C_D	Shaft- ϕ D_{Jm} [BS 1916 d8]	Bush- ϕ $D_{i,am}$ Machined in situ to BS 1916 H7	Clearance C_{Dm}									
	D_i	D_o		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.									
36DX32	2 ^{1/4}	2 ^{7/16}	2.4387 2.4375	0.0980 0.0962	2.010	2.2378 2.2360	2.2463 2.2415	0.0103 0.0037	2.2460 2.2442	2.2512 2.2500	0.0070 0.0040	5 ^{1/16}								
36DX36					1.990								2.260	2.510						
36DX40					2.240								2.490	2.490						
40DX32	2 ^{1/2}	2 ^{11/16}	2.6887 2.6875	0.0991 0.0965	2.010	2.4875 2.4857	2.4963 2.4915	0.0106 0.0040	2.4960 2.4942	2.5012 2.5000			0.0086 0.0050	3 ^{1/8}						
40DX40					1.990										2.510	2.490				
44DX32	2 ^{3/4}	2 ^{15/16}	2.9387 2.9375	0.0991 0.0965	2.010	2.7351 2.7333	2.7457 2.7393	0.0124 0.0042	2.7460 2.7442	2.7512 2.7500					0.0086 0.0050	3 ^{1/8}				
44DX40					1.990												2.510	2.490		
44DX48					2.990												3.010	2.990		
44DX56					3.510												3.490	3.490		
48DX32	3	3 ^{3/16}	3.1889 3.1875	0.0991 0.0965	2.010	2.9849 2.9831	2.9959 2.9893	0.0128 0.0044	2.9960 2.9942	3.0012 3.0000							0.0086 0.0050	3 ^{1/8}		
48DX48					1.990														3.010	2.990
48DX60					3.760														3.740	3.740
56DX40	3 ^{1/2}	3 ^{11/16}	3.6889 3.6875	0.0991 0.0965	2.510	3.4844 3.4822	3.4959 3.4893	0.0137 0.0049	3.4950 3.4928	3.5014 3.5000	0.0086 0.0050	3 ^{1/8}								
56DX48					2.490														3.010	2.990
56DX60					3.760														3.740	3.740
64DX48	4	4 ^{3/16}	4.1889 4.1875	0.0991 0.0965	3.010	3.9839 3.9817	3.9959 3.9893	0.0142 0.0054	3.9950 3.9928	4.0014 4.0000			0.0086 0.0050	3 ^{1/8}						
64DX60					2.990														3.760	3.740
64DX76					4.760										4.740	4.740				

For stock availability please contact your local sales representative

8.5 DX Thrust Washers - Inch sizes

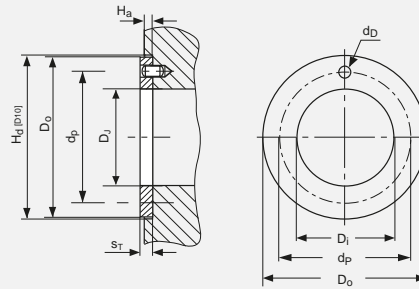


All dimensions in inch

Part No.	Inside- ϕ D_i max. min.	Outside- ϕ D_o max. min.	Thickness s_T max. min.	Dowel hole		Recess depth H_d max. min.
				ϕd_p max. min.	PCD- ϕd_p max. min.	
DX06	0.5100 0.5000	0.8750 0.8650	0.0660 0.0625	0.0770 0.0670	0.6920	0.050 0.040
DX07	0.5720 0.5620	1.0000 0.9900			0.6820	
DX08	0.6350 0.6250	1.1250 1.1150		0.1090 0.0990	0.7860	
DX09	0.6970 0.6870	1.1870 1.1770			0.7760	
DX10	0.7600 0.7500	1.2500 1.2400		0.8800		
DX11	0.8220 0.8120	1.3750 1.3650		0.8700		
DX12	0.8850 0.8750	1.5000 1.4900		0.1400 0.1300	0.9420	
DX14	1.0100 1.0000	1.7500 1.7400			0.9320	
DX16	1.1350 1.1250	2.0000 1.9900		0.1710 0.1610	1.0050	
DX18	1.2600 1.2500	2.1250 2.1150			0.9950	
DX20	1.3850 1.3750	2.2500 2.2400		0.2020 0.1920	1.0990	
DX22	1.5100 1.5000	2.5000 2.4900			1.0890	
DX24	1.6350 1.6250	2.6250 2.6150	0.0970 0.0935	1.1920	0.080 0.070	
DX26	1.7600 1.7500	2.7500 2.7400		1.1820		
DX28	2.0100 2.0000	3.0000 2.9900	0.0970 0.0935	1.3800		
DX30	2.1350 2.1250	3.1250 3.1150		1.3700		
DX32	2.2600 2.2500	3.2500 3.2400		1.5670		
				1.5570		
				1.6920		
				1.6820		
				1.8170		
				1.8070		
				2.0050		
				1.9950		
				2.1300		
				2.1200		
				2.2550		
				2.2450		
				2.5050		
				2.4950		
				2.6300		
				2.6200		
				2.7550		
				2.7450		

For stock availability please contact your local sales representative

8.6 DX Strip

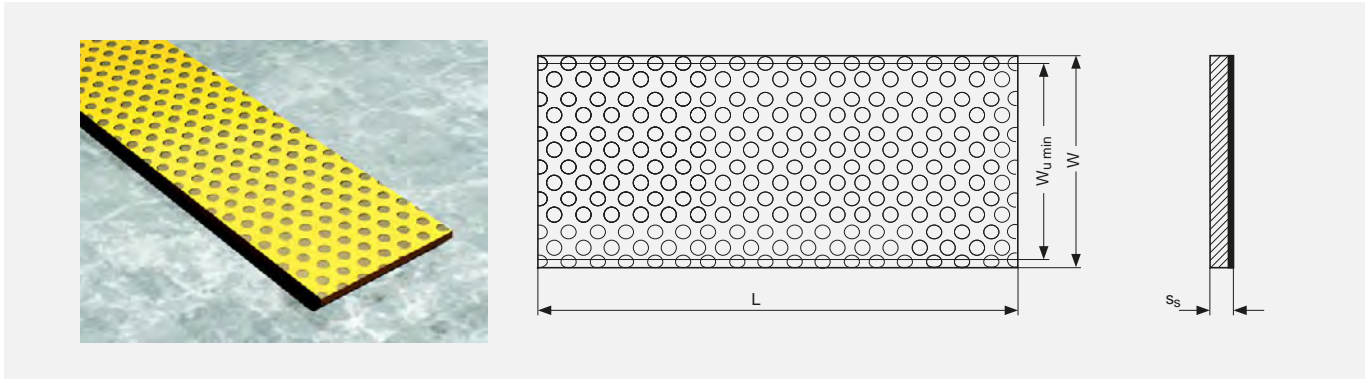

All dimensions in mm

Part No.	Length L	Total Width W	Usable Width $W_{U\ min}$	Thickness s_s	
				max.	min.
S10150DX	503 500	160	150	1.07	1.03
S15190DX		200	190	1.56	1.52
S20190DX				2.05	2.01
S25190DX				2.57	2.53

For stock availability please contact your local sales representative

8.7 DX Strip - Inch sizes

DX Strip Inch sizes are available as Non-Standard products on request.

9 Data Sheet for bearing design

Company:

Project:

Application:

Date:

Existing Design New Design

Quantity Annual


Contact name:

Tel.:

Fax:

Email:

Drawing attached YES NO

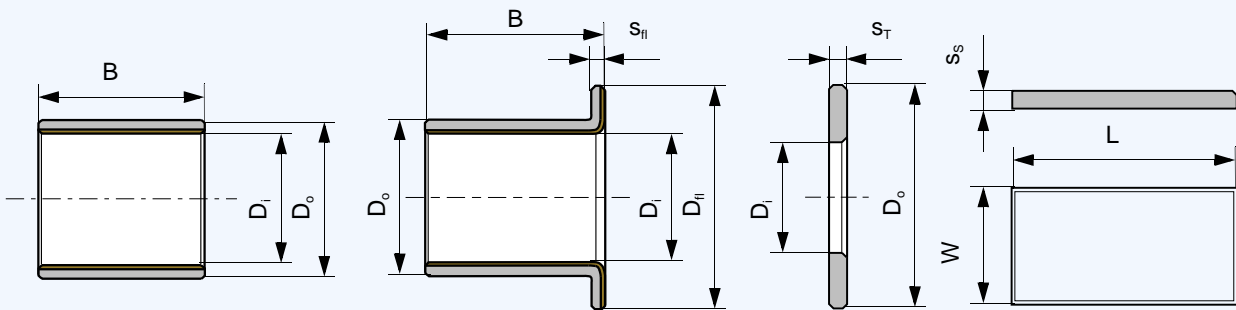

Cylindrical Bush Flanged Bush Thrust Washer Slideplate Special (Sketch)

Steady load Rotating load Rotational movement Oscillating movement Linear movement

Dimensions in mm

Inside Diameter	D_i	<input type="text"/>
Outside Diameter	D_o	<input type="text"/>
Length	B	<input type="text"/>
Flange Diameter	D_{fl}	<input type="text"/>
Flange Thickness	s_{fl}	<input type="text"/>
Length of slideplate	L	<input type="text"/>
Width of slideplate	W	<input type="text"/>
Thickness of slideplate	s_s	<input type="text"/>

Load

Radial load	F [N]	<input type="text"/>
Axial load	F [N]	<input type="text"/>

Movement

Rotational speed	n [1/min]	<input type="text"/>
Speed	v [m/s]	<input type="text"/>
Length of Stroke	L_s [mm]	<input type="text"/>
Frequency of Stroke	[1/min]	<input type="text"/>
Angular displacement	ϕ [°]	<input type="text"/>
Oscillating frequency	n_{osc} [1/min]	<input type="text"/>

Service hours per day

Continuous operation	[h]	<input type="text"/>
Intermittent operation	[h]	<input type="text"/>

Fits and Tolerances

Housing (\emptyset , tolerance)	D_H	<input type="text"/>
Shaft (\emptyset , tolerance)	D_J	<input type="text"/>

Mating surface

Material	<input type="text"/>
Hardness	HB/HRC <input type="text"/>
Surface roughness	R_a [μm] <input type="text"/>

Operating Environment

Temperature - ambient	T_{amb}	<input type="text"/>
Temperature - min/max	T_{min}/T_{max}	<input type="text"/>

Housing material

Assembly with good heat transfer properties

Assembly with poor heat transfer properties

Dry operation With lubricant

If grease, type with technical datasheet

If oil, type with technical datasheet

- Oil splash

- Oil bath

- Oil circulation

Service life

Required service life L_H [h]

Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2009 (This edition replaces earlier editions which hereby lose their validity).

Declaration on lead contents of GGB products/compliance with EU law

Since July 1, 2006 it has been prohibited under Directive 2002/95/EC (restriction of the use of certain hazardous substances in electrical and electronic equipment; ROHS Directive) to put products on the market that contain lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls (PBB) or polybrominated diphenyl ethers (PBDE).

Certain applications listed in the annex to the ROHS Directive are exempted. A maximum concentration value of 0.01% by weight and per homogeneous material, for cadmium and of 0.1% by weight and per homogeneous material, for lead, mercury, hexavalent chromium, PBB and PBDE shall be tolerated.

According to Directive 2000/53/EC on end-of life vehicles, since July 1, 2003 it has been prohibited to put on the market materials and components that contain lead, mercury, cadmium or hexavalent chromium. Due to an exceptional provision, lead-containing bearing shells and bushes could still be put on the market up until July 1, 2008. This general exception expired on July 1, 2008. A maximum concentration value of up to 0.1% by weight and per homogeneous material, for lead, hexavalent chromium and mercury shall be tolerated.

All products of GGB, with the exception of DU, DUB, SY and SP satisfy these requirements of Directives 2002/95/EC (ROHS Directive) and 2000/53/EC (End-of-life Vehicle Directive).

All products manufactured by GGB are also compliant with REACH Regulation (EC) No. 1 907/2006 of December 18, 2006.

DX[®] and DS[™] are trademarks of GGB.

Visit us on the internet:
www.ggbearings.com

