

GGB DU[®] and DU-B[™]

Metal-Polymer Self-lubricating Bearing Solutions



The Global Leader
in High Performance Bearing Solutions




an EnPro Industries company

Quality

All the products described in this handbook are manufactured under DIN EN ISO 9001, ISO/TS 16949 and ISO 14001 approved quality management systems.

In addition GGB North America has been certified AS9100 revision B complying with the requirements of aerospace industry's quality management system for the manufacture of metal-backed bearings and filament wound bearings and washers.

AMERICA

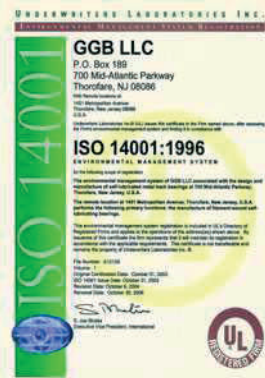

FRANCE



CHINA



GERMANY



BRAZIL



SLOVAKIA



Technical approvals:

Tested and approved by MPA Stuttgart (for DU[®]B) for structural bearings for civil engineering applications.

Content

| | | | |
|---|-----------|---|-----------|
| Quality | I | 4 Data Sheet | 22 |
| Formula Symbols and Designations | II | 4.1 Data for bearing design calculations | 22 |
| Historical | III | 5 Lubrication | 23 |
| 1 Introduction | 5 | 5.1 Lubricants | 23 |
| 1.1 Applications | 5 | 5.2 Tribology | 23 |
| 1.2 Characteristics and Advantages | 5 | Hydrodynamic lubrication | 23 |
| 1.3 Basic Forms Available | 5 | Mixed film lubrication | 24 |
| 1.4 Materials | 6 | Boundary lubrication | 24 |
| 2 Material | 7 | 5.3 Characteristics of Lubricated DU bearings | 24 |
| 2.1 Structure | 7 | 5.4 Design Guidance for Lubricated Applications | 24 |
| 2.2 Dry Wear Mechanism | 7 | 5.5 Clearances for lubricated operation | 26 |
| 2.3 Physical, Mechanical and Electrical Properties | 9 | 5.6 Mating Surface Finish for lubricated operation | 26 |
| 2.4 Chemical Properties | 10 | 5.7 Grooving for lubricated operation | 26 |
| Electrochemical Corrosion | 10 | 5.8 Grease Lubrication | 26 |
| 2.5 Frictional Properties | 10 | 6 Bearing Assembly | 27 |
| 3 Performance | 12 | Dimensions and Tolerances | 27 |
| 3.1 Design Factors | 12 | 6.1 Allowance for Thermal Expansion | 27 |
| Calculation | 12 | 6.2 Tolerances for minimum clearance | 27 |
| 3.2 Specific Load \bar{p} | 12 | Sizing | 28 |
| 3.3 Specific Load Limit \bar{p}_{lim} | 13 | 6.3 Counterface Design | 28 |
| 3.4 Sliding Speed U | 13 | 6.4 Installation | 29 |
| Continuous Rotation | 13 | Fitting of cylindrical bushes | 29 |
| Oscillating Movement | 13 | Fitting of flanged bushes | 29 |
| 3.5 $\bar{p}U$ Factor | 14 | Insertion Forces | 29 |
| 3.6 Application Factors | 14 | Alignment | 30 |
| Temperature | 14 | Sealing | 30 |
| Mating Surface | 15 | 6.5 Axial Location | 30 |
| Bearing Size | 15 | Fitting of Thrust Washers | 30 |
| Bore Burnishing | 16 | Slideways | 31 |
| Type of Load | 16 | 7 Modification | 32 |
| 3.7 Calculation of Bearing Size .. | 17 | 7.1 Cutting and Machining | 32 |
| Calculation for Bushes | 17 | Drilling Oil Holes | 32 |
| Calculation for Thrust Washers .. | 17 | Cutting Strip Material | 32 |
| Calculation for Slideways | 17 | 7.2 Electroplating | 32 |
| 3.8 Calculation of Bearing Service Life .. | 18 | DU Components | 32 |
| Specific load p | 18 | Mating Surfaces | 32 |
| High load factor a_E | 18 | | |
| Modified $\bar{p}U$ Factor | 18 | | |
| Estimation of bearing life L_H | 19 | | |
| Bore Burnishing | 19 | | |
| Slideways | 19 | | |
| 3.9 Worked Examples | 20 | | |

| | | | | | |
|----------|---------------------------------------|-----------|------------|--|-----------|
| 8 | Standard Products | 33 | 8.9 | DU Strip | 50 |
| 8.1 | DU Cylindrical Bushes | 33 | 8.10 | DUB Strip | 50 |
| 8.2 | DU Flanged Bushes | 38 | 8.11 | DU Strip - Inch sizes | 50 |
| 8.3 | DU Flanged Washers | 40 | 9 | Test Methods | 51 |
| 8.4 | DU Thrust Washer | 41 | 9.1 | Measurement of | |
| 8.5 | DUB Cylindrical Bushes | 42 | | Wrapped Bushes | 51 |
| 8.6 | DUB Flanged Bushes | 44 | | Test A of ISO 3547 Part 2 | 51 |
| 8.7 | DU Cylindrical Bushes - Inch sizes | 45 | | Test B (alternatively to Test A) | 51 |
| 8.8 | DU Thrust Washers - Inch sizes | 49 | | Test C | 51 |
| | | | | Measurement of Wall Thickness (alternatively to Test C) | 51 |
| | | | | Test D | 51 |

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DU[®] bearings.

The information given permits designers to establish the correct size of bearing required and the expected life and performance.

GGB Research and Development services are available to assist with unusual design problems.

Complete information on the range of DU standard stock products is given together with details of other DU products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worth-while to contact the Company should additional information be required.

As it is impossible to cover all conditions of operation which arise in practice, customers are advised to carry out prototype testing wherever possible.

1.1 Applications

DU is suitable for

- rotating,
- oscillating,
- reciprocating and
- sliding movements.

Also available are DU related material compositions for specific applications, for

example when increased corrosion resistance of the bearing material is required due to

- atmospheric or environmental considerations
- food safety regulations

1.2 Characteristics and Advantages

- **DU requires no lubrication**
- **Provides maintenance free operation**
- **DU has a high pU capability**
- **DU exhibits low wear rate**
- **Seizure resistant**
- **Suitable for temperatures from -200 to +280 °C**
- **High static and dynamic load capacity**
- **Good frictional properties with negligible stick-slip**
- **Resists solvents**
- **No water absorption and therefore dimensionally stable**
- **DU is electrically conductive and shows no electrostatic effects**
- **DU has good embedability and is tolerant of dusty environments**
- **Compact and light**
- **DU bearings are prefinished and require no machining after assembly**

1.3 Basic Forms Available

Standard Components available from stock.

These products are manufactured to International, National or GGB standard designs.

Metric and Imperial sizes

- Cylindrical Bushes
- Flanged Bushes *
- Thrust Washers
- Flanged Washers *
- Strip Material

* Metric sizes only

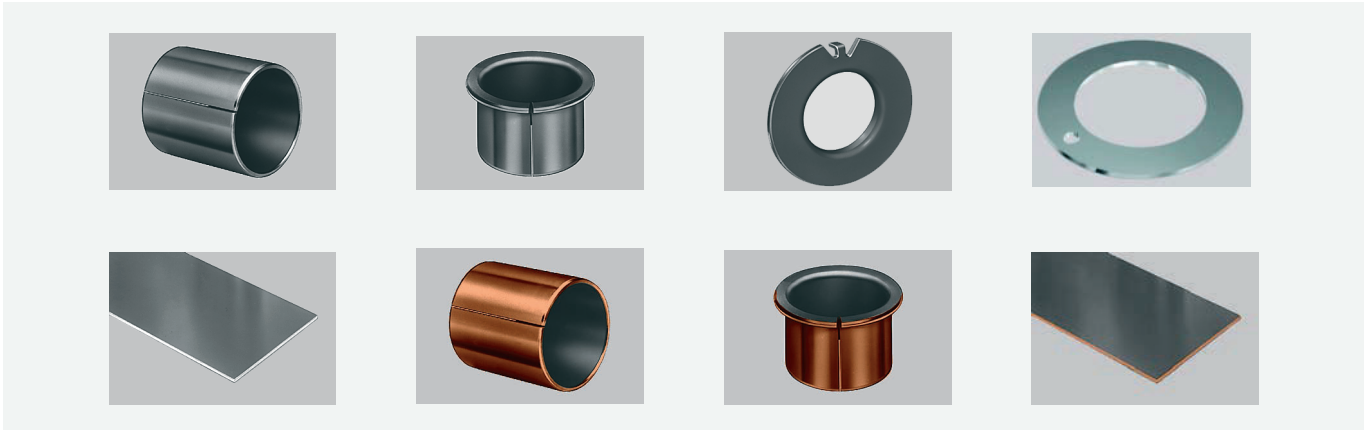


Fig. 1: Standard Components

Non-Standard Components not available from stock.

These products are manufactured to customers' requirements with or without GGB recommendations, and include for example

- Modified Standard Components

- Half Bearings
- Flat Components
- Deep Drawn Parts
- Pressings
- Stampings



Fig. 2: Non-Standard Components

1.4 Materials

| Material | Backing | Bearing Lining | Operating Temperature [°C] | | Maximum Load \bar{p}_{lim} [N/mm ²] |
|----------|---------|----------------|----------------------------|---------|---|
| | | | Minimum | Maximum | |
| DU | Steel | PTFE+Lead | -200 | +280 | 250 |
| DUB | Bronze | PTFE+Lead | -200 | +280 | 140 |

Table 1: Characteristics of DU and DUB

2 Material

2.1 Structure

DU

DU and DUB take advantage of the outstanding dry bearing properties of Polytetrafluoroethylene (PTFE) and combines them with strength, stability and good wear resistance, excellent heat conductivity and low thermal expansion.

DU consists of three bonded layers: a steel backing strip and a porous bronze matrix, impregnated and overlaid with the PTFE/lead bearing material.

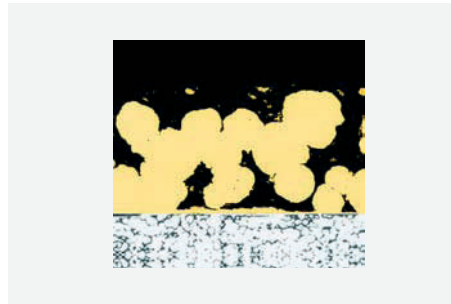


Fig. 3: DU Microsection

DUB

DUB also consists of three layers, with a bronze backing replacing the steel backing strip. The structure is otherwise the same as that of DU.

The bronze backing provides a high corrosion resistance, anti magnetic properties and a good thermal conductivity.



Fig. 4: DUB Microsection

2.2 Dry Wear Mechanism

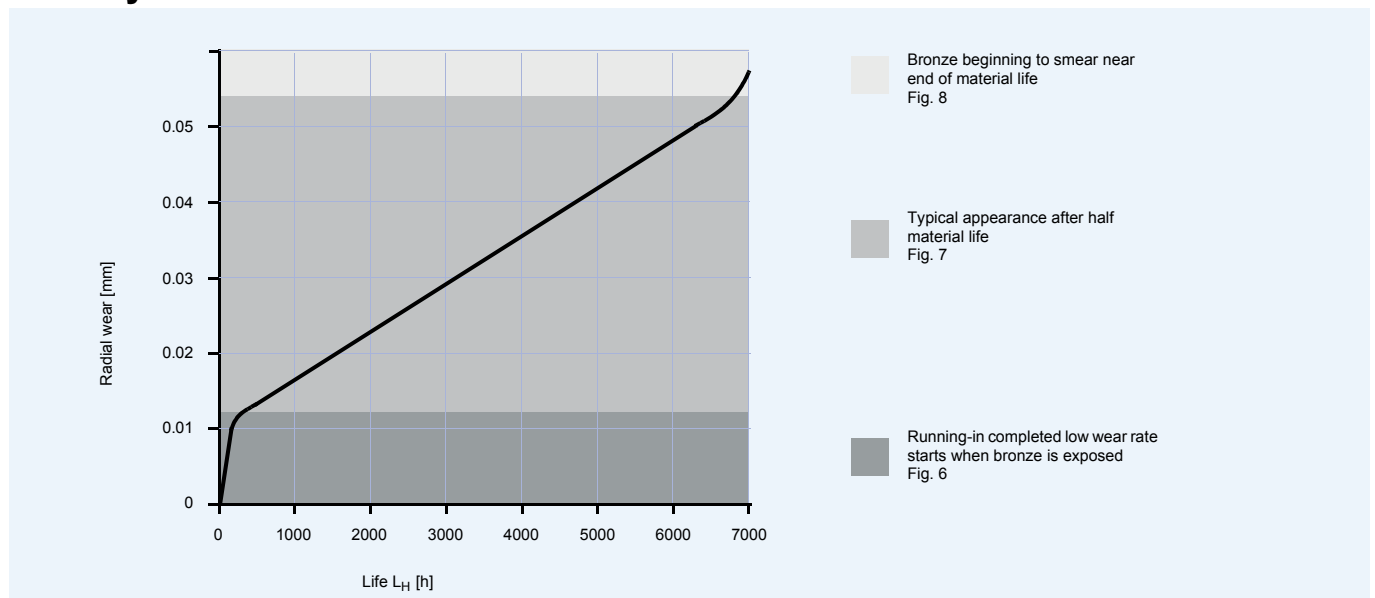


Fig. 5: Effect of wear on the DU bearing surface under dry operating conditions.

Running-in

During normal operation, a DU bearing quickly beds in and the PTFE/lead overlay material removed during this period, typically 0.015 mm, is transferred to the mating surface and forms a physically bonded lubricant film.

The rubbing surface of the bearing often acquires a grey-green colour and the bronze matrix can be seen exposed over about 10 % of the bearing surface. Any

excess of the PTFE/lead surface layer will be shed as fine feathery particles.

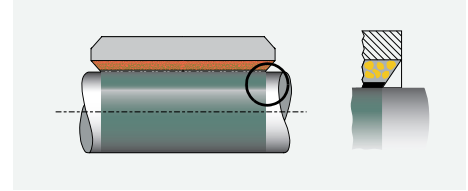


Fig. 6: Running-in

After 50 % of useful life

Following the running-in period the wear rate reduces to a minimum and the percentage of bronze exposed gradually increases.

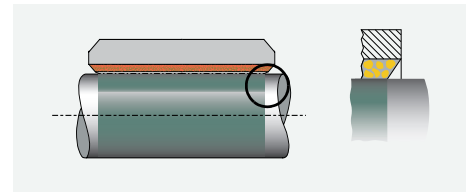


Fig. 7: After 50 % of useful life

End of useful life

After an extended period of operation the wear rate increases as the component approaches the end of its useful life as a self-lubricating bearing. At this stage at least 70 % of the bearing surface will be exposed bronze, and approximately 0.06 mm wear will have occurred.

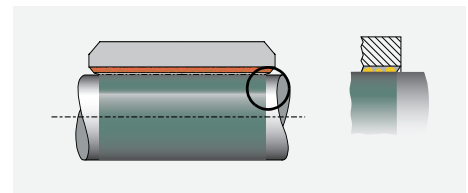


Fig. 8: End of useful life

Wear of Mating Surfaces

There is no measurable wear of mating surfaces made from recommended materials unless a DU bearing is operated

beyond its useful life or becomes contaminated with abrasive dirt.

2.3 Physical, Mechanical and Electrical Properties

| Characteristic | Symbol | Value | | Unit | Comments | |
|-------------------------------|---|---------------------|--------------------|--------------------|---------------------|--|
| | | DU | DUB | | | |
| Physical Properties | Thermal Conductivity | λ | 40 | 60 | W/mK | after running in. |
| | Coefficient of linear thermal expansion : | | | | | measured on strip 1.9 mm thick. |
| | parallel to surface | α_1 | 11 | 18 | 1/10 ⁶ K | |
| | normal to surface | α_2 | 30 | 36 | 1/10 ⁶ K | |
| | Maximum Operating Temperature | T_{max} | +280 | +280 | °C | |
| Minimum Operating Temperature | T_{min} | -200 | -200 | °C | | |
| Mechanical Properties | Compressive Yield Strength | σ_c | 350 | 300 | N/mm ² | measured on disc 25 mm diameter x 2.44 mm thick. |
| | Maximum Load | | | | | |
| | Static | $\bar{p}_{sta,max}$ | 250 | 140 | N/mm ² | |
| | Dynamic | $\bar{p}_{dyn,max}$ | 140 | 140 | N/mm ² | |
| Electrical Properties | Surface Resistance | R_{OB} | 1 – 10 | 1 – 12 | Ω | depends on applied pressure and contact area |
| Nuclear Radiation Resistance | Maximum Thermal Neutron dose | D_{Nth} | 2×10^{15} | 2×10^{15} | nvt | nvt = thermal neutron flux |
| | Maximum gamma ray dose | D_γ | 10^6 | 10^6 | Gy = J/kg | 1 Gray = 1 J/kg |

Table 2: Properties of DU and DUB

2.4 Chemical Properties

The following table provides an indication of the chemical resistance of DU and DUB to various chemical media. It is recom-

ended that the chemical resistance is confirmed by testing if possible.

| | Chemical | % | °C | DU | DUB |
|----------------------|----------------------------|----|----|----|-----|
| Strong Acids | Hydrochloric Acid | 5 | 20 | - | - |
| | Nitric Acid | 5 | 20 | - | - |
| | Sulphuric Acid | 5 | 20 | - | - |
| Weak Acids | Acetic Acid | 5 | 20 | - | o |
| | Formic Acid | 5 | 20 | - | o |
| Bases | Ammonia | 10 | 20 | o | - |
| | Sodium Hydroxide | 5 | 20 | o | o |
| Solvents | Acetone | | 20 | + | + |
| | Carbon Tetrachloride | | 20 | + | + |
| Lubricants and Fuels | Paraffin | | 20 | + | + |
| | Gasolene | | 20 | + | + |
| | Kerosene | | 20 | + | + |
| | Diesel Fuel | | 20 | + | + |
| | Mineral Oil | | 70 | o | o |
| | HFA-ISO46 High Water Fluid | | 70 | o | o |
| | HFC-Water-Glycol | | 70 | - | - |
| | HFD-Phosphate Ester | | 70 | o | o |
| | Water | | 20 | o | + |
| | Sea Water | | 20 | - | o |

Table 3: Chemical Resistance of DU and DUB

| | |
|---|--|
| + | <p>Satisfactory: Corrosion damage is unlikely to occur.</p> |
| o | <p>Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.</p> |
| - | <p>Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.</p> |

Electrochemical Corrosion

DUB should not be used in conjunction with aluminium housings due to the risk of

electrochemical corrosion in the presence of water or moisture.

2.5 Frictional Properties

DU bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of DU depends upon:

- The specific load \bar{p} [N/mm²]
- The sliding speed U [m/s]
- The roughness of the mating running surface R_a [μ m]

- The bearing temperature T [°C].

A typical relationship is shown in Fig. 9, which can be used as a guide to establish the actual friction under clean, dry conditions after running in.

Exact values may vary by $\pm 20\%$ depending on operating conditions.

Before running in, the friction may be up to 50 % higher.

With frequent starts and stops, the static coefficient of friction is approximately equal to, or even slightly less than the dynamic coefficient of friction.

After progressively longer periods of dwell under load (e.g. hours or days) the static

coefficient of friction on the first movement may be between 1.5 and 3 times greater, particularly before running in.

Friction increases at bearing temperatures below 0 °C.

Where frictional characteristics are critical to a design they should be established by prototype testing.

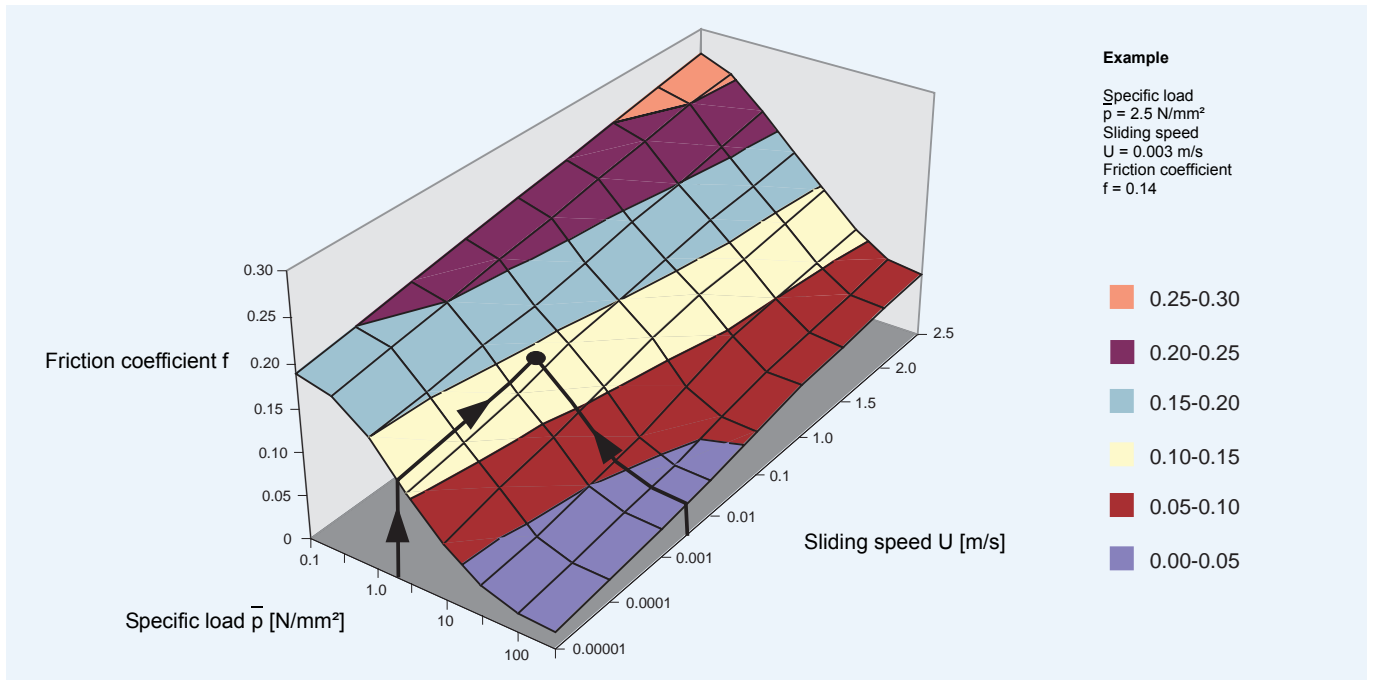


Fig. 9: Variation of friction coefficient f with specific load \bar{p} and sliding speed U at temperature $T = 25 \text{ °C}$

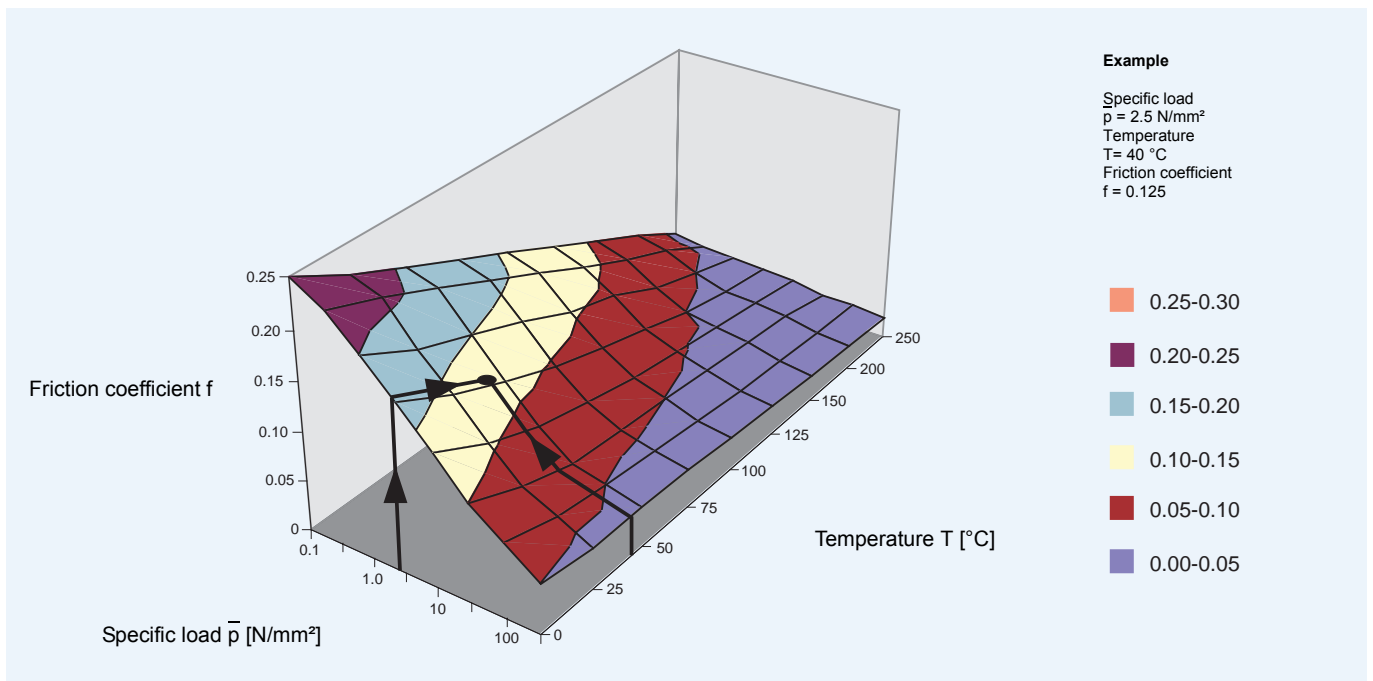


Fig. 10: Variation of friction coefficient f with specific load \bar{p} and temperature T at sliding speed $U = 0.01 \text{ m/s}$

3 Performance

3.1 Design Factors

The main parameters when determining the size or calculating the service life for a DU bearing are:

- Specific Load Limit \bar{p}_{lim}
- $\bar{p}U$ Factor

- Mating surface roughness R_a
- Mating surface material
- Temperature T
- Other environmental factors e.g. housing design, dirt, lubrication

Calculation

Two design procedures are provided as follows:

- A bearing service life calculation based on the permitted bearing dimensions

- A calculation of the necessary bearing dimensions based on the required bearing service life

3.2 Specific Load \bar{p}

For the purpose of assessing bearing performance the specific load \bar{p} is defined as the working load divided by the projected

area of the bearing and is expressed in N/mm^2 .

Cylindrical Bush

(3.2.1) [N/mm²]

$$\bar{p} = \frac{F}{D_i \cdot B}$$

Flanged Bush (Axial Loading)

(3.2.3) [N/mm²]

$$\bar{p} = \frac{F}{0.04 \cdot (D_{fi}^2 - D_i^2)}$$

Thrust Washer

(3.2.2) [N/mm²]

$$\bar{p} = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$

Slideway

(3.2.4) [N/mm²]

$$\bar{p} = \frac{F}{L \cdot W}$$

Permanent deformation of the DU bearing lining may occur at specific loads above $140 N/mm^2$ and under these conditions DU should only be used with slow intermittent movements.

The permissible maximum load on a thrust washer is higher than that on the flange of a flanged bush, and under conditions of high axial loads a thrust washer should be specified.

3.3 Specific Load Limit \bar{p}_{lim}

The maximum load which can be applied to a DU bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit.

In general the specific load on a DU bearing should not exceed the Specific Load Limits given in Table 4.

The values of Specific Load Limit specified in Table 4 assume good alignment between the bearing and mating surface (Fig. 29).

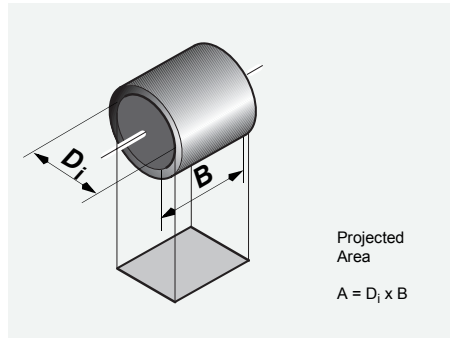


Fig. 11: Projected Area

Maximum specific load \bar{p}_{lim}

| Type of loading | \bar{p}_{lim} [N/mm ²] | | | | | | | | | | |
|--|--------------------------------------|------|------|------|------|-----------------|-----------------|-----------------|-----------------|-----------------|--|
| steady load, rotating movement | 140 | | | | | | | | | | |
| steady load, oscillating movement | | | | | | | | | | | |
| \bar{p}_{lim} | 140 | 140 | 115 | 95 | 85 | 80 | 60 | 44 | 30 | 20 | |
| No. of movement cycles Q | 1000 | 2000 | 4000 | 6000 | 8000 | 10 ⁴ | 10 ⁵ | 10 ⁶ | 10 ⁷ | 10 ⁸ | |
| dynamic load, rotating or oscillating movement | | | | | | | | | | | |
| \bar{p}_{lim} | 60 | 60 | 50 | 46 | 42 | 40 | 30 | 22 | 15 | 10 | |
| No. of load cycles Q | 1000 | 2000 | 4000 | 6000 | 8000 | 10 ⁴ | 10 ⁵ | 10 ⁶ | 10 ⁷ | 10 ⁸ | |

Table 4: Maximum specific load \bar{p}_{lim}

3.4 Sliding Speed U

Speeds in excess of 2.5 m/s sometimes lead to overheating, and a running in procedure may be beneficial.

This could consist of a series of short runs progressively increasing in duration from an initial run of a few seconds.

Calculation of Sliding Speed U [m/s]

Continuous Rotation

Cylindrical Bush

$$(3.4.1) \quad U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} \quad [\text{m/s}]$$

Thrust Washer

$$(3.4.2) \quad U = \frac{(D_o + D_i) \cdot \pi \cdot N}{2 \cdot 60 \cdot 10^3} \quad [\text{m/s}]$$

Oscillating Movement

Cylindrical Bush

$$(3.4.3) \quad U = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{osz}}{360} \quad [\text{m/s}]$$

Thrust Washer

$$(3.4.4) \quad U = \frac{(D_o + D_i) \cdot \pi}{2 \cdot 60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{osz}}{360} \quad [\text{m/s}]$$

3.5 $\bar{p}U$ Factor

The useful operating life of a DU bearing is governed by the $\bar{p}U$ factor, the product of the specific load \bar{p} [N/mm²] and the sliding speed U [m/s].

For thrust washers and flanged bush thrust faces the rubbing velocity at the mean diameter is used.

$\bar{p}U$ factors up to 3.6 N/mm² x m/s can be accommodated for short periods, whilst for continuous rating.

$\bar{p}U$ factors up to 1.8 N/mm² x m/s can be used, depending upon the operating life required.

| | DU | Unit |
|-------------------------|-----|-------------------------|
| \bar{p} | 140 | N/mm ² |
| U | 2.5 | m/s |
| $\bar{p}U$ continuous | 1.8 | N/mm ² x m/s |
| $\bar{p}U$ intermittent | 3.6 | N/mm ² x m/s |

Table 5: Typical data \bar{p} , U and $\bar{p}U$

Calculation of $\bar{p}U$ Factor [N/mm² x m/s]

$$(3.5.1) \quad \bar{p}U = \bar{p} \cdot U \quad [\text{N/mm}^2 \times \text{m/s}]$$

3.6 Application Factors

The following factors influence the bearing performance of DU and must be considered in calculating the required dimension

or estimating the bearing life for a particular application.

Temperature

The useful life of a DU bearing depends upon the operating temperature.

Under dry running conditions frictional heat is generated at the rubbing surface of the bearing dependent on the $\bar{p}U$ condition. For a given $\bar{p}U$ factor the operating temperature of the bearing depends upon the temperature of the surrounding environ-

ment and the heat dissipation properties of the housing. Intermittent operation affects the heat dissipation from the assembly and hence the operating temperature of the bearing.

The effect of temperature on the operating life of DU bearings is indicated by the factor a_T shown in Table 6.

| Mode of Operation | Nature of housing | Temperature of bearing environment T_{amb} [°C] and Temperature application factor a_T | | | | | |
|--|--|--|-----|-----|-----|-----|-----|
| | | 25 | 60 | 100 | 150 | 200 | 280 |
| Dry continuous operation | Average heat dissipating qualities | 1.0 | 0.8 | 0.6 | 0.4 | 0.2 | 0.1 |
| Dry continuous operation | Light pressings or isolated housing with poor heat dissipating qualities | 0.5 | 0.4 | 0.3 | 0.2 | 0.1 | - |
| Dry continuous operation | Non-metallic housings with bad heat dissipating qualities | 0.3 | 0.3 | 0.2 | 0.1 | - | - |
| Dry intermittent operation (duration less than 2 min, followed by a longer dwell period) | Average heat dissipating qualities | 2.0 | 1.6 | 1.2 | 0.8 | 0.4 | 0.2 |
| Continuously immersed in water | | 2.0 | 1.5 | 0.6 | - | - | - |
| Alternately immersed in water & dry | | 0.2 | 0.1 | - | - | - | - |
| Continuously immersed in non lubricant liquids other than water | | 1.5 | 1.2 | 0.9 | 0.6 | 0.3 | 0.1 |
| Continuously immersed in lubricant | | 3.0 | 2.5 | 2.0 | 1.5 | - | - |

Table 6: Temperature application factor a_T

Mating Surface

The effect of the mating surface material type on the operating life of DU bearings is indicated by the mating surface factor a_M and the life correction constant a_L shown in Table 7.

| Material | a_M | a_L |
|--|-------|-------|
| Steel and Cast Iron | | |
| Carbon Steel | 1 | 200 |
| Carbon Manganese Steel | 1 | 200 |
| Alloy Steel | 1 | 200 |
| Case Hardened Steel | 1 | 200 |
| Nitrided Steel | 1 | 200 |
| Salt bath nitrocarburised | 1 | 200 |
| Stainless Steel (7-10 % Ni, 17-20 % Cr) | 2 | 200 |
| Sprayed Stainless Steel | 1 | 200 |
| Cast Iron(0.3 μm R_a) | 1 | 200 |

| Material | a_M | a_L |
|--|---------|-------|
| Plated Steel with minimum thickness of plating 0.013 mm | | |
| Cadmium | 0.2 | 600 |
| Hard Chrome | 2.0 | 600 |
| Lead | 1.5 | 600 |
| Nickel | 0.2 | 600 |
| Phosphated | 0.2 | 300 |
| Tin Nickel | 1.2 | 600 |
| Titanium Nitride | 1.0 | 600 |
| Tungsten Carbide Flame Plated | 3.0 | 600 |
| Zinc | 0.2 | 600 |
| Non ferrous metals | | |
| Aluminium Alloys | 0.4 | 200 |
| Bronze and Copper Base Alloys | 0.1-0.4 | 200 |
| Hard Anodised Aluminium (0.025 mm thick) | 3.0 | 600 |

Table 7: Mating surface factor a_M and life correction constant a_L

Note:

The factor values given assume a mating surface finish of $\leq 0.4 \mu\text{m}$ R_a

- A ground surface is preferred to fine turned
- Surfaces should be cleaned of abrasive particles after polishing

- Cast iron surfaces should be ground to $< 0.3 \mu\text{m}$ R_a
- The grinding cut should be in the same direction as the bearing motion relative to the shaft

Bearing Size

The running clearance of a DU bearing increases with bearing diameter resulting in a proportionally smaller contact area between the shaft and bearing. This reduction in contact area has the effect of increasing the actual unit load and hence p_U

factor. The bearing size factor (Fig. 13) is used in the design calculations to allow for this effect. The bearing size factor is also applicable to thrust washers, where for other reasons, bearing diameter has an effect on performance.

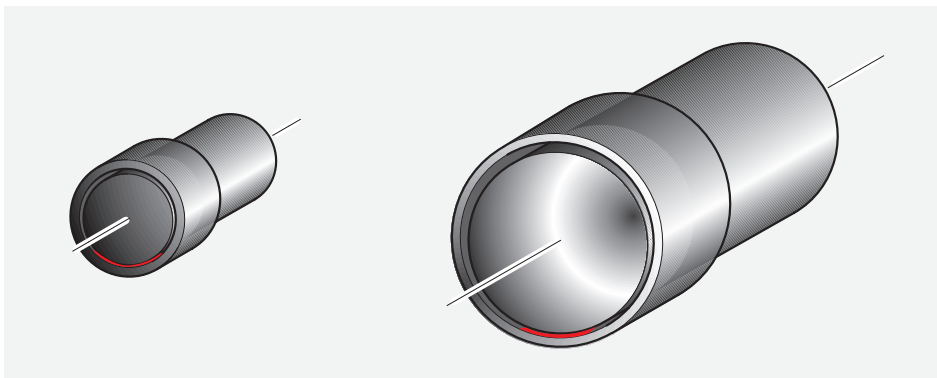


Fig. 12: Contact area between bearing and shaft.

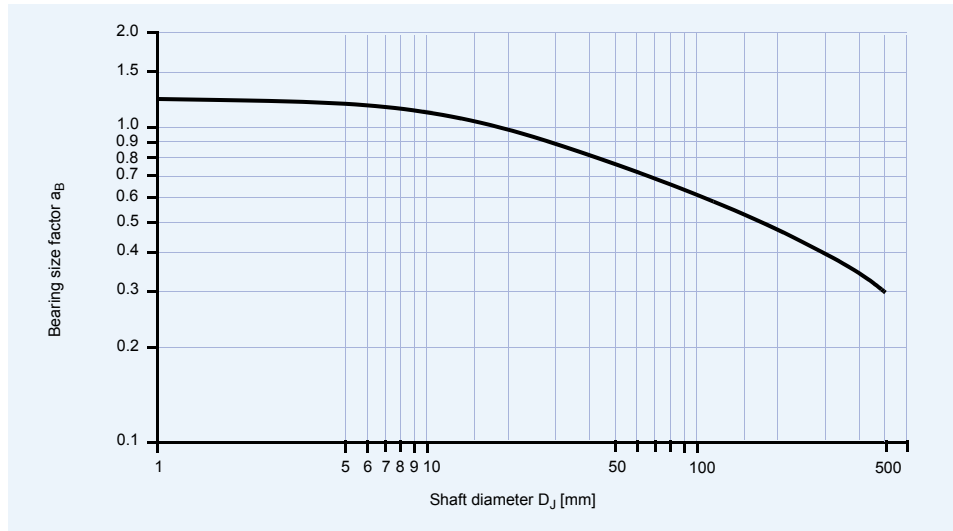


Fig. 13: Bearing size factor a_B

Bore Burnishing

Burnishing or machining the bore of a DU bearing results in a reduction in the wear performance. The application factor a_C

given in Table 8 is used in the design calculations to allow for this effect.

| Degree of sizing | | Application factor a_C |
|--|----------|--------------------------|
| Burnishing: Excess of burnishing tool diameter over mean bore size | 0.025 mm | 0.8 |
| | 0.038 mm | 0.6 |
| | 0.050 mm | 0.3 |
| Boring: Depth of cut | 0.025 mm | 0.6 |
| | 0.038 mm | 0.3 |
| | 0.050 mm | 0.1 |

Table 8: Bore burnishing or machining application factor a_C

Type of Load

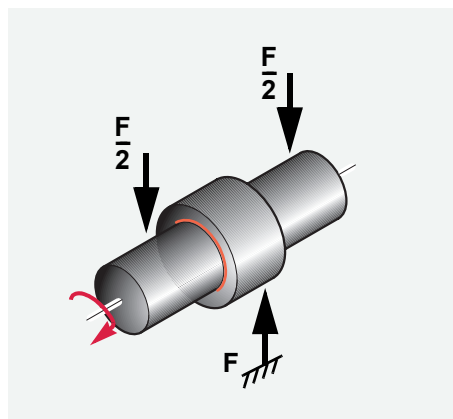


Fig. 14: Steady load, Bush stationary, Shaft rotating

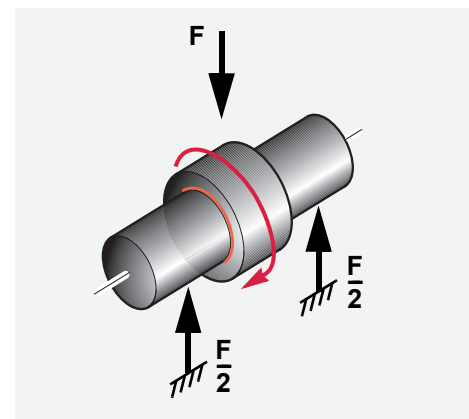


Fig. 15: Rotating load, Shaft stationary, Bush rotating

3.7 Calculation of Bearing Size

In designing all bearings, the shaft diameter is usually determined by considerations of physical stability or stiffness and the main variable to be determined is the length of the bush or the land width of the thrust washer.

The formulae given below enable designers to calculate the length or width

necessary to satisfy both the Specific Load Limit and the $\bar{p}U$ /Life relationship.

If it is found that the total length exceeds twice the diameter of the shaft, this indicates that the conditions envisaged are too severe for DU material and consideration should be given to repositioning the bearings in order to reduce the load.

Calculation for Bushes

Bush Stationary, Shaft Rotating

$$(3.7.1) \quad B = \frac{F \cdot N \cdot (L_H + a_L)}{1.25 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \frac{F}{\bar{p}_{lim} \cdot D_i} \quad [\text{mm}]$$

Bush Rotating, Shaft Stationary

$$(3.7.2) \quad B = \frac{F \cdot N \cdot (L_H + a_L)}{2.5 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \frac{F}{\bar{p}_{lim} \cdot D_i} \quad [\text{mm}]$$

Calculation for Thrust Washers

$$(3.7.3) \quad D_o - D_i = \frac{F \cdot N \cdot (L_H + a_L)}{1.25 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \sqrt{D_i^2 + \frac{1.3F}{\bar{p}_{lim}}} - D_i \quad [\text{mm}]$$

Calculation for Slideways

$$(3.7.4) \quad A = \frac{2.38 \cdot F \cdot U(L_H + a_L)}{10^3 \cdot a_T \cdot a_M} \cdot \frac{(L + L_S)}{L} + \frac{F}{\bar{p}_{lim}} \quad [\text{mm}^2]$$

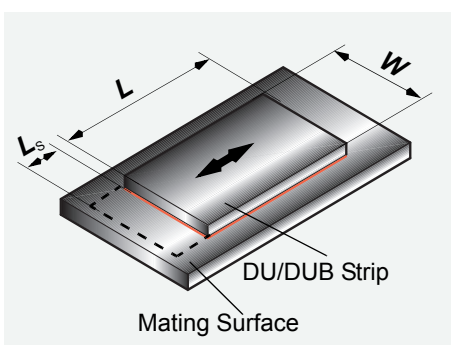


Fig. 16: Slideway

3.8 Calculation of Bearing Service Life

Where the size of a bearing is governed largely by the space available the following calculation can be used to determine whether

its useful life will satisfy the requirements. If the calculated life is inadequate, a larger bearing should be considered.

Specific load \bar{p}

Bushes

$$(3.8.1) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{F}{D_i \cdot B}$$

Flanged Bushes

$$(3.8.2) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{F}{0.04 \cdot (D_{fi}^2 - D_i^2)}$$

High load factor a_E

$$(3.8.4) \quad a_E \quad [-]$$

$$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}}$$

\bar{p}_{lim} see Table 4, Page 13

If a_E is negative then the bearing is overloaded. Increase the bearing diameter and/or length.

Modified $\bar{p}U$ Factor

Bushes

$$(3.8.5) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B}$$

Flanged Bushes

$$(3.8.6) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{6.5 \cdot 10^{-4} F \cdot N}{a_E \cdot (D_{fi} - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

For oscillating movement, calculate the average rotational speed.

$$(3.8.8) \quad N \quad [1/\text{min}]$$

$$N = \frac{4\phi \cdot N_{osz}}{360}$$

Thrust Washers

$$(3.8.3) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{4F}{\bar{p} \cdot (D_o^2 - D_i^2)}$$

Thrust Washers

$$(3.8.7) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{3.34 \cdot 10^{-5} F \cdot N}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

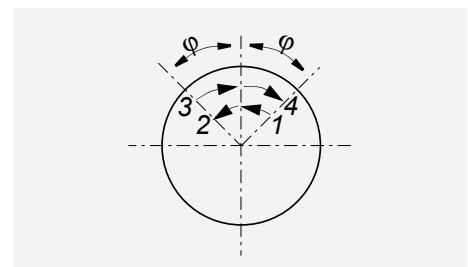


Fig. 17: Oscillating cycle ϕ

Estimation of bearing life L_H

Bushes (Steady load)

$$(3.8.9) \quad L_H = \frac{615}{\bar{p}U} \cdot a_L \quad [h]$$

Bushes (Rotating load)

$$(3.8.10) \quad L_H = \frac{1230}{\bar{p}U} \cdot a_L \quad [h]$$

Flanged Bushes (Axial load)

$$(3.8.11) \quad L_H = \frac{410}{\bar{p}U} \cdot a_L \quad [h]$$

Thrust Washers

$$(3.8.12) \quad L_H = \frac{410}{\bar{p}U} \cdot a_L \quad [h]$$

Bore Burnishing

If the DU bush is bore burnished then this must be allowed for in estimating the bea-

ring life by the application factor a_C (Table 8, Page 16).

Estimated Bearing Life

$$(3.8.13) \quad L_H = L_H \cdot a_C \quad [h]$$

Slideways

Specific load factor

$$(3.8.14) \quad a_{E1} = A - \frac{F}{\bar{p}_{lim}} \quad [-]$$

If negative the bearing is overloaded and the bearing area should be increased.

Speed temperature and material application factors

$$(3.8.15) \quad a_{E2} = \frac{420 \cdot a_T \cdot a_M}{F \cdot U} \quad [-]$$

Relative contact area factor

$$(3.8.16) \quad a_{E3} = \frac{A}{A_M} \quad [-]$$

Estimated bearing life

$$(3.8.17) \quad L_H = a_{E1} \cdot a_{E2} \cdot a_{E3} \cdot a_L \quad [h]$$

Estimated bearing lives greater than 4000 h are subject to error due to inaccuracies in the extrapolation of test data.

$Z_T = L_H \times N_{OSZ} \times 60$ (for Oscillating Movements) (3.8.18).

$Z_T = L_H \times C \times 60$ (for dynamic load) (3.8.19).

Check that Z_T is less than total number of cycles Q for the operating specific load \bar{p} (Table 4, Page 13).

For Oscillating Movements or Dynamic load: Calculate estimated number of cycles Z_T .

If $Z_T < Q$, L_H will be limited by wear after Z_T cycles.

If $Z_T > Q$, L_H will be limited by fatigue after Z_T cycles.

3.9 Worked Examples

Cylindrical Bush

| Given: | | | |
|--------------|-----------------------|-----------------------|----------|
| Load Details | Steady Load | Inside Diameter D_i | 40 mm |
| | Continuous Rotation | Length B | 30 mm |
| Shaft | Steel | Bearing Load F | 5000 N |
| | Unlubricated at 25 °C | Rotational Speed N | 50 1/min |

| Calculation Constants and Application Factors | | | |
|---|-----------------------|--------------------|--|
| Specific Load Limit \bar{p}_{lim} | 140 N/mm ² | (Table 4, Page 13) | |
| Temperature Application Factor a_T | 1.0 | (Table 6, Page 14) | |
| Material Application Factor a_M | 1.0 | (Table 7, Page 15) | |
| Bearing Size Factor a_B | 0.85 | (Fig. 13, Page 16) | |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) | |

| Calculation | Ref | Value |
|--|------------------|--|
| Specific Load \bar{p} [N/mm ²] | (3.2.1), Page 12 | $\bar{p} = \frac{F}{D_i \cdot B} = \frac{5000}{40 \cdot 30} = 4.17$ |
| Sliding Speed U [m/s] | (3.4.1), Page 13 | $U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{40 \cdot 3.14 \cdot 50}{60 \cdot 10^3} = 0.105$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 4.17 \cdot 0.105 = 0.438$ |
| High Load Factor a_E [-] (must be >0) | (3.8.4), Page 18 | $a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{140 - 4.17}{140} = 0.97$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.5), Page 18 | $\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 0.53$ |
| Life L_H [h] | (3.8.9), Page 19 | $L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{0.53} \cdot 200 = 960$ |

Cylindrical Bush

| Given: | | | |
|--------------|------------------------------|-----------------------|----------|
| Load Details | Steady Load Load Rotating | Inside Diameter D_i | 50 mm |
| | Continuous Rotation | Length B | 50 mm |
| Shaft | Steel | Bearing Load F | 10000 N |
| | Unlubricated at 100 °C | Rotational Speed N | 50 1/min |

| Calculation Constants and Application Factors | | | |
|---|----------------------|--------------------|--|
| Specific Load Limit \bar{p}_{lim} | 60 N/mm ² | (Table 4, Page 13) | |
| Temperature Application Factor a_T | 0.6 | (Table 6, Page 14) | |
| Material Application Factor a_M | 1.0 | (Table 7, Page 15) | |
| Bearing Size Factor a_B | 0.78 | (Fig. 13, Page 16) | |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) | |

| Calculation | Ref | Value |
|--|------------------|--|
| Specific Load \bar{p} [N/mm ²] | (3.2.1), Page 12 | $\bar{p} = \frac{F}{D_i \cdot B} = \frac{10000}{50 \cdot 50} = 4.0$ |
| Sliding Speed U [m/s] | (3.4.1), Page 13 | $U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{50 \cdot 3.14 \cdot 50}{60 \cdot 10^3} = 0.131$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 4.0 \cdot 0.131 = 0.542$ |
| High Load Factor a_E [-] (must be >0) | (3.8.4), Page 18 | $a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{60 - 4.0}{60} = 0.93$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.5), Page 18 | $\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.20$ |
| Life L_H [h] | (3.8.9), Page 19 | $L_H = \frac{1230}{\bar{p}U} \cdot a_L = \frac{1230}{1.20} \cdot 200 = 825$ |

Cylindrical Bush

| Given: | | | |
|--------------|-----------------------|-----------------------|----------|
| Load Details | Dynamic Load | Inside Diameter D_i | 30 mm |
| | Continuous Rotation | Length B | 30 mm |
| Shaft | Steel | Bearing Load F | 25000 N |
| | Unlubricated at 25 °C | Rotational Speed N | 15 1/min |

| Calculation Constants and Application Factors | | | |
|---|----------------------|--------------------|--|
| Specific Load Limit \bar{p}_{lim} | 60 N/mm ² | (Table 4, Page 13) | |
| Temperature Application Factor a_T | 1.0 | (Table 6, Page 14) | |
| Material Application Factor a_M | 1.0 | (Table 7, Page 15) | |
| Bearing Size Factor a_B | 1 | (Fig. 13, Page 16) | |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) | |

| Calculation | Ref | Value |
|--|------------------|--|
| Specific Load \bar{p} [N/mm ²] | (3.2.1), Page 12 | $\bar{p} = \frac{F}{D_i \cdot B} = \frac{25000}{30 \cdot 30} = 27.78$ |
| Sliding Speed U [m/s] | (3.4.1), Page 13 | $U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{30 \cdot 3.14 \cdot 15}{60 \cdot 10^3} = 0.024$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 27.78 \cdot 0.024 = 0.669$ |
| High Load Factor a_E [-] (must be >0) | (3.8.4), Page 18 | $a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{60 - 27.78}{60} = 0.54$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.5), Page 18 | $\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.23$ |
| Life L_H [h] | (3.8.9), Page 19 | $L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{1.23} \cdot 200 = 350$ |
| Calculate total load cycles | Table 4, Page 13 | $Z_T = 300 \cdot 60 \cdot 60 = 300 \cdot 10^6$ Q for 27.78 N/mm ² = bearing will fatigue after 10 ⁵ cycles (= 28 h) |

Cylindrical Bush

| Given: | | | |
|--------------|--------------------------------------|-----------------------|---------|
| Load Details | Steady Load Oscillating Movements | Inside Diameter D_i | 45 mm |
| | Stainless Steel | Length B | 40 mm |
| Shaft | | Bearing Load F | 40000 N |
| | Unlubricated at 25 °C | Frequency C | 150 |
| | Continuous operation | Amplitudes ϕ | 20 ° |

| Calculation Constants and Application Factors | | | |
|---|-----------------------|--------------------|--|
| Specific Load Limit \bar{p}_{lim} | 140 N/mm ² | (Table 4, Page 13) | |
| Temperature Application Factor a_T | 1.0 | (Table 6, Page 14) | |
| Material Application Factor a_M | 2.0 | (Table 7, Page 15) | |
| Bearing Size Factor a_B | 0.81 | (Fig. 13, Page 16) | |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) | |

| Calculation | Ref | Value |
|--|------------------|--|
| Specific Load \bar{p} [N/mm ²] | (3.2.1), Page 12 | $\bar{p} = \frac{F}{D_i \cdot B} = \frac{40000}{45 \cdot 40} = 22.22$ |
| Sliding Speed U [m/s] | (3.4.1), Page 13 | $U = \frac{45 \cdot 3.14 \cdot 33.33}{60 \cdot 10^3} = 0.078$ |
| Average speed N [1/min] | (3.8.8), Page 18 | $N = \frac{4\phi \cdot N_{osz}}{360} = \frac{4 \cdot 20 \cdot 150}{360} = 33.33$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 22.22 \cdot 0.078 = 1.733$ |
| High Load Factor a_E [-] (must be >0) | (3.8.4), Page 18 | $a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{140 - 22.22}{140} = 0.84$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.5), Page 18 | $\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.29$ |
| Life L_H [h] | (3.8.9), Page 19 | $L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{1.29} \cdot 200 = 277$ |
| Calculate total load cycles | Table 4, Page 13 | $Z_T = 277 \cdot 150 \cdot 60 = 2.5 \cdot 10^6$ Q for 22.22 N/mm ² = 10 ⁸ bearing o.k.! |

Thrust Washer

| Given: | | | |
|--------------|-----------------------|------------------------|----------|
| Load Details | Axial Load, | Outside Diameter D_o | 62 mm |
| | Continuous Rotation | Inside Diameter D_i | 38 mm |
| Shaft | Steel | Bearing Load F | 6500 N |
| | Unlubricated at 25 °C | Rotational Speed N | 60 1/min |

Calculation Constants and Application Factors

| | | |
|--------------------------------------|-----------------------|--------------------|
| Specific Load Limit p_{lim} | 140 N/mm ² | (Table 4, Page 13) |
| Temperature Application Factor a_T | 1.0 | (Table 6, Page 14) |
| Material Application Factor a_M | 1.0 | (Table 7, Page 15) |
| Bearing Size Factor a_B | 0.85 | (Fig. 13, Page 16) |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) |

| Calculation | Ref | Value |
|--|----------------------|--|
| Specific Load \bar{p} [N/mm ²] | (3.8.3), Page 18 | $\bar{p} = \frac{4 \cdot 6500}{3.14 \cdot (62^2 - 38^2)} = 3.45$ |
| Sliding Speed U [m/s] | (3.4.2), Page 13 | $U = \frac{(62+38) \cdot 3.14 \cdot 60}{60 \cdot 1000} = 0.157$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 3.45 \cdot 0.157 = 0.541$ |
| High Load Factor a_E [-] | (3.8.4), Page 18 | $a_E = \frac{140 - 3.45}{140} = 0.98$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.7), Page 18 | $\bar{p}U = \frac{3.34 \cdot 10^{-5} \cdot 6500 \cdot 60}{0.87 \cdot (62 - 38) \cdot 1 \cdot 1 \cdot 0.85} = 0.65$ |
| Life L_H [h] | (3.8.12), Page 19 | $L_H = \frac{410}{0.65} \cdot 200 = 431$ |

Flanged Bush

| Given: | | | |
|--------------|-----------------------|----------------------------------|----------|
| Load Details | Axial Load | Flange outside Diameter D_{fl} | 23 mm |
| | Continuous Rotation | Inside Diameter D_i | 15 mm |
| Shaft | Steel | Bearing Load F | 250 N |
| | Unlubricated at 25 °C | Rotational Speed N | 25 1/min |

Calculation Constants and Application Factors


| | | |
|--------------------------------------|-----------------------|--------------------|
| Specific Load Limit p_{lim} | 140 N/mm ² | (Table 4, Page 13) |
| Temperature Application Factor a_T | 1.0 | (Table 6, Page 14) |
| Material Application Factor a_M | 1.0 | (Table 7, Page 15) |
| Bearing Size Factor a_B | 1.0 | (Fig. 13, Page 16) |
| Life Correction Constant a_L | 200 | (Table 7, Page 15) |

| Calculation | Ref | Value |
|--|----------------------|---|
| Specific Load \bar{p} [N/mm ²] | (3.2.2), Page 12 | $\bar{p} = \frac{250}{0.04 \cdot (23^2 - 15^2)} = 20.55$ |
| Sliding Speed U [m/s] | (3.4.2), Page 13 | $U = \frac{(23+15) \cdot 3.14 \cdot 25}{60 \cdot 1000} = 0.025$ |
| pU Factor (Calculate from Table 5, Page 14) | (3.5.1), Page 14 | $\bar{p}U = \bar{p} \cdot U = 20.55 \cdot 0.025 = 0.513$ |
| High Load Factor a_E [-] | (3.8.4), Page 18 | $a_E = \frac{140 - 20.55}{140} = 0.85$ |
| Modified pU Factor [N/mm ² x m/s] | (3.8.6), Page 18 | $\bar{p}U = \frac{6.5 \cdot 10^{-5} \cdot 250 \cdot 50}{0.85 \cdot (23 - 15) \cdot 1 \cdot 1 \cdot 1} = 0.59$ |
| Life L_H [h] | (3.8.11), Page 19 | $L_H = \frac{410}{0.59} \cdot 200 = 495$ |

4 Data Sheet

Application: _____

4.1 Data for bearing design calculations

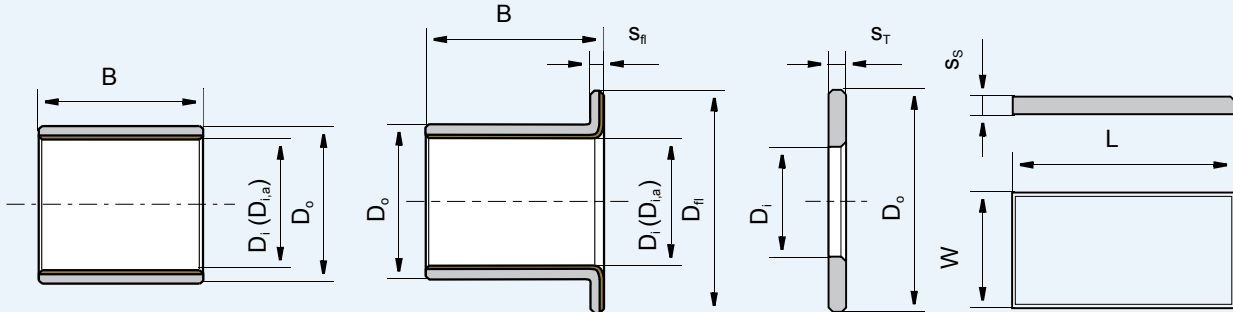

- Cylindrical Bush
 Flanged Bush
 Thrust Washer
 Slideplate
 Special (Sketch)
- Rotational movement
 Steady load
 Rotating load
 Oscillating movement
 Linear movement

Existing Design New Design

Quantity

Dimensions in mm

Inside Diameter D_i
 Outside Diameter D_o
 Length B
 Flange Diameter D_f
 Flange Thickness S_f
 Length of slideplate L
 Width of slideplate W
 Thickness of slideplate S_s

Load

Radial load or specific load F [N]
 \bar{p} [N/mm²]

Axial load or specific load F [N]
 \bar{p} [N/mm²]

Movement

Rotational speed N [1/min]
 Speed U [m/s]
 Length of Stroke L_s [mm]
 Frequency of Stroke [1/min]
 Oscillating cycle φ [°]
 Oscillating frequency N_{osz} [1/min]

Service hours per day

Continuous operation
 Intermittent operation
 Operating time
 Days per year

Fits and Tolerances

Shaft D_J
 Bearing Housing D_H

Operating Environment

Ambient temperature T_{amb} [°]
 Housing with good heat transfer properties
 Light pressing or insulated housing which poor heat transfer properties
 Non metal housing with poor heat transfer properties
 Alternate operation in water and dry

Mating surface

Material
 Hardness HB/HRC
 Surface finish R_a [μm]

Lubrication

Dry
 Continuous lubrication
 Process fluid lubrication
 Initial lubrication only
 Hydrodynamic conditions
 Process Fluid
 Lubricant
 Dynamic viscosity η

Service life

Required service life L_H [h]

Customer Data
 Company: City:
 Street: Post Code:

Project:
 Name:
 Tel.:

Date:
 Signature:
 Fax:

5 Lubrication

Although DU was developed as a dry self lubricating bearing material, DU also provides excellent performance in lubricated applications.

5.1 Lubricants

DU can be used with most fluids including

- water
- lubricating oils
- engine oil
- turbine oil
- hydraulic fluid
- solvent
- refrigerants

In general, the fluid will be acceptable if it does not chemically attack the PTFE/lead overlay or the porous bronze interlayer. Where there is doubt about the suitability of a fluid, a simple test is to submerge a

The following sections describe the basics of lubrication and provide guidance on the application of DU in such environments.

sample of DU material in the fluid for two to three weeks at 15-20 °C above the operating temperature.

The following will usually indicate that the fluid is not suitable for use with DU:

- A significant change in the thickness of the DU material,
- A visible change in the bearing surface other than some discolouration or staining
- A visible change in the microstructure of the bronze interlayer

5.2 Tribology

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load
- Speed
- Lubricant Viscosity
- Lubricant Flow

Hydrodynamic lubrication

Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film
- Very low friction and no wear of the bearing or shaft since there is no contact.
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when

$$(5.2.1) \quad \bar{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{N/mm}^2]$$

$$\bar{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i}$$

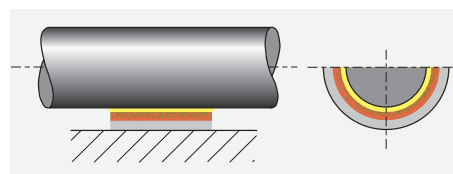


Fig. 18: Hydrodynamic lubrication

Mixed film lubrication

Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Friction and wear depend upon the degree of hydrodynamic support developed.

- DU provides low friction and high wear resistance to support the boundary lubricated element of the load.

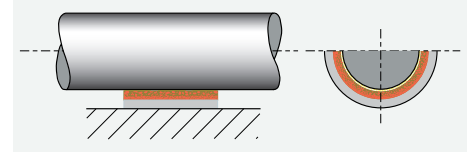


Fig. 19: Mixed film lubrication

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent self lubricating properties of DU material minimises wear under these conditions.

- The coefficient of friction with DU is typically 0.02 to 0.06 under boundary lubrication conditions.

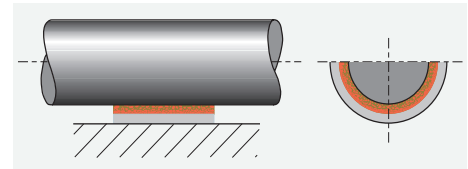


Fig. 20: Boundary lubrication

5.3 Characteristics of Lubricated DU bearings

DU is particularly effective in the most demanding of lubricated applications

where full hydrodynamic operation cannot be maintained, for example:

• High load conditions

In highly loaded applications operating under boundary or mixed film conditions DU shows excellent wear resistance and low friction.

• Start up and shut down under load

With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions. DU minimises wear and requires less start up torque than conventional metallic bearings.

• Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only. DU provides excellent self lubricating properties.

• Dry operation after running in water

If a DU bearing is required to run dry after running in water under non hydrodynamic conditions then the wear resistance will be substantially reduced due to an increased amount of bedding in wear.

5.4 Design Guidance for Lubricated Applications

Fig. 21 shows the three lubrication regimes discussed above. In order to use Fig. 21, using the formula on page 12 and page 13:

- Calculate the specific load \bar{p} ,
- Calculate the shaft surface speed U .

Using the viscosity temperature relationships presented in Table 9.

- Determine the lubricant viscosity in centipoise, of the lubricant.

If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

Area 1

The bearing will operate with boundary lubrication and pU factor will be the major determinant of bearing life. The DU bearing performance can be calculated using

Area 2

The bearing will operate with mixed film lubrication and the pU factor is no longer a significant parameter in determining the

Area 3

The bearing will operate with hydrodynamic lubrication. The bearing wear will be determined only by the cleanliness of the

Area 4

These are the most demanding operating conditions. The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both.

These conditions may cause:

the method given in Section 3, although the result will probably underestimate the bearing life

bearing life. The DU bearing performance will depend upon the nature of the fluid and the actual service conditions.

lubricant and the frequency of start up and shut down.

- excessive operating temperature and/or
- high wear rate.

The bearing performance may be improved by adding one or more grooves to the bearing and a shaft surface finish <math><0.05 \mu\text{m } R_a</math>.

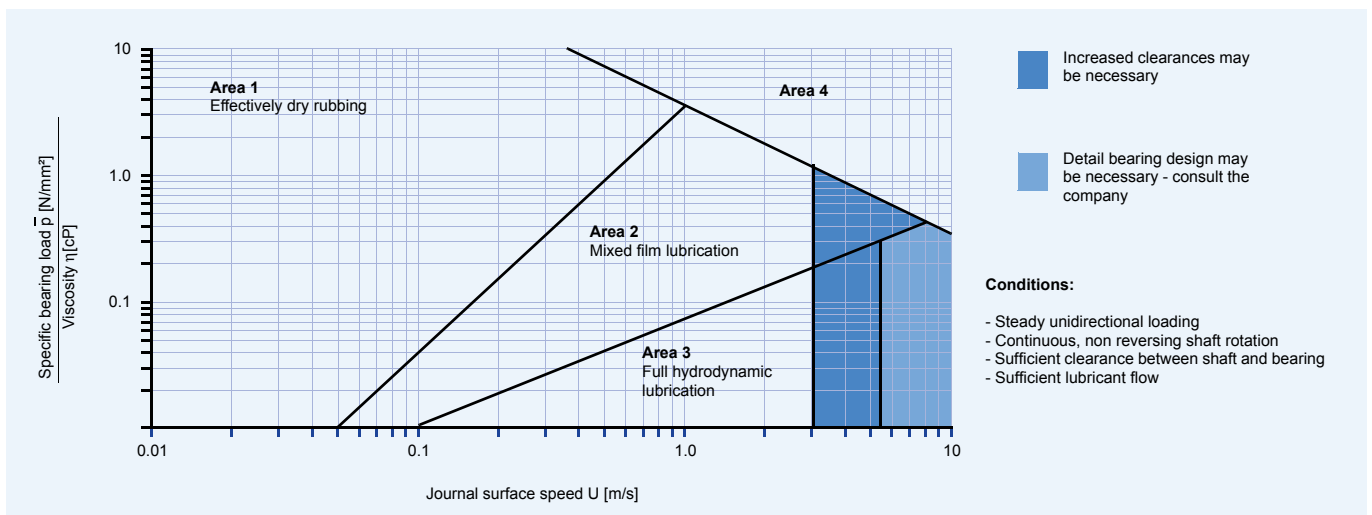


Fig. 21: Design guide for lubricated application

| Temperature [°C] | Viscosity cP | | | | | | | | | | | | | | |
|------------------|--------------|------|------|------|------|------|------|------|------|------|------|-----|-----|-----|-----|
| | 0 | 10 | 20 | 30 | 40 | 50 | 60 | 70 | 80 | 90 | 100 | 110 | 120 | 130 | 140 |
| Lubricant | | | | | | | | | | | | | | | |
| ISO VG 32 | 310 | 146 | 77 | 44 | 27 | 18 | 13 | 9.3 | 7.0 | 5.5 | 4.4 | 3.6 | 3.0 | 2.5 | 2.2 |
| ISO VG 46 | 570 | 247 | 121 | 67 | 40 | 25 | 17 | 12 | 9.0 | 6.9 | 5.4 | 4.4 | 3.6 | 3.0 | 2.6 |
| ISO VG 68 | 940 | 395 | 190 | 102 | 59 | 37 | 24 | 17 | 12 | 9.3 | 7.2 | 5.8 | 4.7 | 3.9 | 3.3 |
| ISO VG 100 | 2110 | 780 | 335 | 164 | 89 | 52 | 33 | 22 | 15 | 11.3 | 8.6 | 6.7 | 5.3 | 4.3 | 3.6 |
| ISO VG 150 | 3600 | 1290 | 540 | 255 | 134 | 77 | 48 | 31 | 21 | 15 | 11 | 8.8 | 7.0 | 5.6 | 4.6 |
| Diesel oil | 4.6 | 4.0 | 3.4 | 3.0 | 2.6 | 2.3 | 2.0 | 1.7 | 1.4 | 1.1 | 0.95 | | | | |
| Petrol | 0.6 | 0.56 | 0.52 | 0.48 | 0.44 | 0.40 | 0.36 | 0.33 | 0.31 | | | | | | |
| Kerosene | 2.0 | 1.7 | 1.5 | 1.3 | 1.1 | 0.95 | 0.85 | 0.75 | 0.65 | 0.60 | 0.55 | | | | |
| Water | 1.79 | 1.30 | 1.0 | 0.84 | 0.69 | 0.55 | 0.48 | 0.41 | 0.34 | 0.32 | 0.28 | | | | |

Table 9: Viscosity data

5.5 Clearances for lubricated operation

The recommended shaft and housing diameters given for standard DU bushes will provide sufficient clearance for applications operating with boundary lubrication.

For bearings operating with mixed film or hydrodynamic lubrication it may be neces-

sary to improve the fluid flow through the bearing by reducing the recommended shaft diameter by approximately 0.1%, particularly when the shaft surface speed exceeds 2.5 m/s.

5.6 Mating Surface Finish for lubricated operation

- $R_a \leq 0.4 \mu\text{m}$ Boundary lubrication
- $R_a = 0.1\text{-}0.2 \mu\text{m}$ Mixed film or hydrodynamic conditions
- $R_a \leq 0.05 \mu\text{m}$ for the most demanding operating conditions

5.7 Grooving for lubricated operation

In demanding applications an axial oil groove will improve the performance of DU. Fig. 22 shows the recommended form and location of a single groove with

respect to the applied load and the bearing split. GGB can manufacture special DU bearings with embossed or milled grooves on request.

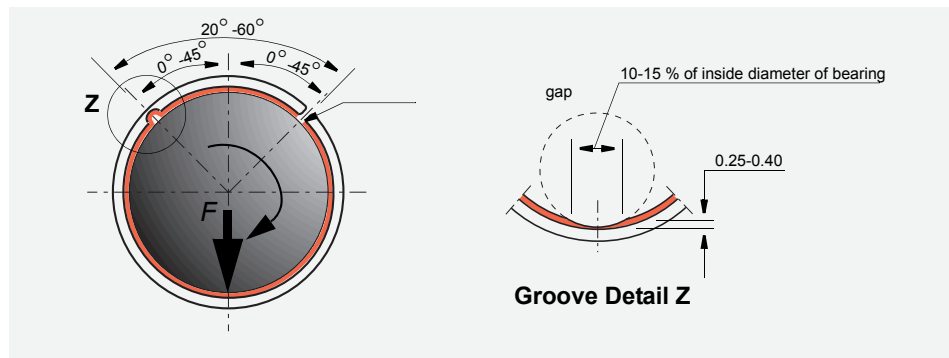


Fig. 22: Location of oil holes and grooves

5.8 Grease Lubrication

DU is not generally recommended for use with grease lubrication. In particular the following must be avoided:

- Dynamic loads - which can result in erosion of the PTFE/lead bearing surface.

- Greases with EP additives or fillers such as graphite or MoS_2 which can cause rapid wear of DU.

6 Bearing Assembly

Dimensions and Tolerances

DU bushes are prefinished in the bore, and except in very exceptional circumstances, must not be burnished, broached or otherwise modified. It is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables. Under dry running conditions any increase in the clearances given will result in a proportional reduction in performance.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

Where free running is essential, or where light loads (less than 0.1 N/mm²) prevail and the available torque is low, increased clearance is required and it is recommended that the shaft size quoted in the table be reduced by 0.025 mm.

6.1 Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 23 to

compensate for the inward thermal expansion of the bearing lining.

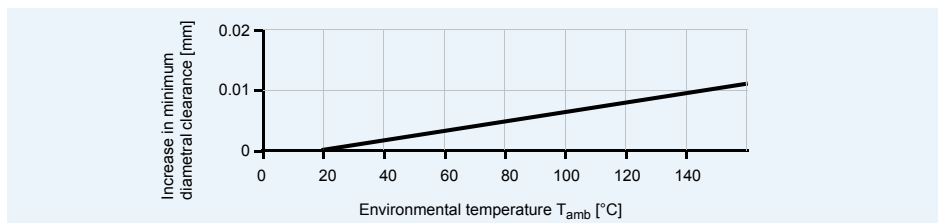


Fig. 23: Increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 10, in order to give an increased

interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 23.

| Housing material | Reduction in housing diameter per 100 °C rise | Reduction in shaft diameter per 100 °C rise |
|---------------------|---|---|
| Aluminium alloys | 0.1 % | 0.1 % + values from Fig. 23 |
| Copper base alloys | 0.05 % | 0.05 % + values from Fig. 23 |
| Steel and cast iron | – | values from Fig. 23 |
| Zinc base alloys | 0.15 % | 0.15 % + values from Fig. 23 |

Table 10: Allowance for high temperature

6.2 Tolerances for minimum clearance

Where it is required to keep the variation of assembled clearance to a minimum, closer tolerances can be specified towards the upper end of the journal tolerance and the lower end of the housing tolerance.

If housings to H6 tolerance are used, then the journals should be finished to the following limits.

The sizes in Table 11 give the following nominal clearance range.

| D_i | D_j |
|----------------|------------------|
| <25 mm | -0.019 to -0.029 |
| >25 mm < 50 mm | -0.021 to -0.035 |

Table 11: Shaft tolerances for use with H6 housings

| D_i | C_D |
|-------|----------------|
| 10 mm | 0.005 to 0.078 |
| 50 mm | 0.005 to 0.130 |

Table 12: Clearance vs bearing diameter

Sizing

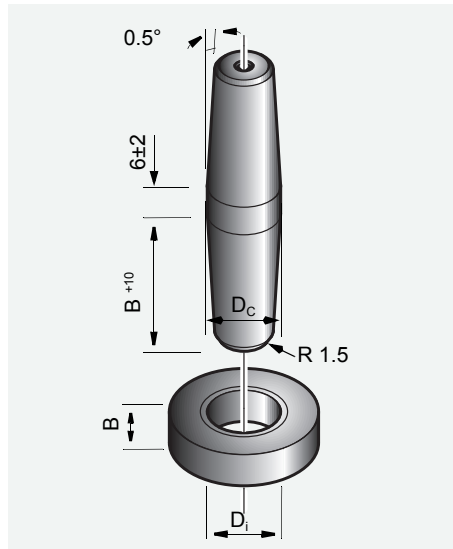


Fig. 24: Burnishing tool

The burnishing or fine boring of the bore of an assembled DU bush in order to achieve a smaller clearance tolerance is only permissible if a substantial reduction in performance is acceptable. Fig. 24 shows a recommended burnishing tool for the sizing of DU bushes.

The coining section of the burnishing tool should be case hardened (case depth 0.6-1.2 mm, HRC 60±2) and polished ($R_z \approx 1 \mu\text{m}$).

Note: Ball burnishing of DU bushes is not recommended.

| Assembled bush Inside- \varnothing | Required bush Inside- \varnothing | Required burnishing tool diameter D_c |
|--------------------------------------|-------------------------------------|---|
| $D_{i,a}$ | $D_{i,a} + 0.025$ | $D_{i,a} + 0.06$ |
| $D_{i,a}$ | $D_{i,a} + 0.038$ | $D_{i,a} + 0.08$ |
| $D_{i,a}$ | $D_{i,a} + 0.050$ | $D_{i,a} + 0.1$ |

Table 13: Burnishing tool tolerances

The values given in Table 13 indicate the dimensions of the burnishing tool required to give specific increases in the bearing bore diameter.

Exact values must be determined by test.

The reduction in bearing performance as a result of burnishing is allowed for in the bearing life calculation by the application factor a_c (Table 8, Page 16).

6.3 Counterface Design

The suitability of mating surface materials and recommendations of mating surface finish for use with DU are discussed in detail on page 15.

DU is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings, particularly without the protection of oil or grease, stainless steel, hard chromium plated mild steel, or hard anodised aluminium is recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DU bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft overlay of the DU must be removed.

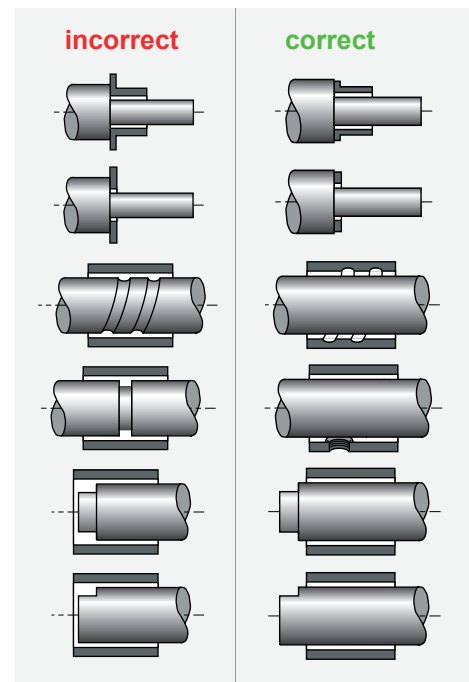


Fig. 25: Counterface Design

6.4 Installation

Fitting of cylindrical bushes

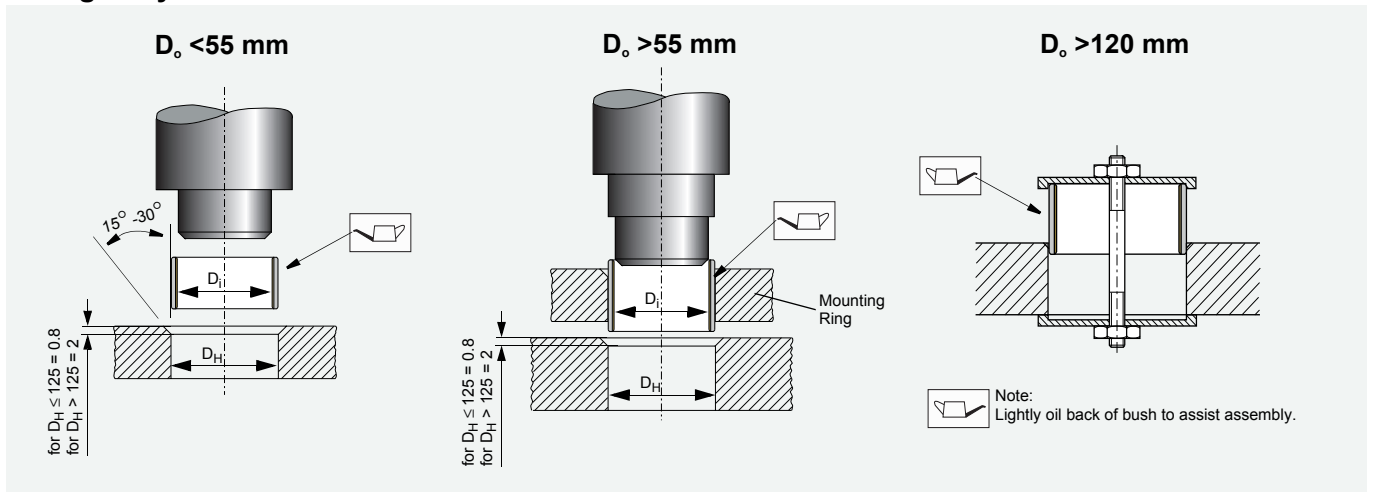


Fig. 26: Fitting of cylindrical bushes

Fitting of flanged bushes

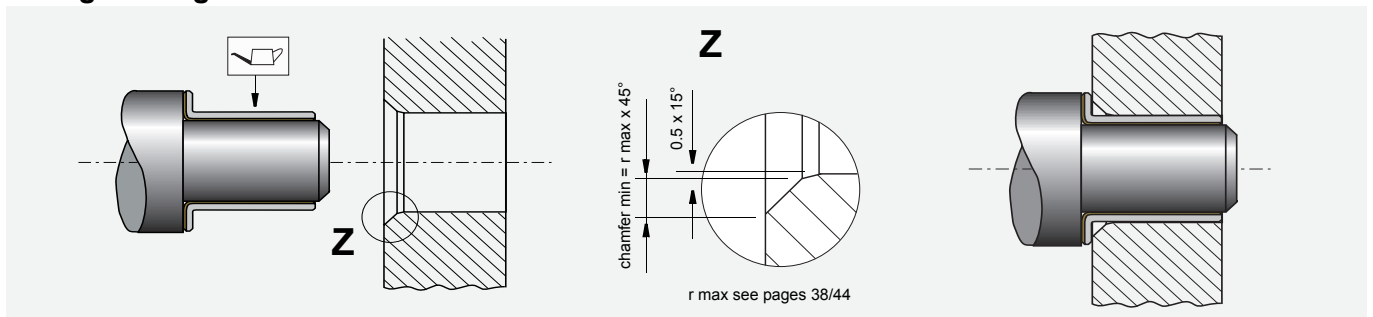


Fig. 27: Fitting of flanged bushes

Insertion Forces

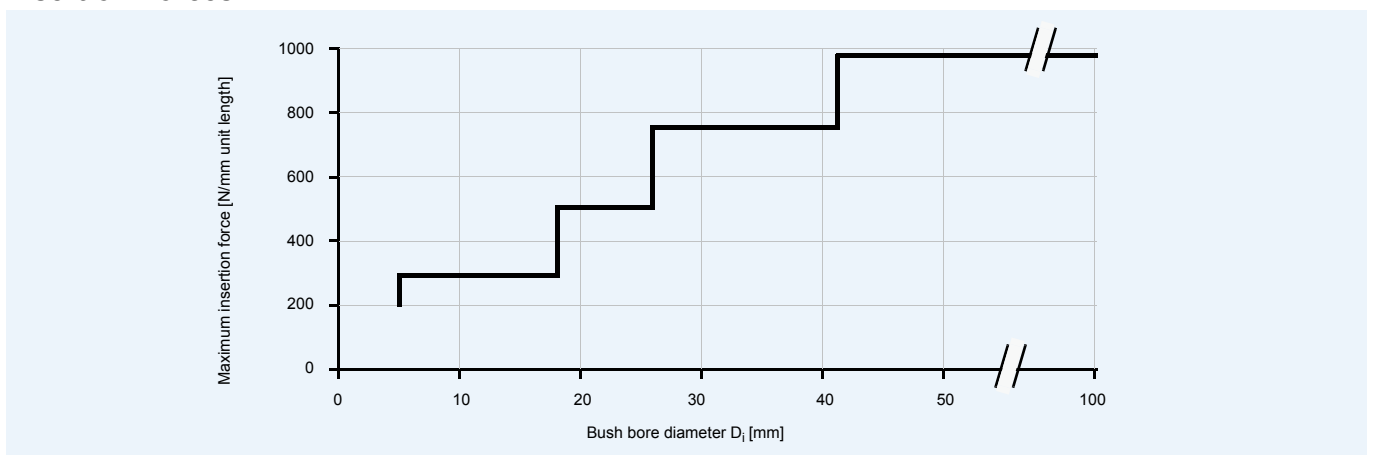


Fig. 28: Maximum Insertion Force

Alignment

Accurate alignment is an important consideration for all bearing assemblies, but is particularly so for dry bearings because there is no lubricant to spread the load.

With DU bearings misalignment over the length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 29.

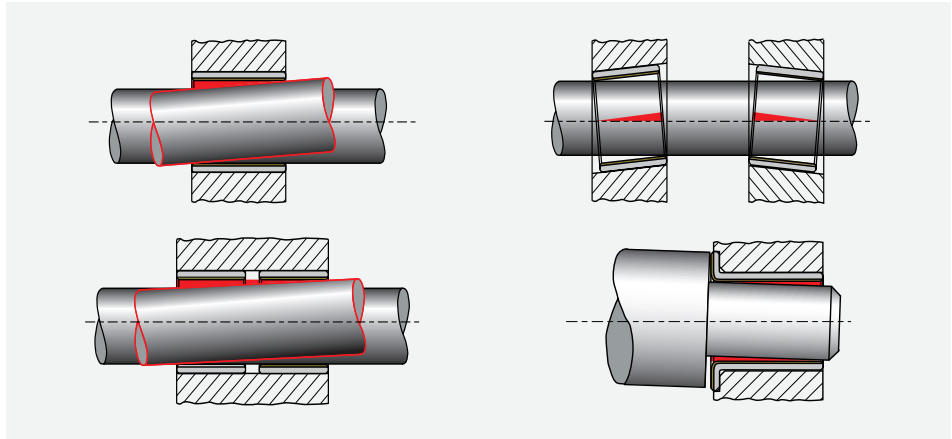


Fig. 29: Alignment

Sealing

While DU can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly abrasive material

entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 30 should be provided.

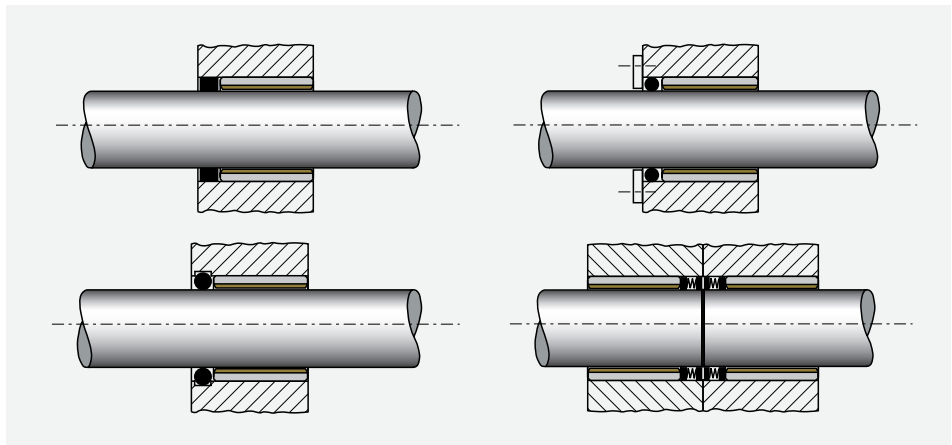


Fig. 30: Recommended sealing arrangements

6.5 Axial Location

Where axial location is necessary, it is advisable to fit DU thrust washers in con-

junction with DU bushes, even when the axial loads are low.

Fitting of Thrust Washers

DU thrust washers should be located in a recess as shown in Fig. 31. The recess diameter should be 0.125 mm larger than the washer diameter and the depth as given in the product tables.

If a recess is not possible one of the following methods may be used:

- Two dowel pins
- Two screws
- Adhesive
- Soldering

Important Note

- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing
- Dowels pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DU must not be heated above 320 °C
- Contact adhesive manufacturers for guidance selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive

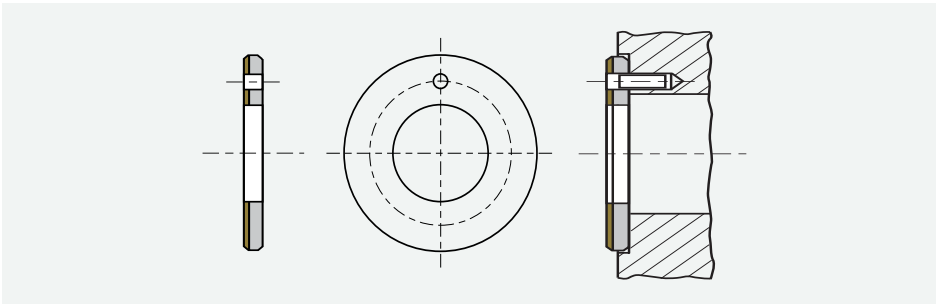


Fig. 31: Installation of Thrust-Washer

Grooves for Wear Debris Removal

Tests with thrust washers have demonstrated that for optimum dry wear performance at specific loads in excess of 35 N/mm², four wear debris removal grooves should

be machined in the bearing surface as shown in Fig. 32.

Grooves in bushes have not been found to be beneficial in this respect.

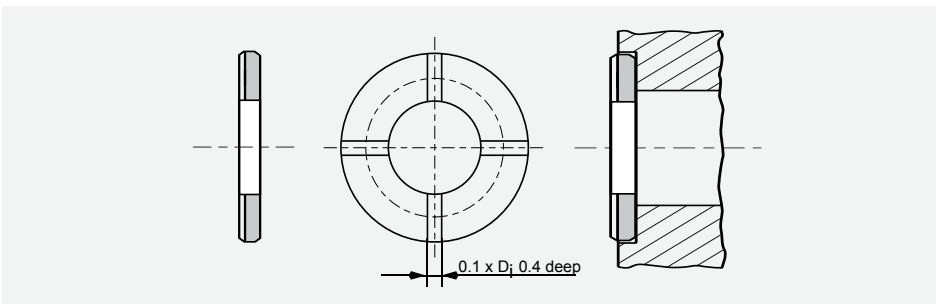


Fig. 32: Debris removal Grooves

Slideways

DU strip material for use as slideway bearings should be installed using one of the following methods:

- Countersunk screws
- Adhesives
- Mechanical location as shown in Fig. 33

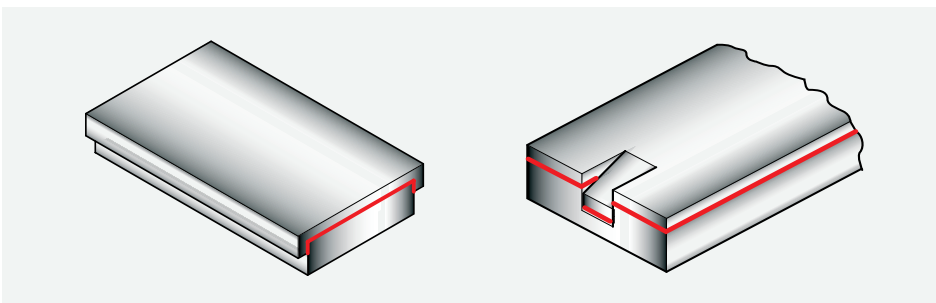


Fig. 33: Mechanical location of DU slideplates

7 Modification

7.1 Cutting and Machining

The modification of DU bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the PTFE side in order to avoid burrs. When cutting is done from the steel side, the

minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

Cutting Strip Material

DU strip material may be cut to size by any one of the following methods.

Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs:

- Using side and face cutter, or slitting saw, with the strip held flat and securely

on a horizontal milling machine.

- Cropping
- Guillotine
(For widths less than 90 mm only)
- Water-jet cutting
- Laser cutting (see Health Warning)

7.2 Electroplating

DU Components

In order to provide some protection in mildly corrosive environments the steel back and end faces of standard range DU bearings are tin flashed.

If exposed to corrosive liquids further protection should be provided and in very corrosive conditions DUB should be considered.

DU can be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081-2
- cadmium ISO 2081-2
- nickel ISO 1456-8
- hard chromium ISO 1456-8

For the harder materials if the specified plating thickness exceeds approximately 5 μm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

With light deposits of materials such as cadmium, no special precautions are necessary. Harder materials such as nickel however, may strike through the PTFE/lead surface layer of DU and it is advisable to use an appropriate method of masking the bearing surface.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.



Mating Surfaces

DU can be used against some plated materials as indicated on page 15.

Care should be taken to ensure that the recommended shaft sizes and surface finish are achieved after the plating process.

8 Standard Products

8.1 DU Cylindrical Bushes

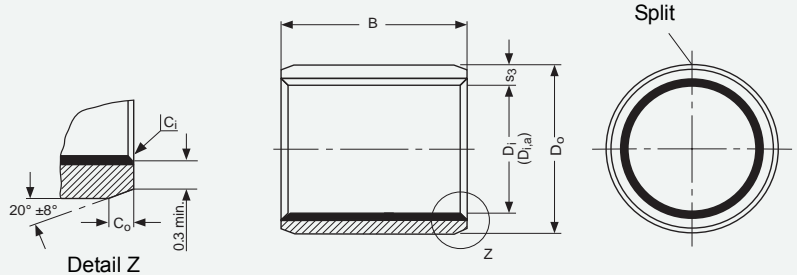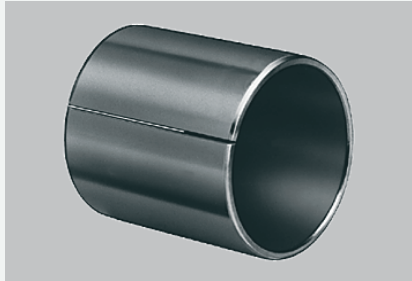

Dimensions and Tolerances according to ISO 3547 and GSP-Specifications

All dimensions in mm

Outside C_o and Inside C_i chamfers

| Wall thickness s ₃ | C _o (a) | | C _i (b) |
|----------------------------------|--------------------|-----------|--------------------|
| | machined | rolled | |
| 0.75 | 0.5 ± 0.3 | 0.5 ± 0.3 | -0.1 to -0.4 |
| 1 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.5 |
| 1.5 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.7 |

| Wall thickness s ₃ | C _o (a) | | C _i (b) |
|----------------------------------|--------------------|-----------|--------------------|
| | machined | rolled | |
| 2 | 1.2 ± 0.4 | 1.0 ± 0.4 | -0.1 to -0.7 |
| 2.5 | 1.8 ± 0.6 | 1.2 ± 0.4 | -0.2 to -1.0 |

a = Chamfer C_o machined or rolled at the opinion of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

| Part No. | Nominal Diameter | | Wall thickness s ₃ | Width B | Shaft-∅ D _J [h6, f7, h8] | Housing-∅ D _H [H6, H7] | Bush-∅ D _{i,a} Ass. in H6/H7 housing | Clearance C _D | | | | | |
|----------|------------------|----------------|----------------------------------|------------|--|--------------------------------------|---|-----------------------------|----------------|----------------|----------------|----------------|----------------|
| | D _i | D _O | | | | | | | max. min. | max. min. | max. min. | max. min. | max. min. |
| 0203DU | 2 | 3.5 | 0.750 0.730 | 3.25 | h6 | H6 | 2.048 2.000 | 0.054 0.000 | | | | | |
| 0205DU | | | | 2.75 | | | | | 2.000 1.994 | 3.508 3.500 | | | |
| 0303DU | 3 | 4.5 | | 3.25 | | | | | h6 | H6 | 3.048 3.000 | | |
| 0305DU | | | | 2.75 | | | | | | | | 3.000 2.994 | 4.508 4.500 |
| 0306DU | | | | 5.25 | | | | | | | | 4.508 4.500 | |
| 0403DU | 4 | 5.5 | | 3.25 | | | | | h6 | H6 | 4.048 4.000 | | |
| 0404DU | | | | 2.75 | 4.000 3.992 | 5.508 5.500 | | | | | | | |
| 0406DU | | | | 4.25 | 4.000 3.992 | 5.508 5.500 | | | | | | | |
| 0410DU | | | | 3.75 | 4.000 3.992 | 5.508 5.500 | | | | | | | |
| 0505DU | 5 | 7 | | 5.25 | h6 | H6 | 5.055 4.990 | | | | | | |
| 0508DU | | | | 4.75 | | | | | 4.990 4.978 | 7.015 7.000 | | | |
| 0510DU | | | | 8.25 | | | | | 4.990 4.978 | 7.015 7.000 | | | |
| 0604DU | 6 | 8 | 10.25 | f7 | H7 | 6.055 5.990 | | | | | | | |
| 0606DU | | | 9.75 | | | | 5.990 5.978 | 8.015 8.000 | | | | | |
| 0608DU | | | 4.25 | | | | 5.990 5.978 | 8.015 8.000 | | | | | |
| 0610DU | | | 3.75 | | | | 5.990 5.978 | 8.015 8.000 | | | | | |
| 0705DU | | | 6.25 | | | | 5.990 5.978 | 8.015 8.000 | | | | | |
| 0710DU | 7 | 9 | 10.25 | f7 | H7 | 7.055 6.990 | | | | | | | |
| 0710DU | 4.75 | 6.987 6.972 | 9.015 9.000 | | | | | | | | | | |
| 0710DU | 7 | 9 | 9.75 | | | 0.083 0.003 | | | | | | | |

8 Standard Products

| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J [h6, f7, h8] | | Housing- \varnothing D_H [H6, H7] | | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | | Clearance C_D |
|----------|------------------|------------------|-------------------------|------------------|--|------------------|--|------------------|---|------------------|--------------------|
| | D_i | D_o | | | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | |
| 0806DU | 8 | 10 | 1.005 0.980 | 6.25 | 7.987 7.972 | 10.015 10.000 | 8.055 7.990 | 0.083 0.003 | | | |
| 0808DU | | | | 5.75 | | | | | | | |
| 0810DU | | | | 8.25 | | | | | | | |
| 0812DU | | | | 7.75 | | | | | | | |
| 1006DU | | | | 10.25 | | | | | | | |
| 1008DU | 9.75 | 9.987 9.972 | | 12.018 12.000 | 10.058 9.990 | 0.086 0.003 | | | | | |
| 1010DU | 12.25 | | | | | | | | | | |
| 1012DU | 11.75 | | | | | | | | | | |
| 1015DU | 15.25 | | | | | | | | | | |
| 1020DU | 14.75 | | | | | | | | | | |
| 1208DU | 12 | 14 | | 8.25 | 11.984 11.966 | 14.018 14.000 | 12.058 11.990 | 0.092 0.006 | | | |
| 1210DU | | | | 7.75 | | | | | | | |
| 1212DU | | | | 10.25 | | | | | | | |
| 1215DU | | | | 9.75 | | | | | | | |
| 1220DU | | | | 12.25 | | | | | | | |
| 1225DU | 11.75 | 12.984 12.966 | | 15.018 15.000 | 13.058 12.990 | 0.092 0.006 | | | | | |
| 1310DU | 15.25 | | | | | | | | | | |
| 1320DU | 14.75 | | | | | | | | | | |
| 1405DU | 20.25 | | | | | | | | | | |
| 1410DU | 19.75 | | | | | | | | | | |
| 1412DU | 14 | 16 | 5.25 | 13.984 13.966 | 16.018 16.000 | 14.058 13.990 | 0.092 0.006 | | | | |
| 1415DU | | | 4.75 | | | | | | | | |
| 1420DU | | | 10.25 | | | | | | | | |
| 1425DU | | | 9.75 | | | | | | | | |
| 1510DU | | | 12.25 | | | | | 14.984 14.966 | 17.018 17.000 | 15.058 14.990 | 0.092 0.006 |
| 1512DU | 11.75 | | | | | | | | | | |
| 1515DU | 15.25 | | | | | | | | | | |
| 1520DU | 14.75 | | | | | | | | | | |
| 1525DU | 20.25 | | | | | | | | | | |
| 1610DU | 16 | 18 | 10.25 | 15.984 15.966 | 18.018 18.000 | 16.058 15.990 | 0.092 0.006 | | | | |
| 1612DU | | | 9.75 | | | | | | | | |
| 1615DU | | | 12.25 | | | | | | | | |
| 1620DU | | | 11.75 | | | | | | | | |
| 1625DU | | | 15.25 | | | | | | | | |
| 1720DU | 17 | 19 | 20.25 | 16.984 16.966 | 19.021 19.000 | 17.061 16.990 | 0.095 0.006 | | | | |
| | | | 19.75 | | | | | | | | |

| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{I,a}$ Ass. in H6/H7 housing | Clearance C_D |
|----------|------------------|------------------|----------------------|------------------|---|---------------------------------------|---|-----------------|
| | D_i | D_o | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. |
| 1810DU | 18 | 20 | 1.005 0.980 | 10.25 | 17.984 17.966 | 20.021 20.000 | 18.061 17.990 | 0.095 0.006 |
| 1815DU | | | | 9.75 | | | | |
| 1820DU | | | | 15.25 | | | | |
| 1825DU | | | | 14.75 | | | | |
| 2010DU | | | | 20.25 | | | | |
| 2015DU | 19.75 | 19.980 19.959 | 23.021 23.000 | 20.071 19.990 | 0.112 0.010 | | | |
| 2020DU | 25.25 | | | | | | | |
| 2025DU | 24.75 | | | | | | | |
| 2030DU | 30.25 | | | | | | | |
| 2030DU | 29.75 | | | | | | | |
| 2215DU | 22 | 25 | 1.505 1.475 | 15.25 | 21.980 21.959 | 25.021 25.000 | 22.071 21.990 | 0.112 0.010 |
| 2220DU | | | | 14.75 | | | | |
| 2225DU | | | | 20.25 | | | | |
| 2230DU | | | | 19.75 | | | | |
| 2230DU | | | | 25.25 | | | | |
| 2415DU | 24 | 27 | 1.505 1.475 | 14.75 | 23.980 23.959 | 27.021 27.000 | 24.071 23.990 | 0.112 0.010 |
| 2420DU | | | | 20.25 | | | | |
| 2425DU | | | | 19.75 | | | | |
| 2430DU | | | | 25.25 | | | | |
| 2430DU | | | | 24.75 | | | | |
| 2515DU | 25 | 28 | 1.505 1.475 | 15.25 | 24.980 24.959 | 28.021 28.000 | 25.071 24.990 | 0.112 0.010 |
| 2520DU | | | | 14.75 | | | | |
| 2525DU | | | | 20.25 | | | | |
| 2530DU | | | | 19.75 | | | | |
| 2550DU | | | | 25.25 | | | | |
| 2815DU | 28 | 32 | 1.505 1.475 | 14.75 | 27.980 27.959 | 32.025 32.000 | 28.085 27.990 | 0.112 0.010 |
| 2820DU | | | | 20.25 | | | | |
| 2825DU | | | | 19.75 | | | | |
| 2830DU | | | | 25.25 | | | | |
| 2830DU | | | | 24.75 | | | | |
| 3010DU | 30 | 34 | 2.005 1.970 | 10.25 | 29.980 29.959 | 34.025 34.000 | 30.085 29.990 | 0.126 0.010 |
| 3015DU | | | | 9.75 | | | | |
| 3020DU | | | | 15.25 | | | | |
| 3025DU | | | | 14.75 | | | | |
| 3030DU | | | | 20.25 | | | | |
| 3040DU | 19.75 | 31.975 31.950 | 36.025 36.000 | 32.085 31.990 | 0.135 0.015 | | | |
| 3220DU | 30.25 | | | | | | | |
| 3230DU | 29.75 | | | | | | | |
| 3240DU | 40.25 | | | | | | | |
| 3240DU | 39.75 | | | | | | | |

8 Standard Products


| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | Clearance C_D | | | |
|----------|------------------|-------|-------------------------|------------------|--|--|---|--------------------|------------------|------------------|------------------|
| | D_i | D_o | | | | | | | max. min. | max. min. | max. min. |
| 3520DU | 35 | 39 | 2.005 1.970 | 20.25 | 34.975 34.950 | 39.025 39.000 | 35.085 34.990 | 0.135 0.015 | | | |
| 3530DU | | | | 19.75 | | | | | | | |
| 3535DU | | | | 30.25 | | | | | | | |
| 3540DU | | | | 29.75 | | | | | | | |
| 3550DU | | | | 35.25 | | | | | | | |
| 3720DU | | | | 34.75 | | | | | | | |
| 4020DU | 40 | 44 | | 20.25 | 39.975 39.950 | 41.025 41.000 | 40.085 39.990 | | | | |
| 4030DU | 19.75 | | | | | | | | | | |
| 4040DU | 30.25 | | | | | | | | | | |
| 4050DU | 29.75 | | | | | | | | | | |
| 4520DU | 45 | 50 | | 40.25 | | | | | 44.975 44.950 | 50.025 50.000 | 45.105 44.990 |
| 4530DU | 19.75 | | | | | | | | | | |
| 4540DU | 30.25 | | | | | | | | | | |
| 4545DU | 29.75 | | | | | | | | | | |
| 4550DU | 40.25 | | | | | | | | | | |
| 5020DU | 44.75 | | | | | | | | | | |
| 5030DU | 50 | 55 | 20.25 | 49.975 49.950 | 55.030 55.000 | 50.110 49.990 | | | | | |
| 5040DU | 19.75 | | | | | | | | | | |
| 5050DU | 30.25 | | | | | | | | | | |
| 5060DU | 29.75 | | | | | | | | | | |
| 5520DU | 55 | 60 | 40.25 | | | | 54.970 54.940 | 60.030 60.000 | 55.110 54.990 | | |
| 5525DU | 19.75 | | | | | | | | | | |
| 5530DU | 25.25 | | | | | | | | | | |
| 5540DU | 24.75 | | | | | | | | | | |
| 5550DU | 30.25 | | | | | | | | | | |
| 5555DU | 29.75 | | | | | | | | | | |
| 6020DU | 60 | 65 | 20.25 | 59.970 59.940 | 65.030 65.000 | 60.110 59.990 | | | | | |
| 6030DU | 19.75 | | | | | | | | | | |
| 6040DU | 30.25 | | | | | | | | | | |
| 6050DU | 29.75 | | | | | | | | | | |
| 6060DU | 40.25 | | | | | | | | | | |
| 6070DU | 39.75 | | | | | | | | | | |

| Part No. | Nominal Diameter | | Wall thickness S ₃ | Width B | Shaft-∅ D _J [h6, f7, h8] | Housing-∅ D _H [H6, H7] | Bush-∅ D _{I,a} Ass. in H6/H7 housing | Clearance C _D | | | | | | |
|----------|------------------|----------------|----------------------------------|--------------------|--|--------------------------------------|---|-----------------------------|------------------|------------------|------------------|------------------|------------------|------------------|
| | D _i | D _o | | | | | | | max. min. | max. min. | max. min. | max. min. | max. min. | |
| 6530DU | 65 | 70 | 2.505 2.460 | 30.25 | f7 | H7 | 65.110 64.990 | 0.170 0.020 | | | | | | |
| 6550DU | | | | 29.75 | | | | | 64.970 64.940 | 70.030 70.000 | | | | |
| 6570DU | | | | 50.25 49.75 | | | | | | | | | | |
| 7040DU | 70 | 75 | | 40.25 | | | | | 69.970 69.940 | 75.030 75.000 | 70.110 69.990 | | | |
| 7050DU | | | | 39.75 | | | | | | | | | | |
| 7070DU | | | | 50.25 49.75 | | | | | | | | | | |
| 7560DU | 75 | 80 | | 60.25 | | | | | 74.970 74.940 | 80.030 80.000 | 75.110 74.990 | | | |
| 7580DU | | | | 59.75 | | | | | | | | | | |
| 8040DU | | | | 80.25 79.75 | | | | | | | | | | |
| 8060DU | 80 | 85 | | 40.50 | | | | | h8 | H7 | 80.035 85.000 | 80.155 80.020 | | |
| 8080DU | | | | 39.50 | | | | | | | | | 80.000 79.946 | 85.035 85.000 |
| 80100DU | | | | 60.50 59.50 | | | | | | | | | | |
| 8530DU | 85 | 90 | 80.50 79.50 | 85.000 84.946 | 90.035 90.000 | 85.155 85.020 | | | | | | | | |
| 8560DU | | | 100.50 99.50 | | | | | | | | | | | |
| 85100DU | | | 30.50 29.50 | | | | | | | | | | | |
| 9060DU | 90 | 95 | 60.50 | 90.000 89.946 | 95.035 95.000 | 90.155 90.020 | | | | | | | | |
| 90100DU | | | 59.50 | | | | | | | | | | | |
| 9560DU | | | 100.50 99.50 | | | | | | | | | | | |
| 95100DU | 95 | 100 | 60.50 | 95.000 94.946 | 100.035 100.000 | 95.155 95.020 | | | | | | | | |
| 10050DU | | | 59.50 | | | | | | | | | | | |
| 10060DU | | | 100.50 99.50 | | | | | | | | | | | |
| 100115DU | 100 | 105 | 50.50 49.50 | 100.000 99.946 | 105.035 105.000 | 100.155 100.020 | | | | | | | | |
| 10560DU | | | 60.50 | | | | | | | | | | | |
| 105115DU | | | 115.50 114.50 | | | | | | | | | | | |
| 11060DU | 105 | 110 | 60.50 | 105.000 104.946 | 110.035 110.000 | 105.155 105.020 | | | | | | | | |
| 110115DU | | | 59.50 | | | | | | | | | | | |
| 11550DU | | | 115.50 114.50 | | | | | | | | | | | |
| 11570DU | 110 | 115 | 60.50 | 110.000 109.946 | 115.035 115.000 | 110.155 110.020 | | | | | | | | |
| 12050DU | | | 59.50 | | | | | | | | | | | |
| 12060DU | | | 50.50 49.50 | | | | | | | | | | | |
| 120100DU | 115 | 120 | 70.50 | 115.000 114.946 | 120.035 120.000 | 115.155 115.020 | | | | | | | | |
| 125100DU | | | 69.50 | | | | | | | | | | | |
| 13060DU | | | 50.50 49.50 | | | | | | | | | | | |
| 12060DU | 120 | 125 | 60.50 | 120.000 119.946 | 125.040 125.000 | 120.210 120.070 | | | | | | | | |
| 120100DU | | | 59.50 | | | | | | | | | | | |
| 125100DU | | | 100.50 99.50 | | | | | | | | | | | |
| 13060DU | 125 | 130 | 100.50 | 125.000 124.937 | 130.040 130.000 | 125.210 125.070 | | | | | | | | |
| 130100DU | | | 99.50 | | | | | | | | | | | |
| 13060DU | | | 60.50 | | | | | | | | | | | |
| 130100DU | 130 | 135 | 59.50 | 130.000 129.937 | 135.040 135.000 | 130.210 130.070 | | | | | | | | |
| 13060DU | | | 100.50 | | | | | | | | | | | |
| 130100DU | | | 99.50 | | | | | | | | | | | |
| 12060DU | 120 | 125 | 2.490 | h8 | H7 | 120.035 125.000 | 120.210 120.070 | | | | | | | |
| 120100DU | | | 2.440 | | | | | | | | | | | |
| 125100DU | | | 100.50 99.50 | | | | | | | | | | | |
| 13060DU | 130 | 135 | 2.465 | h8 | H7 | 130.040 135.000 | 130.210 130.070 | | | | | | | |
| 130100DU | | | 2.415 | | | | | | | | | | | |
| 13060DU | | | 60.50 | | | | | | | | | | | |

8 Standard Products

| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | Clearance C_D | | | | |
|----------|------------------|-------|-------------------------|-----------------|--|--|---|--------------------|--------------------|--------------------|--------------------|----------------|
| | D_i | D_o | | | | | | | max. min. | max. min. | max. min. | max. min. |
| 13560DU | 135 | 140 | 2.465 2.415 | 60.50 | h8 | H7 | 135.210 135.070 | 0.273 0.070 | | | | |
| 13580DU | | | | 80.50 | | | | | 135.000 134.937 | 140.040 140.000 | | |
| 14060DU | 140 | 145 | | 60.50 | | | | | 140.000 | 145.040 | | |
| 140100DU | | | | 80.50 | | | | | 140.000 139.937 | 145.040 145.000 | | |
| 15060DU | 150 | 155 | | 60.50 | | | | | 150.000 149.937 | 155.040 155.000 | 150.210 150.070 | |
| 15080DU | | | | 80.50 | | | | | | | | |
| 150100DU | | | | 99.50 | | | | | | | | |
| 16080DU | 160 | 165 | | 80.50 | | | | | 160.000 159.937 | 165.040 165.000 | 160.210 160.070 | |
| 160100DU | | | | 99.50 | | | | | | | | |
| 180100DU | 180 | 185 | | 100.50 99.50 | | | | | 180.000 179.937 | 185.046 185.000 | 180.216 180.070 | 0.279 0.070 |
| 200100DU | 200 | 205 | | | | | | | 200.000 199.928 | 205.046 205.000 | 200.216 200.070 | 0.288 0.070 |
| 210100DU | 210 | 215 | | | | | | | 210.000 209.928 | 215.046 215.000 | 210.216 210.070 | |
| 220100DU | 220 | 225 | | | | | | | 220.000 219.928 | 225.046 225.000 | 220.216 220.070 | |
| 250100DU | 250 | 255 | | | | | | | 250.000 249.928 | 255.052 255.000 | 250.222 250.070 | 0.294 0.070 |
| 300100DU | 300 | 305 | | | | | | | 300.000 299.919 | 305.052 305.000 | 300.222 300.070 | 0.303 0.070 |

8.2 DU Flanged Bushes

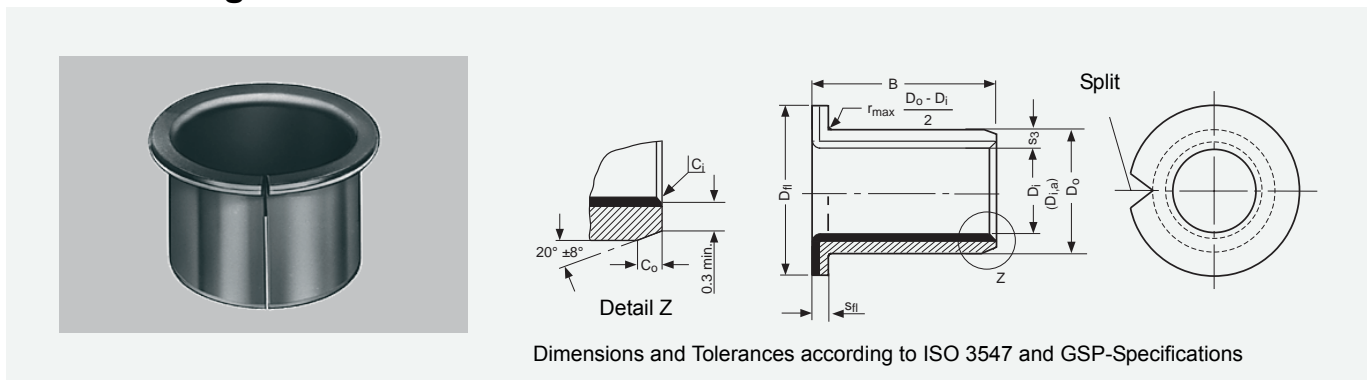

All dimensions in mm

Outside C_o and Inside C_i chamfers

| Wall thickness s_3 | C_o (a) | | C_i (b) |
|-------------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 0.75 | 0.5 ± 0.3 | 0.5 ± 0.3 | -0.1 to -0.4 |
| 1 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.5 |
| 1.5 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.7 |

| Wall thickness s_3 | C_o (a) | | C_i (b) |
|-------------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 2 | 1.2 ± 0.4 | 1.0 ± 0.4 | -0.1 to -0.7 |
| 2.5 | 1.8 ± 0.6 | 1.2 ± 0.4 | -0.2 to -1.0 |



a = Chamfer C_o machined or rolled at the opinion of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

| Part No. | Nominal Diameter | | Wall thickness s_3 | Flange thickness s_f | Flange- \varnothing D_f | Width B | Shaft- \varnothing D_J [h6, f7] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | Clearance C_D |
|----------|------------------|-------|-------------------------|---------------------------|--------------------------------|--------------|--|--|---|--------------------|
| | D_i | D_o | | | | | | | | |
| BB0304DU | 3 | 4.5 | 0.750 0.730 | 0.80 0.70 | 7.50 | 4.25 | h6 | H6 | 3.048 3.000 | 0.054 0.000 |
| BB0404DU | | | | | 6.50 | | | | | |
| BB0505DU | 5 | 7 | 1.005 0.980 | 1.05 0.80 | 10.50 | 5.25 4.75 | f7 | H7 | 5.055 4.990 | 0.077 0.000 |
| | | | | | 9.50 | | | | | |

| Part No. | Nominal Diameter | | Wall thickness S_3 | Flange thickness S_{fl} | Flange- \varnothing D_{fl} | Width B | Shaft- \varnothing D_J [h6, f7] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | Clearance C_D | | | | | | |
|----------|------------------|----------------|----------------------|---------------------------|--------------------------------|------------------|-------------------------------------|---------------------------------------|---|-----------------|------------------|------------------|------------------|------------------|------------------|----------------|
| | D_i | D_o | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | | | | | | |
| BB0604DU | 6 | 8 | 1.005 0.980 | 1.05 0.80 | 12.50 11.50 | 4.25 | 5.990 5.978 | 8.015 8.000 | 6.055 5.990 | 0.077 0.000 | | | | | | |
| BB0608DU | | | | | | 3.75 | | | | | | | | | | |
| BB0806DU | | | | | | 8.25 | | | | | | | | | | |
| BB0808DU | 7.75 | 15.50 14.50 | | | 5.75 | 7.987 7.972 | | | | | 10.015 10.000 | 8.055 7.990 | | | | |
| BB0810DU | 7.25 | | | | | | | | | | | | | | | |
| BB1007DU | 9.75 | | | | | | | | | | | | | | | |
| BB1009DU | 9.25 | 18.50 17.50 | | | 7.25 | 9.987 9.972 | | | | | 12.018 12.000 | 10.058 9.990 | | | | |
| BB1012DU | 6.75 | | | | | | | | | | | | | | | |
| BB1017DU | 9.25 | | | | | | | | | | | | | | | |
| BB1207DU | 12 | 14 | | | 1.005 0.980 | 1.05 0.80 | | | | | 20.50 19.50 | 8.75 | 11.984 11.966 | 14.018 14.000 | 12.058 11.990 | 0.092 0.006 |
| BB1209DU | | | | | | | | | | | | 12.25 | | | | |
| BB1212DU | | | | | | | | | | | | 11.75 | | | | |
| BB1217DU | 17.25 | 22.50 21.50 | | | 12.25 | 13.984 13.966 | | | | | 16.018 16.000 | 14.058 13.990 | | | | |
| BB1412DU | 16.75 | | | | | | | | | | | | | | | |
| BB1417DU | 12.25 | | | | | | | | | | | | | | | |
| BB1509DU | 15 | 17 | | | 1.005 0.980 | 1.05 0.80 | | | | | 23.50 22.50 | 9.25 | 14.984 14.966 | 17.018 17.000 | 15.058 14.990 | |
| BB1512DU | | | | | | | | | | | | 8.75 | | | | |
| BB1517DU | | | | | | | | | | | | 12.25 | | | | |
| BB1612DU | 16 | 18 | 1.005 0.980 | 1.05 0.80 | 24.50 23.50 | 17.25 | 15.984 15.966 | 18.018 18.000 | 16.058 15.990 | | | | | | | |
| BB1617DU | | | | | | 16.75 | | | | | | | | | | |
| BB1812DU | | | | | | 12.25 | | | | | | | | | | |
| BB1817DU | 18 | 20 | 1.005 0.980 | 1.05 0.80 | 26.50 25.50 | 11.75 | 17.984 17.966 | 20.021 20.000 | 18.061 17.990 | | | | | | | |
| BB1822DU | | | | | | 17.25 | | | | | | | | | | |
| BB2012DU | | | | | | 21.75 | | | | | | | | | | |
| BB2017DU | 20 | 23 | 1.505 1.475 | 1.60 1.30 | 30.50 29.50 | 11.75 | 19.980 19.959 | 23.021 23.000 | 20.071 19.990 | | | | | | | |
| BB2022DU | | | | | | 16.25 | | | | | | | | | | |
| BB2512DU | | | | | | 21.75 | | | | | | | | | | |
| BB2517DU | 25 | 28 | 1.505 1.475 | 1.60 1.30 | 35.50 34.50 | 11.75 | 24.980 24.959 | 28.021 28.000 | 25.071 24.990 | | | | | | | |
| BB2522DU | | | | | | 11.25 | | | | | | | | | | |
| BB3016DU | | | | | | 16.25 | | | | | | | | | | |
| BB3026DU | 30 | 34 | 1.505 1.475 | 1.60 1.30 | 42.50 41.50 | 15.75 | 29.980 29.959 | 34.025 34.000 | 30.085 29.990 | | | | | | | |
| BB3516DU | | | | | | 26.25 | | | | | | | | | | |
| BB3526DU | | | | | | 25.75 | | | | | | | | | | |
| BB4016DU | 35 | 39 | 2.005 1.970 | 2.10 1.80 | 47.50 46.50 | 16.25 | 34.975 34.950 | 39.025 39.000 | 35.085 34.990 | | | | | | | |
| BB4026DU | | | | | | 15.75 | | | | | | | | | | |
| BB4516DU | | | | | | 26.25 | | | | | | | | | | |
| BB4526DU | 40 | 44 | 2.005 1.970 | 2.10 1.80 | 53.50 52.50 | 16.25 | 39.975 39.950 | 44.025 44.000 | 40.085 39.990 | | | | | | | |
| BB4526DU | | | | | | 15.75 | | | | | | | | | | |
| BB4526DU | | | | | | 25.75 | | | | | | | | | | |
| BB4516DU | 45 | 50 | 2.505 2.460 | 2.60 2.30 | 58.50 57.50 | 16.25 | 44.975 44.950 | 50.025 50.000 | 45.105 44.990 | | | | | | | |
| BB4526DU | | | | | | 15.75 | | | | | | | | | | |
| BB4526DU | | | | | | 25.75 | | | | | | | | | | |

8.3 DU Flanged Washers

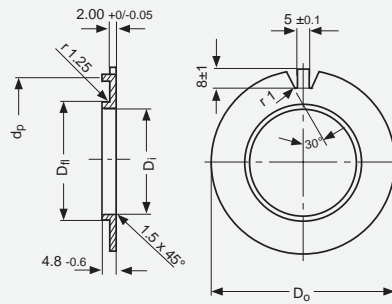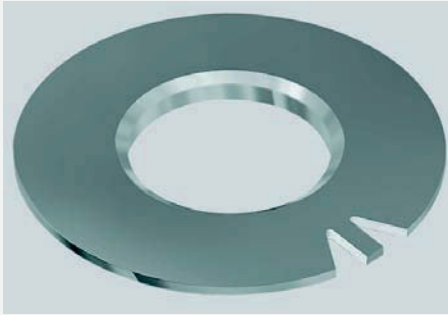


All dimensions in mm

| Part No. | Inside- \varnothing | Outside- \varnothing | Flange- \varnothing | Location- \varnothing |
|----------|-----------------------|------------------------|-----------------------|-------------------------|
| | D_i | D_o | D_{fl} | d_P |
| | max. min. | max. min. | max. min. | max. min. |
| BS40DU | 40.7 40.2 | 75.0 74.5 | 44.000 43.900 | 65.0 64.5 |
| BS50DU | 51.5 51.0 | 85.0 84.5 | 55.000 54.880 | 75.0 74.5 |
| BS60DU | 61.5 61.0 | 95.0 94.5 | 65.000 64.880 | 85.0 84.5 |
| BS70DU | 71.5 71.0 | 110.0 109.5 | 75.000 74.880 | 100.0 99.5 |
| BS80DU | 81.5 81.0 | 120.0 119.5 | 85.000 84.860 | 110.0 109.5 |
| BS90DU | 91.5 91.0 | 130.0 129.5 | 95.000 94.860 | 120.0 119.5 |
| BS100DU | 101.5 101.0 | 140.0 139.5 | 105.000 104.860 | 130.0 129.5 |

Corrosion Protection: Washers will be supplied covered with a light coating of oil.

Tab (Lug) Form: Washers are supplied with this feature in an unformed state (Flat). This feature may be supplied in the formed state only when requested by the customer.

8.4 DU Thrust Washer

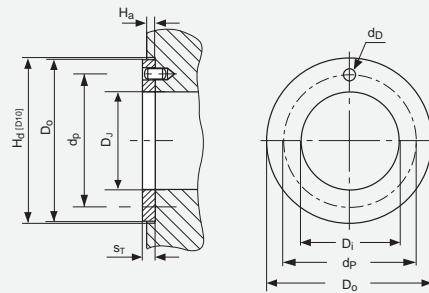


All dimensions in mm

| Part No. | Inside- \varnothing D_i | | Outside- \varnothing D_o | | Thickness s_T max. min. | Dowel Hole | | Recess Depth H_a max. min. |
|----------|--------------------------------|-------|---------------------------------|-------|---------------------------------|-----------------------------------|--|---------------------------------------|
| | min. | max. | max. | min. | | $\varnothing d_D$ max. min. | PCD- $\varnothing d_P$ max. min. | |
| WC08DU | 10.00 | 10.25 | 20.00 | 19.75 | 1.50 1.45 | No Hole | No Hole | 1.20 0.95 |
| WC10DU | 12.00 | 12.25 | 24.00 | 23.75 | | 1.875 1.625 | 18.12 17.88 | |
| WC12DU | 14.00 | 14.25 | 26.00 | 25.75 | | 2.375 2.125 | 20.12 19.88 | |
| WC14DU | 16.00 | 16.25 | 30.00 | 29.75 | | | 22.12 21.88 | |
| WC16DU | 18.00 | 18.25 | 32.00 | 31.75 | | 3.375 3.125 | 25.12 24.88 | |
| WC18DU | 20.00 | 20.25 | 36.00 | 35.75 | | | 28.12 27.88 | |
| WC20DU | 22.00 | 22.25 | 38.00 | 37.75 | | 4.375 4.125 | 30.12 29.88 | |
| WC22DU | 24.00 | 24.25 | 42.00 | 41.75 | | | 33.12 32.88 | |
| WC24DU | 26.00 | 26.25 | 44.00 | 43.75 | | 61.12 60.88 | 35.12 34.88 | |
| WC25DU | 28.00 | 28.25 | 48.00 | 47.75 | | | 38.12 37.88 | |
| WC30DU | 32.00 | 32.25 | 54.00 | 53.75 | | 65.12 64.88 | 43.12 42.88 | |
| WC35DU | 38.00 | 38.25 | 62.00 | 61.75 | | | 50.12 49.88 | |
| WC40DU | 42.00 | 42.25 | 66.00 | 65.75 | | 76.12 75.88 | 54.12 53.88 | |
| WC45DU | 48.00 | 48.25 | 74.00 | 73.75 | | | 61.12 60.88 | |
| WC50DU | 52.00 | 52.25 | 78.00 | 77.75 | 2.00 1.95 | 65.12 64.88 | 1.70 1.45 | |
| WC60DU | 62.00 | 62.25 | 90.00 | 89.75 | | 76.12 75.88 | | |

8 Standard Products

8.5 DUB Cylindrical Bushes

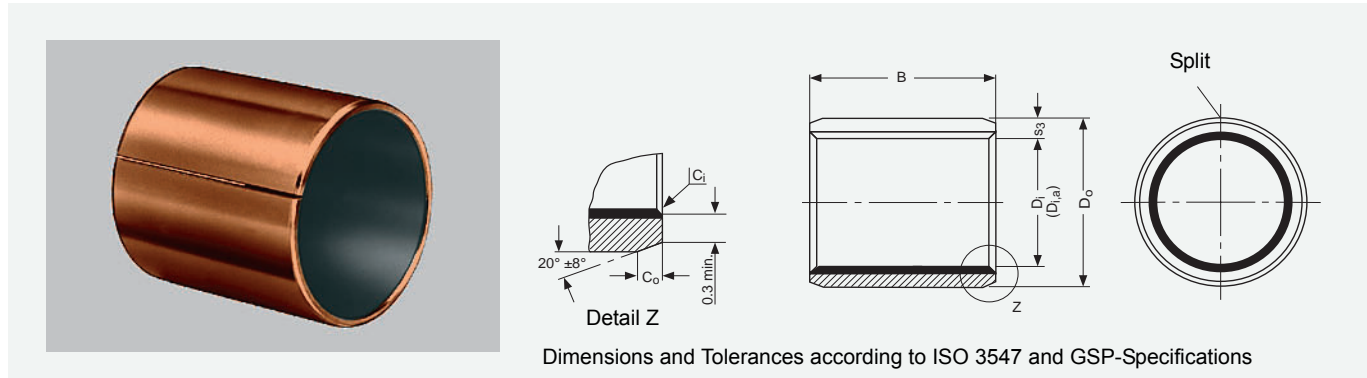

All dimensions in mm

Outside Co and Inside Ci chamfers

| Wall thickness s_3 | C_o (a) | | C_i (b) |
|-------------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 0.75 | 0.5 ± 0.3 | 0.5 ± 0.3 | -0.1 to -0.4 |
| 1 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.5 |
| 1.5 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.7 |

| Wall thickness s_3 | C_o (a) | | C_i (b) |
|-------------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 2 | 1.2 ± 0.4 | 1.0 ± 0.4 | -0.1 to -0.7 |
| 2.5 | 1.8 ± 0.6 | 1.2 ± 0.4 | -0.2 to -1.0 |

a = Chamfer C_o machined or rolled at the opinion of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715


| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_j [h6, f7, h8] | | Housing- \varnothing D_H [H6, H7] | | Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing | Clearance C_D |
|----------|------------------|-------|-------------------------|----------------|--|------------------|--|------------------|---|--------------------|
| | D_i | D_o | | | max. min. | max. min. | max. min. | max. min. | max. min. | |
| 0203DUB | 2 | 3.5 | 0.750 0.730 | 3.25 | h6 | 2.000 1.994 | H6 | 3.508 3.500 | 2.048 2.000 | 0.054 0.000 |
| 0205DUB | | | | 5.25 4.75 | | | | | | |
| 0306DUB | 3 | 4.5 | 0.750 0.730 | 6.25 5.75 | h6 | 3.000 2.994 | H6 | 4.508 4.500 | 3.048 3.000 | 0.056 0.000 |
| 0404DUB | | | | 4.25 3.75 | | | | | | |
| 0406DUB | 4 | 5.5 | 0.750 0.730 | 6.25 5.75 | h6 | 4.000 3.992 | H6 | 5.508 5.500 | 4.048 4.000 | 0.077 0.000 |
| 0505DUB | | | | 5.25 4.75 | | | | | | |
| 0510DUB | 5 | 7 | 0.750 0.730 | 10.25 9.75 | h6 | 4.990 4.978 | H6 | 7.015 7.000 | 5.055 4.990 | 0.083 0.003 |
| 0606DUB | | | | 6.25 5.75 | | | | | | |
| 0608DUB | 6 | 8 | 0.750 0.730 | 8.25 7.75 | h6 | 5.990 5.978 | H6 | 8.015 8.000 | 6.055 5.990 | 0.086 0.003 |
| 0610DUB | | | | 10.25 9.75 | | | | | | |
| 0808DUB | 8 | 10 | 1.005 0.980 | 8.25 7.75 | f7 | 7.987 7.972 | H7 | 10.015 10.000 | 8.055 7.990 | 0.086 0.003 |
| 0810DUB | | | | 10.25 9.75 | | | | | | |
| 0812DUB | 8 | 10 | 1.005 0.980 | 12.25 11.75 | f7 | 7.987 7.972 | H7 | 10.015 10.000 | 8.055 7.990 | 0.086 0.003 |
| 1010DUB | | | | 10.25 9.75 | | | | | | |
| 1015DUB | 10 | 12 | 1.005 0.980 | 15.25 14.75 | f7 | 9.987 9.972 | H7 | 12.018 12.000 | 10.058 9.990 | 0.086 0.003 |
| 1208DUB | | | | 8.25 7.75 | | | | | | |
| 1210DUB | 12 | 14 | 1.005 0.980 | 10.25 9.75 | f7 | 11.984 11.966 | H7 | 14.018 14.000 | 12.058 11.990 | 0.092 0.006 |
| 1212DUB | | | | 12.25 11.75 | | | | | | |
| 1215DUB | 12 | 14 | 1.005 0.980 | 15.25 14.75 | f7 | 11.984 11.966 | H7 | 14.018 14.000 | 12.058 11.990 | 0.092 0.006 |
| 1215DUB | | | | 15.25 14.75 | | | | | | |

| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_j [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing | Clearance C_D | | | | | | |
|----------|------------------|-------|-------------------------|------------|--|--|---|--------------------|--------------|--------------|------------------|----------------|--------------|--------|
| | D_i | D_o | | | | | | | max. min. | max. min. | max. min. | max. min. | max. min. | |
| 1410DUB | 14 | 16 | 1.005 0.980 | 10.25 | f7 | H7 | 14.058 13.990 | 0.092 0.006 | | | | | | |
| 1415DUB | | | | 9.75 | | | | | 13.984 | 16.018 | | | | |
| 1420DUB | | | | 15.25 | | | | | 13.966 | 16.000 | | | | |
| 1515DUB | 15 | 17 | | 20.25 | | | | | 14.984 | 17.018 | 15.058 | | | |
| 1525DUB | | | | 19.75 | | | | | 14.966 | 17.000 | 14.990 | | | |
| 1615DUB | | | | 15.25 | | | | | 15.984 | 18.018 | 16.058 | | | |
| 1625DUB | 16 | 18 | | 14.75 | | | | | 15.966 | 18.000 | 15.990 | | | |
| 1820DUB | | | | 25.25 | | | | | 17.984 | 20.021 | 18.061 | | | |
| 1825DUB | | | | 24.75 | | | | | 17.966 | 20.000 | 17.990 | | | |
| 2015DUB | 20 | 23 | | 20.25 | | | | | f7 | H7 | 20.071 19.990 | 0.112 0.010 | | |
| 2020DUB | | | | 15.25 | | | | | | | | | 19.980 | 23.021 |
| 2025DUB | | | | 14.75 | | | | | | | | | 19.959 | 23.000 |
| 2030DUB | | | 20.25 | 21.980 | 25.021 | 22.071 | | | | | | | | |
| 2215DUB | | | 19.75 | 21.959 | 25.000 | 21.990 | | | | | | | | |
| 2220DUB | 22 | 25 | 25.25 | f7 | H7 | 25.071 24.990 | 0.135 0.015 | | | | | | | |
| 2225DUB | | | 24.75 | | | | | 24.980 | 28.021 | | | | | |
| 2515DUB | | | 15.25 | | | | | 24.959 | 28.000 | 25.071 | | | | |
| 2525DUB | 25 | 28 | 14.75 | 24.975 | 28.021 | 25.071 | | | | | | | | |
| 2830DUB | | | 25.25 | 27.980 | 28.000 | 28.085 | | | | | | | | |
| 3020DUB | | | 24.75 | 27.959 | 32.025 | 27.990 | | | | | | | | |
| 3030DUB | 30 | 34 | 30.25 | f7 | H7 | 30.085 29.990 | 0.126 0.010 | | | | | | | |
| 3040DUB | | | 20.25 | | | | | 29.980 | 34.025 | | | | | |
| 3520DUB | | | 19.75 | | | | | 29.959 | 34.000 | 35.085 | | | | |
| 3530DUB | 35 | 39 | 40.25 | 34.975 | 39.025 | 35.085 | | | | | | | | |
| 4030DUB | | | 39.75 | 34.950 | 39.000 | 34.990 | | | | | | | | |
| 4050DUB | | | 30.25 | 39.975 | 44.025 | 40.085 | | | | | | | | |
| 4530DUB | 45 | 50 | 29.75 | 39.950 | 44.000 | 39.990 | | | | | | | | |
| 4550DUB | | | 50.25 | 44.975 | 50.025 | 45.105 | | | | | | | | |
| 5040DUB | | | 49.75 | 44.950 | 50.000 | 44.990 | | | | | | | | |
| 5060DUB | 50 | 55 | 40.25 | f7 | H7 | 50.110 49.990 | 0.160 0.015 | | | | | | | |
| 5540DUB | | | 39.75 | | | | | 49.975 | 55.030 | | | | | |
| 6040DUB | | | 60.25 | | | | | 49.950 | 55.000 | 50.110 | | | | |
| 6050DUB | 60 | 65 | 59.75 | 54.970 | 60.030 | 55.110 | | | | | | | | |
| 6060DUB | | | 59.75 | 54.940 | 60.000 | 54.990 | | | | | | | | |
| 6070DUB | | | 40.25 | 59.970 | 65.030 | 60.110 | | | | | | | | |
| 6570DUB | | | 49.75 | 59.940 | 65.000 | 59.990 | | | | | | | | |
| 6570DUB | | | 70.25 | 64.970 | 70.030 | 65.110 | | | | | | | | |
| 6570DUB | 65 | 70 | 69.75 | 64.940 | 70.000 | 64.990 | | | | | | | | |

8 Standard Products

| Part No. | Nominal Diameter | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing | Clearance C_D |
|-----------|------------------|-------|----------------------|--------------------|---|---------------------------------------|---|--------------------|
| | D_i | D_o | | | | | | |
| 7050DUB | 70 | 75 | 2.505 2.460 | 50.25 | f7 | 69.970 69.940 | 75.030 75.000 | 70.110 69.990 |
| 7070DUB | | | | 49.75 | | | | |
| 7580DUB | 75 | 80 | 2.490 2.440 | 80.25 | h7 | 74.970 74.940 | 80.030 80.000 | 75.110 74.990 |
| 8060DUB | 80 | 85 | | 60.50 | | 80.000 79.946 | 85.035 85.000 | 80.155 80.020 |
| 80100DUB | | | 59.50 | 100.50 99.50 | h8 | 90.000 89.946 | 90.035 90.000 | 85.155 85.020 |
| 85100DUB | 85 | 90 | 100.50 99.50 | 85.000 84.946 | | 90.035 90.000 | 85.155 85.020 | 0.209 0.020 |
| 9060DUB | 90 | 95 | 60.50 | H7 | 90.000 89.946 | 95.035 95.000 | 90.155 90.020 | |
| 90100DUB | | | 59.50 | | | | | 100.50 99.50 |
| 95100DUB | 95 | 100 | 100.50 99.50 | 95.000 94.946 | 100.035 100.000 | 95.155 95.020 | 0.209 0.020 | |
| 10060DUB | 100 | 105 | 60.50 | h8 | 100.000 99.946 | 105.035 105.000 | | 100.155 100.020 |
| 100115DUB | | | 59.50 | | | | 115.50 114.50 | |
| 105115DUB | 105 | 110 | 115.50 114.50 | 105.000 104.946 | 110.035 110.000 | 105.155 105.020 | 0.209 0.020 | |
| 110115DUB | 110 | 115 | 115.50 114.50 | 110.000 109.946 | 115.035 115.000 | 115.155 115.020 | | |

8.6 DUB Flanged Bushes

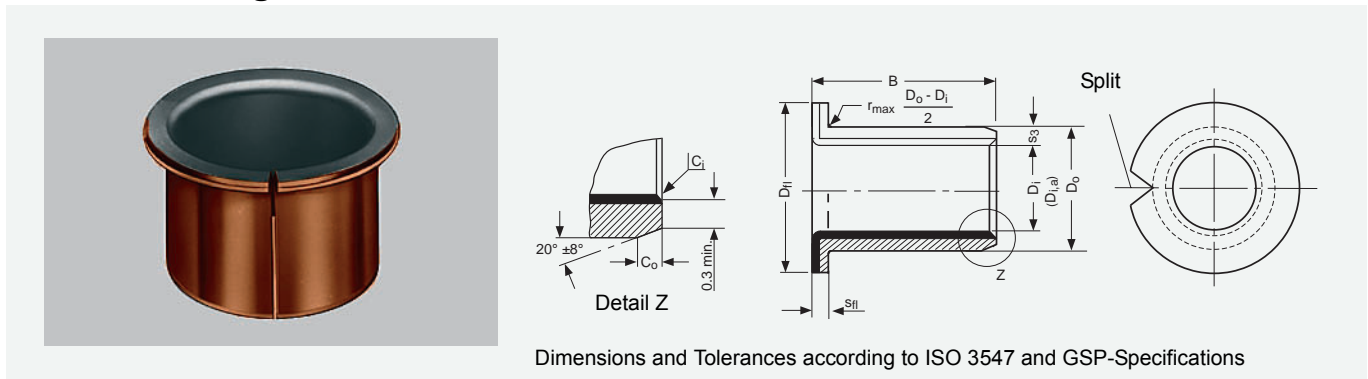

All dimensions in mm

Outside C_0 and Inside C_1 chamfers

| Wall thickness s_3 | C_0 (a) | | C_1 (b) |
|----------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 0.75 | 0.5 ± 0.3 | 0.5 ± 0.3 | -0.1 to -0.4 |
| 1 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.5 |
| 1.5 | 0.6 ± 0.4 | 0.6 ± 0.4 | -0.1 to -0.7 |

| Wall thickness s_3 | C_0 (a) | | C_1 (b) |
|----------------------|---------------|---------------|--------------|
| | machined | rolled | |
| 2 | 1.2 ± 0.4 | 1.0 ± 0.4 | -0.1 to -0.7 |
| 2.5 | 1.8 ± 0.6 | 1.2 ± 0.4 | -0.2 to -1.0 |

a = Chamfer C_0 machined or rolled at the opinion of the manufacturer


b = C_1 can be a radius or a chamfer in accordance with ISO 13715

| Part No. | Nominal Diameter | | Wall thickness s_3 | Flange thickness s_{fi} | Flange- \varnothing D_{fi} | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing | Clearance C_D |
|-----------|------------------|-------|----------------------|---------------------------|--------------------------------|--------------|---|---------------------------------------|---|-----------------|
| | D_i | D_o | | | | | | | | |
| BB0304DUB | 3 | 4.5 | 0.750 0.730 | 0.80 0.70 | 7.50 | 4.25 | h6 | H6 | 3.048 3.000 | 0.054 0.000 |
| BB0404DUB | | | | | 6.50 | | | | | |
| BB0505DUB | 5 | 7 | 1.005 0.980 | 1.05 0.80 | 10.50 | 5.25 4.75 | f7 | H7 | 5.055 4.990 | 0.077 0.000 |
| | | | | | 9.50 | | | | | |

| Part No. | Nominal Diameter | | Wall thickness S_3 | Flange thickness S_{fl} | Flange- \varnothing D_{fl} | Width B | Shaft- \varnothing D_J [h6, f7, h8] | Housing- \varnothing D_H [H6, H7] | Bush- \varnothing D_{La} Ass. in H6/H7 housing | Clearance C_D | | |
|-----------|------------------|-------|----------------------|---------------------------|--------------------------------|------------------|---|---------------------------------------|--|------------------|------------------|----------------|
| | D_i | D_o | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. | | |
| BB0604DUB | 6 | 8 | 1.005 0.980 | 1.05 0.80 | 12.50 11.50 | 4.25 | f7 | H7 | 6.055 5.990 | 0.077 0.000 | | |
| BB0608DUB | | | | | | 3.75 | | | | | 5.990 5.978 | |
| BB0806DUB | 8 | 10 | | | 15.50 14.50 | 5.75 | | | 7.987 7.972 | 10.015 10.000 | 8.055 7.990 | 0.083 0.000 |
| BB0810DUB | | | | | | 5.25 | | | | | | |
| BB1007DUB | 10 | 12 | | | 18.50 17.50 | 7.25 | | | 9.987 9.972 | 12.018 12.000 | 10.058 9.990 | 0.086 0.003 |
| BB1012DUB | | | | | | 6.75 | | | | | | |
| BB1207DUB | 12 | 14 | | | 20.50 19.50 | 7.25 | | | 11.984 11.966 | 14.018 14.000 | 12.058 11.990 | 0.092 0.006 |
| BB1209DUB | | | | | | 6.75 | | | | | | |
| BB1212DUB | | | | | | 9.25 | | | | | | |
| BB1417DUB | 14 | 16 | | | 22.50 21.50 | 7.25 | | | 13.984 13.966 | 16.018 16.000 | 14.05 13.990 | 0.092 0.006 |
| BB1512DUB | | | | | | 9.25 | | | | | | |
| BB1517DUB | 15 | 17 | | | 23.50 22.50 | 11.75 | | | 14.984 14.966 | 17.018 17.000 | 15.058 14.990 | 0.092 0.006 |
| BB1612DUB | | | | | | 12.25 | | | | | | |
| BB1617DUB | 16 | 18 | | | 24.50 23.50 | 11.75 | | | 15.984 15.966 | 18.018 18.000 | 16.058 15.990 | 0.092 0.006 |
| BB1812DUB | | | | | | 12.25 | | | | | | |
| BB1822DUB | 18 | 20 | | | 26.50 25.50 | 11.75 | | | 17.984 17.966 | 20.021 20.000 | 18.061 17.990 | 0.095 0.006 |
| BB2012DUB | | | 12.25 | | | | | | | | | |
| BB2017DUB | 20 | 23 | 30.50 29.50 | 11.25 | 19.980 19.959 | 23.021 23.000 | 20.071 19.990 | 0.112 0.010 | | | | |
| BB2512DUB | | | | 16.25 | | | | | | | | |
| BB2522DUB | 25 | 28 | 35.50 34.50 | 11.75 | 24.980 24.959 | 28.021 28.000 | 25.071 24.990 | 0.112 0.010 | | | | |
| BB3016DUB | | | | 11.25 | | | | | | | | |
| BB3026DUB | 30 | 34 | 42.50 41.50 | 15.75 | 29.980 29.959 | 34.025 34.000 | 30.085 29.990 | 0.126 0.010 | | | | |
| BB3526DUB | | | | 16.25 | | | | | | | | |
| BB3526DUB | 35 | 39 | 47.50 46.50 | 25.75 | 34.975 34.950 | 39.025 39.000 | 35.085 34.990 | 0.135 0.015 | | | | |
| BB4026DUB | | | | 25.75 | | | | | | | | |
| BB4026DUB | 40 | 44 | 53.50 52.50 | 26.25 | 39.975 39.950 | 44.025 44.000 | 40.085 39.990 | 0.135 0.015 | | | | |
| BB4526DUB | | | | 25.75 | | | | | | | | |
| BB4526DUB | 45 | 50 | 58.50 57.50 | 26.25 | 44.975 44.950 | 50.025 50.000 | 45.105 44.990 | 0.155 0.015 | | | | |
| BB4526DUB | | | | 25.75 | | | | | | | | |

8 Standard Products

8.7 DU Cylindrical Bushes - Inch sizes

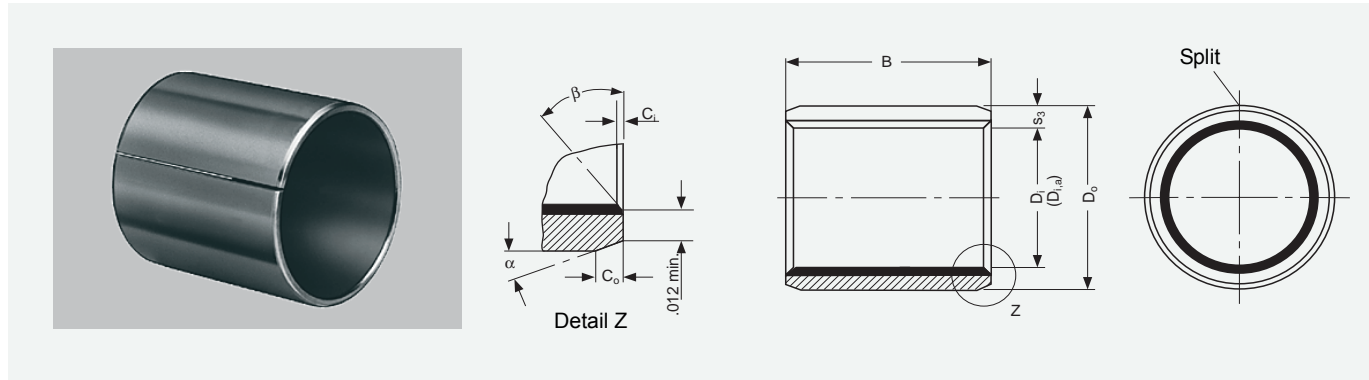

All dimensions in inch

ID and OD chamfers

| D_i | C_o | α | C_i | β |
|---------------|-----------------|----------|-----------------|---------|
| 1/8" - 5/16" | 0.008" - 0.024" | 30°-45° | 0.004" - 0.012" | 30°-45° |
| 3/8" - 11/16" | 0.020" - 0.040" | 20°-30° | 0.005" - 0.025" | 40°-55° |
| 3/4" - 7" | 0.020" - 0.040" | 15°-25° | 0.005" - 0.025" | 40°-50° |



| Part No. | Nominal Diameter | | | Wall thickness s_3 | Width B | Shaft- \varnothing D_j | Housing- \varnothing D_H | Bush- \varnothing $D_{i,a}$ Ass. in D_H housing | Clearance C_D | | | |
|----------|------------------|-------|------|----------------------|---------|----------------------------|------------------------------|---|------------------|--------------|--------------|--------------|
| | D_i | D_o | B | | | | | | | max. min. | max. min. | max. min. |
| 02DU02 | 1/8 | 3/16 | 1/8 | 0.0315 0.0305 | 0.1350 | 0.1243 | 0.1878 | 0.1268 | 0.0032 | | | |
| 02DU03 | | | 3/16 | | 0.1150 | | | | | 0.1236 | 0.1873 | 0.1243 |
| 025DU025 | 5/32 | 7/32 | 5/32 | | 0.16625 | 0.1554 | 0.2191 | 0.1581 | 0.0034 | | | |
| 025DU04 | | | 1/4 | | 0.14265 | | | | | 0.2186 | 0.1556 | 0.0002 |
| 03DU03 | 3/16 | 1/4 | 3/16 | | 0.1975 | 0.1865 | 0.2503 | 0.1893 | 0.0035 | | | |
| 03DU04 | | | 1/4 | | 0.1775 | | | | | 0.2497 | 0.1867 | 0.0002 |
| 03DU06 | | | 3/8 | | 0.3850 | | | | | | | |
| 04DU04 | 1/4 | 5/16 | 1/4 | | 0.2600 | 0.2490 | 0.3128 | 0.2518 | 0.0037 0.0002 | | | |
| 04DU06 | | | 3/8 | | 0.2400 | | | | | 0.3122 | 0.2492 | |
| 05DU06 | 5/16 | 3/8 | 3/8 | | 0.3850 | 0.3115 | 0.3753 | 0.3143 | | | | |
| 05DU08 | | | 1/2 | | 0.3650 | | | | | 0.3747 | 0.3117 | |
| 06DU06 | | | 3/8 | | 0.5100 | | | | | | | |
| 06DU08 | 3/8 | 15/32 | 1/2 | 0.3850 | 0.3740 | 0.4691 | 0.3769 | 0.0038 0.0002 | | | | |
| 06DU12 | | | 3/4 | 0.3650 | | | | | 0.4684 | 0.3742 | | |
| 07DU08 | 7/16 | 17/32 | 1/2 | 0.5100 | 0.4365 | 0.5316 | 0.4394 | | | | | |
| 07DU12 | | | 3/4 | 0.4900 | | | | 0.5309 | 0.4367 | 0.0002 | | |
| 08DU06 | | | 3/8 | 0.7600 | | | | | | | | |
| 08DU08 | 1/2 | 19/32 | 1/2 | 0.7400 | 0.4990 | 0.5941 | 0.5019 | 0.0039 0.0002 | | | | |
| 08DU10 | | | 5/8 | 0.4900 | | | | | 0.5934 | 0.4992 | | |
| 08DU14 | | | 7/8 | 0.6350 | | | | | | | | |
| 09DU08 | | | 1/2 | 0.6150 | | | | | | | | |
| 09DU12 | 9/16 | 21/32 | 1/2 | 0.8850 | 0.5615 | 0.6566 | 0.5644 | | | | | |
| | | | 3/4 | 0.8650 | | | | | 0.6559 | 0.5617 | | |

| Part No. | Nominal Diameter | | | Wall thickness s_3 | Width B | Shaft- \varnothing D_J | Housing- \varnothing D_H | Bush- \varnothing $D_{1,a}$ Ass. in D_H housing | Clearance C_D |
|----------|------------------|---------|-------|----------------------|------------------|----------------------------|------------------------------|---|------------------|
| | D_i | D_o | B | | | | | | |
| 10DU08 | 5/8 | 23/32 | 1/2 | 0.0471 0.0461 | 0.5100 0.4900 | 0.6240 0.6230 | 0.7192 0.7184 | 0.6270 0.6242 | 0.0040 0.0002 |
| 10DU10 | | | 5/8 | | 0.6350 0.6150 | | | | |
| 10DU12 | | | 3/4 | | 0.7600 0.7400 | | | | |
| 10DU14 | | | 7/8 | | 0.8850 0.8650 | | | | |
| 11DU14 | 11/16 | 25/32 | 7/8 | | 0.8850 0.8650 | 0.6865 0.6855 | 0.7817 0.7809 | 0.6895 0.6867 | |
| 12DU08 | 3/4 | 7/8 | 1/2 | 0.0627 0.0615 | 0.5100 0.4900 | 0.7491 0.7479 | 0.8755 0.8747 | 0.7525 0.7493 | 0.0046 0.0002 |
| 12DU12 | | | 3/4 | | 0.7600 0.7400 | | | | |
| 12DU16 | | | 1 | | 1.0100 0.9900 | | | | |
| 14DU12 | 7/8 | 1 | 3/4 | 0.0627 0.0615 | 0.7600 0.7400 | 0.8741 0.8729 | 1.0005 0.9997 | 0.8775 0.8743 | 0.0047 0.0001 |
| 14DU14 | | | 7/8 | | 0.8850 0.8650 | | | | |
| 14DU16 | | | 1 | | 1.0100 0.9900 | | | | |
| 16DU12 | | | 3/4 | | 0.7600 0.7400 | | | | |
| 16DU16 | 1 | 1 1/8 | 1 | 0.0784 0.0770 | 1.0100 0.9900 | 0.9991 0.9979 | 1.1256 1.1246 | 1.0026 0.9992 | 0.0052 0.0002 |
| 16DU24 | | | 1 1/2 | | 1.5100 1.4900 | | | | |
| 18DU12 | 1 1/8 | 1 9/32 | 3/4 | 0.0784 0.0770 | 0.7600 0.7400 | 1.1238 1.1226 | 1.2818 1.2808 | 1.1278 1.1240 | 0.0056 0.0002 |
| 18DU16 | | | 1 | | 1.0100 0.9900 | | | | |
| 20DU12 | 1 1/4 | 1 13/32 | 3/4 | 0.0784 0.0770 | 0.7600 0.7400 | 1.2488 1.2472 | 1.4068 1.4058 | 1.2528 1.2490 | 0.0056 0.0002 |
| 20DU16 | | | 1 | | 1.0100 0.9900 | | | | |
| 20DU20 | | | 1 1/4 | | 1.2600 1.2400 | | | | |
| 20DU28 | | | 1 3/4 | | 1.7600 1.7400 | | | | |
| 22DU16 | 1 3/8 | 1 17/32 | 1 | 0.0784 0.0770 | 1.0100 0.9900 | 1.3738 1.3722 | 1.5318 1.5308 | 1.3778 1.3740 | 0.0056 0.0002 |
| 22DU22 | | | 1 3/8 | | 1.3850 1.3650 | | | | |
| 22DU28 | | | 1 3/4 | | 1.7600 1.7400 | | | | |
| 24DU16 | 1 1/2 | 1 21/32 | 1 | 0.0941 0.0923 | 1.0100 0.9900 | 1.4988 1.4972 | 1.6568 1.6558 | 1.5028 1.4990 | 0.0064 0.0002 |
| 24DU20 | | | 1 1/4 | | 1.2600 1.2400 | | | | |
| 24DU24 | | | 1 1/2 | | 1.5100 1.4900 | | | | |
| 24DU32 | | | 2 | | 2.0100 1.9900 | | | | |
| 26DU16 | 1 5/8 | 1 25/32 | 1 | 0.0941 0.0923 | 1.0100 0.9900 | 1.6238 1.6222 | 1.7818 1.7808 | 1.6278 1.6240 | 0.0056 0.0002 |
| 26DU24 | | | 1 1/2 | | 1.5100 1.4900 | | | | |
| 28DU16 | 1 3/4 | 1 15/16 | 1 | 0.0941 0.0923 | 1.0100 0.9900 | 1.7487 1.7471 | 1.9381 1.9371 | 1.7535 1.7489 | 0.0064 0.0002 |
| 28DU24 | | | 1 1/2 | | 1.5100 1.4900 | | | | |
| 28DU28 | | | 1 3/4 | | 1.7600 1.7400 | | | | |
| 28DU32 | | | 2 | | 2.0100 1.9900 | | | | |

8 Standard Products

| Part No. | Nominal Diameter | | | Wall thickness S_3 | Width B | Shaft- \varnothing D_J | Housing- \varnothing D_H | Bush- \varnothing $D_{I,a}$ Ass. in D_H housing | Clearance C_D |
|----------|------------------|------------------|----------------|----------------------|------------------|----------------------------|------------------------------|---|------------------|
| | D_I | D_O | B | max. min. | max. min. | max. min. | max. min. | max. min. | max. min. |
| 30DU16 | $1\frac{7}{8}$ | $2\frac{1}{16}$ | 1 | 0.0941 0.0923 | 1.0100 0.9900 | 1.8737 1.8721 | 2.0633 2.0621 | 1.8787 1.8739 | 0.0066 0.0002 |
| 30DU30 | | | $1\frac{7}{8}$ | | 1.8850 1.8650 | | | | |
| 30DU36 | | | $2\frac{1}{4}$ | | 2.2600 2.2400 | | | | |
| 32DU16 | 2 | $2\frac{3}{16}$ | 1 | | 1.0100 0.9900 | 1.9987 1.9969 | 2.1883 2.1871 | 2.0037 1.9989 | 0.0068 0.0002 |
| 32DU24 | | | $1\frac{1}{2}$ | | 1.5100 1.4900 | | | | |
| 32DU32 | | | 2 | | 2.0100 1.9900 | | | | |
| 32DU40 | | | $2\frac{1}{2}$ | | 2.5100 2.4900 | | | | |
| 36DU32 | $2\frac{1}{4}$ | $2\frac{7}{16}$ | 2 | | 2.0100 1.4900 | 2.2507 2.2489 | 2.4377 2.4365 | 2.2573 2.2509 | 0.0084 0.0002 |
| 36DU36 | | | $2\frac{1}{4}$ | | 2.2600 2.2400 | | | | |
| 36DU40 | | | $2\frac{1}{2}$ | | 2.5100 2.4900 | | | | |
| 36DU48 | | | 3 | | 3.0100 2.9900 | | | | |
| 40DU32 | $2\frac{1}{2}$ | $2\frac{11}{16}$ | 2 | | 2.0100 1.9900 | 2.5011 2.4993 | 2.6881 2.6869 | 2.5077 2.5013 | |
| 40DU40 | | | $2\frac{1}{2}$ | 2.5100 2.4900 | | | | | |
| 40DU48 | | | 3 | 3.0100 2.9900 | | | | | |
| 40DU56 | | | $3\frac{1}{2}$ | 3.5100 3.4900 | | | | | |
| 44DU32 | $2\frac{3}{4}$ | $2\frac{15}{16}$ | 2 | 2.0100 1.9900 | 2.7500 2.7482 | 2.9370 2.9358 | 2.7566 2.7502 | | |
| 44DU40 | | | $2\frac{1}{2}$ | 2.5100 2.4900 | | | | | |
| 44DU48 | | | 3 | 3.0100 2.9900 | | | | | |
| 44DU56 | | | $3\frac{1}{2}$ | 3.5100 3.4900 | | | | | |
| 48DU32 | 3 | $3\frac{3}{16}$ | $2\frac{1}{2}$ | 2.5100 2.4900 | 3.0000 2.9982 | 3.1872 3.1858 | 3.0068 3.0002 | 0.0086 0.0002 | |
| 48DU48 | | | 3 | 3.0100 2.9900 | | | | | |
| 48DU60 | | | $3\frac{3}{4}$ | 3.7600 3.7400 | | | | | |
| 56DU40 | $3\frac{1}{2}$ | $3\frac{11}{16}$ | $2\frac{1}{2}$ | 2.5100 2.4900 | 3.5000 3.4978 | 3.6872 3.6858 | 3.5068 3.5002 | 0.0090 0.0002 | |
| 56DU48 | | | 3 | 3.0100 2.9900 | | | | | |
| 56DU60 | | | $3\frac{3}{4}$ | 3.7600 3.7400 | | | | | |
| 64DU48 | 4 | $4\frac{3}{16}$ | 3 | 3.0100 2.9900 | 4.0000 3.9978 | 4.1872 4.1858 | 4.0068 4.0002 | 0.0090 0.0002 | |
| 64DU60 | | | $3\frac{3}{4}$ | 3.7600 3.7400 | | | | | |
| 64DU76 | | | $4\frac{3}{4}$ | 4.7600 4.7400 | | | | | |
| 80DU48 | 5 | $5\frac{3}{16}$ | 3 | 3.0100 2.9900 | 4.9986 4.9961 | 5.1860 5.1844 | 5.0056 4.9988 | 0.0095 0.0002 | |
| 80DU60 | | | $3\frac{3}{4}$ | 3.7600 3.7400 | | | | | |
| 96DU48 | | | 3 | 3.0100 2.9900 | | | | | |
| 96DU60 | 6 | $6\frac{3}{16}$ | $3\frac{3}{4}$ | 6.0000 5.9975 | 6.0000 5.9975 | 6.1874 6.1858 | 6.0070 6.0002 | | |
| 112DU60 | | | 7 | $7\frac{3}{16}$ | | | | | $3\frac{3}{4}$ |

8.8 DU Thrust Washers - Inch sizes

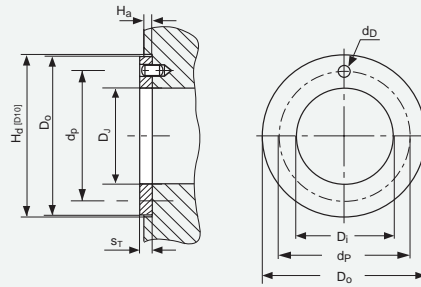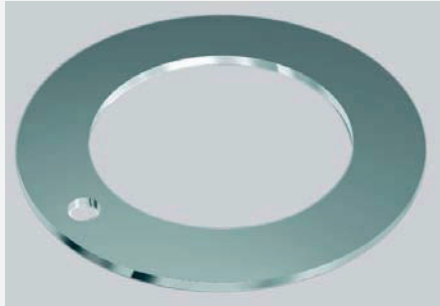


All dimensions in inch

| Part No. | Inside- \varnothing D_i | | Outside- \varnothing D_o | | Thickness s_T max. min. | Dowel Hole | | Recess Depth H_a max. min. |
|----------|--------------------------------|-------|---------------------------------|-------|------------------------------------|-----------------------------------|--|---------------------------------------|
| | max. | min. | max. | min. | | $\varnothing d_D$ max. min. | PCD- $\varnothing d_P$ max. min. | |
| DU06 | 0.510 | 0.500 | 0.875 | 0.865 | 0.063 0.061 | 0.077 0.067 | 0.692 | 0.050 0.040 |
| DU07 | 0.572 | 0.562 | 1.000 | 0.990 | | | 0.682 | |
| DU08 | 0.635 | 0.625 | 1.125 | 1.115 | | 0.109 0.099 | 0.786 | |
| DU09 | 0.697 | 0.687 | 1.187 | 1.177 | | | 0.776 | |
| DU10 | 0.760 | 0.750 | 1.250 | 1.240 | | | 0.880 | |
| DU11 | 0.822 | 0.812 | 1.375 | 1.365 | | 0.140 0.130 | 0.870 | |
| DU12 | 0.885 | 0.875 | 1.500 | 1.490 | | | 0.942 | |
| DU14 | 1.010 | 1.000 | 1.750 | 1.740 | | | 0.932 | |
| DU16 | 1.135 | 1.125 | 2.000 | 1.990 | | 0.171 0.161 | 1.005 | |
| DU18 | 1.260 | 1.250 | 2.125 | 2.115 | | | 0.995 | |
| DU20 | 1.385 | 1.375 | 2.250 | 2.240 | | | 1.099 | |
| DU22 | 1.510 | 1.500 | 2.500 | 2.490 | | 0.202 0.192 | 1.089 | |
| DU24 | 1.635 | 1.625 | 2.625 | 2.615 | | | 1.192 | |
| DU26 | 1.760 | 1.750 | 2.750 | 2.740 | | | 1.182 | |
| DU28 | 2.010 | 2.000 | 3.000 | 2.990 | 0.093 0.091 | 1.380 | 0.080 0.070 | |
| DU30 | 2.135 | 2.125 | 3.125 | 3.115 | | 1.370 | | |
| DU32 | 2.260 | 2.250 | 3.250 | 3.240 | | 1.567 | | |
| | | | | | | 1.557 | | |
| | | | | | | 1.692 | | |
| | | | | | 1.682 | | | |
| | | | | | 1.817 | | | |
| | | | | | 1.807 | | | |
| | | | | | 2.005 | | | |
| | | | | | 1.995 | | | |
| | | | | | 2.130 | | | |
| | | | | | 2.120 | | | |
| | | | | | 2.255 | | | |
| | | | | | 2.245 | | | |
| | | | | | 2.505 | | | |
| | | | | | 2.495 | | | |
| | | | | | 2.630 | | | |
| | | | | | 2.620 | | | |
| | | | | | 2.755 | | | |
| | | | | | 2.745 | | | |

8 Standard Products

8.9 DU Strip

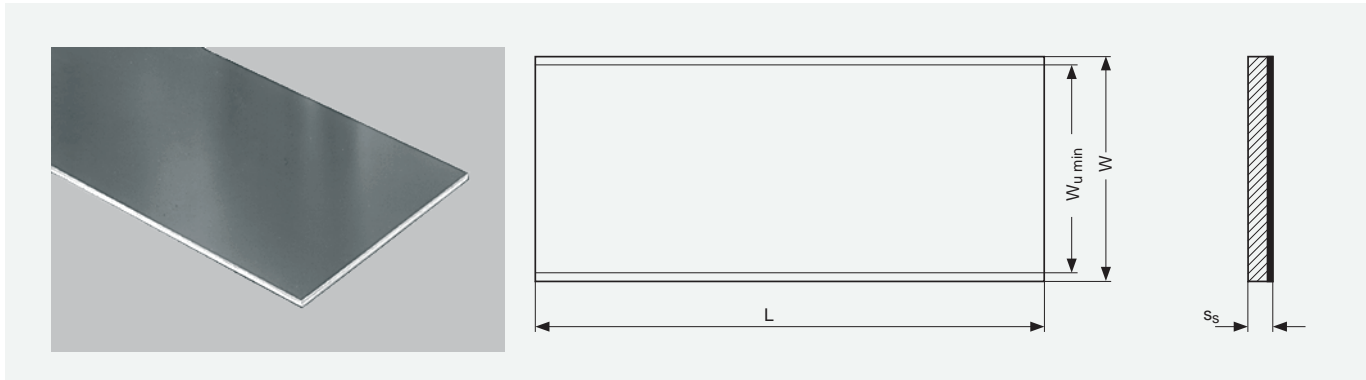

All dimensions in mm

| Part No. | Length L | | Total Width W | Usable Width $W_{U \min}$ | Thickness s_s | |
|----------|----------|------|---------------|---------------------------|-----------------|------|
| | max. | min. | | | max. | min. |
| S07190DU | 503 | 500 | 200 | 190 | 0.74 | 0.70 |
| S10190DU | | | | | 1.01 | 0.97 |
| S15240DU | | | | | 1.52 | 1.48 |
| S20240DU | | | 254 | 240 | 2.00 | 1.96 |
| S25240DU | | | | | 2.50 | 2.46 |
| S30240DU | | | | | 3.06 | 3.02 |

8.10DUB Strip

All dimensions in mm

| Part No. | Length L | | Total Width W | Usable Width $W_{U \min}$ | Thickness s_s | |
|-----------|----------|------|---------------|---------------------------|-----------------|------|
| | max. | min. | | | max. | min. |
| S07085DUB | 503 | 500 | 95 | 85 | 0.74 | 0.70 |
| S10180DUB | | | | | 1.01 | 0.97 |
| S15180DUB | | | | | 1.52 | 1.48 |
| S20180DUB | | | 193 | 180 | 2.00 | 1.96 |
| S25180DUB | | | | | 2.50 | 2.46 |

8.11 DU Strip - Inch sizes

DU Strip Inch sizes are available as Non-Standard products, on request.

9 Test Methods

9.1 Measurement of Wrapped Bushes

It is not possible to accurately measure the external and internal diameters of a wrapped bush in the free condition. In its free state a wrapped bush will not be perfectly cylindrical and the butt joint may be open. When correctly installed in a housing the butt joint will be tightly closed and the bush will conform to the housing.

For this reason the external diameter and internal diameter of a wrapped bush can only be checked with special gauges and test equipment.

The checking methods are defined in ISO 3547 Parts 1 to 7.

Test A of ISO 3547 Part 2

Checking the external diameter in a test machine with checking blocks and adjusting mandrel.

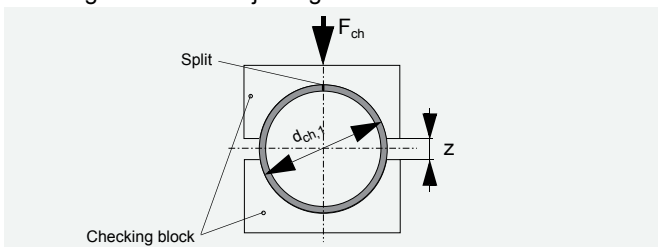


Fig. 34: Test A, Data for drawing

| Test A of ISO 3547 Part 2 on 2015DU | |
|---|---------------------|
| Checking block and setting mandrel $d_{ch,1}$ | 23.062 mm |
| Test force F_{ch} | 4500 N |
| Limits for Δz | 0 and -0.065 mm |
| Bush Outside diameter D_o | 23.035 to 23.075 mm |

Table 14: Test A of ISO 3547 Part 2

Test B (alternatively to Test A)

Check external diameter with GO and NOGO ring gauges.

Test C

Checking the internal diameter of a bush pressed into a ring gauge, which nominal diameter corresponds to the dimension specified in table 6 of ISO 3547 Part 2 (Example $D_i = 20$ mm).

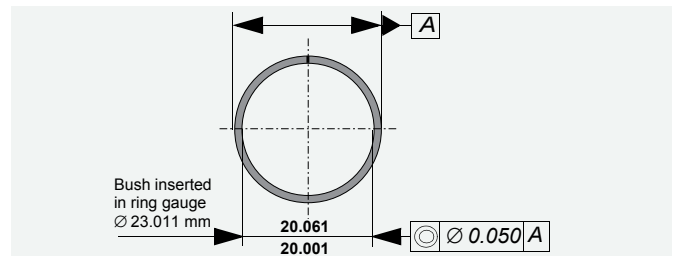


Fig. 35: Test C, Data for drawing

Measurement of Wall Thickness (alternatively to Test C)

The wall thickness is measured at one, two or three positions axially according to the bearing dimensions.

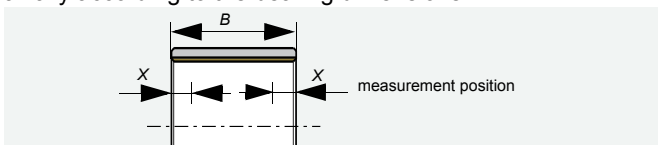


Fig. 36: Measurement position

| B [mm] | X [mm] | measurement position |
|---------------|-----------|----------------------|
| ≤ 15 | B/2 | 1 |
| $>15 \leq 50$ | 4 | 2 |
| $>50 \leq 90$ | 6 and B/2 | 3 |
| >90 | 8 and B/2 | 3 |

Table 15: Measurement position

Test D

Check external diameter by precision measuring tape.

9 Test Methods

Your notes:

Formula Symbols and Designations

| Formula Symbol | Unit | Designation |
|----------------|----------------|--|
| A | mm^2 | Surface Area of DU bearing |
| A_M | mm^2 | Surface Area of mating surface in contact with DU bearing (slideway) |
| a_B | - | Bearing size factor |
| a_C | - | Application factor for bore burnishing or machining |
| a_E | - | High load factor |
| a_{E1} | - | Specific load factor (slideways) |
| a_{E2} | - | Speed, temperature and material factor (slideways) |
| a_{E3} | - | Relative contact area factor (slideways) |
| a_L | - | Life correction constant |
| a_M | - | Mating surface material factor |
| a_T | - | Temperature application factor |
| B | mm | Nominal bush width |
| C | $1/\text{min}$ | Dynamic load frequency |
| C_D | mm | Installed diametral clearance |
| C_i | mm | ID chamfer length |
| C_o | mm | OD chamfer length |
| C_T | - | Total number of dynamic load cycles |
| D_C | mm | Diameter of burnishing tool |
| D_{fl} | mm | Nominal bush flange OD |
| D_H | mm | Housing Diameter |
| D_i | mm | Nominal bush and thrust washer ID |
| $D_{i,a}$ | mm | Bush ID when assembled in housing |
| D_J | mm | Shaft diameter |
| D_{Nth} | nvt | Max. thermal neutron dose |
| D_o | mm | Nominal bush and thrust washer OD |
| D_γ | Gy | Max. Gamma radiation dose |
| $d_{ch,1}$ | mm | Checking block diameter |
| d_D | mm | Dowel hole diameter |
| d_L | mm | Oil hole diameter |
| d_P | mm | Pitch circle diameter for dowel hole |
| F | N | Bearing load |
| F_{ch} | N | Test force |
| F_i | N | Insertion force |
| f | - | friction |

| Formula Symbol | Unit | Designation |
|---------------------|-------------------------|---|
| H_a | mm | Depth of Housing Recess (e.g. for thrust washers) |
| H_d | mm | Diameter of Housing Recess (for thrust washers) |
| L | mm | Strip length |
| L_H | h | Bearing service life |
| L_S | mm | Length of stroke (slideway) |
| N | $1/\text{min}$ | Rotational speed |
| N_{osz} | $1/\text{min}$ | Oscillating movement frequency |
| \bar{p} | N/mm^2 | Specific load |
| \bar{p}_{lim} | N/mm^2 | Specific load limit |
| $\bar{p}_{sta,max}$ | N/mm^2 | Maximum static load |
| $\bar{p}_{dyn,max}$ | N/mm^2 | Maximum dynamic load |
| Q | - | Permissible number of cycles |
| R_a | mm | Surface roughness (DIN 4768, ISO/DIN 4287/1) |
| R_{OB} | Ω | Electrical resistance |
| s_3 | mm | Bush wall thickness |
| s_{fl} | mm | Flange thickness |
| s_S | mm | Strip thickness |
| s_T | mm | Thrust washer thickness |
| T | $^\circ\text{C}$ | Temperature |
| T_{amb} | $^\circ\text{C}$ | Ambient temperature |
| T_{max} | $^\circ\text{C}$ | Maximum temperature |
| T_{min} | $^\circ\text{C}$ | Minimum temperature |
| U | m/s | Sliding speed |
| W | mm | Strip width |
| $W_{U min}$ | mm | Minimum usable strip width |
| Z_T | - | Total number of cycles |
| α_1 | $1/10^6\text{K}$ | Coefficient of linear thermal expansion parallel to surface |
| α_2 | $1/10^6\text{K}$ | Coefficient of linear thermal expansion normal to surface |
| σ_c | N/mm^2 | Compressive Yield strength |
| λ | W/mK | Thermal conductivity |
| ϕ | $^\circ$ | Angular displacement |
| η | Ns/mm^2 | Dynamic Viscosity |

Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2009 (This edition replaces earlier editions which hereby lose their validity).

Declaration on lead contents of GGB products/compliance with EU law

Since July 1, 2006 it has been prohibited under Directive 2002/95/EC (restriction of the use of certain hazardous substances in electrical and electronic equipment; ROHS Directive) to put products on the market that contain lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls (PBB) or polybrominated diphenyl ethers (PBDE).

Certain applications listed in the annex to the ROHS Directive are exempted. A maximum concentration value of 0.01% by weight and per homogeneous material, for cadmium and of 0.1% by weight and per homogeneous material, for lead, mercury, hexavalent chromium, PBB and PBDE shall be tolerated.

According to Directive 2000/53/EC on end-of life vehicles, since July 1, 2003 it has been prohibited to put on the market materials and components that contain lead, mercury, cadmium or hexavalent chromium. Due to an exceptional provision, lead-containing bearing shells and bushes could still be put on the market up until July 1, 2008. This general exception expired on July 1, 2008. A maximum concentration value of up to 0.1% by weight and per homogeneous material, for lead, hexavalent chromium and mercury shall be tolerated.

All products of GGB, with the exception of DU, DUB, SY and SP satisfy these requirements of Directives 2002/95/EC (ROHS Directive) and 2000/53/EC (End-of-life Vehicle Directive).

All products manufactured by GGB are also compliant with REACH Regulation (EC) No. 1 907/2006 of December 18, 2006.

Health Hazard - Warning

There are two separate aspects of health hazard which could arise from certain usage of DU materials.

Fabrication

At temperatures up to 250 °C the polytetrafluoroethylene (PTFE) present in the lining material is completely inert so that even on the rare occasions in which DU bushes are drilled, or sized, after assembly there is no danger in boring or burnishing.

At higher temperatures however, small quantities of toxic fumes can be produced and the direct inhalation of these can cause an influenza type of illness which may not appear for some hours but which subsides without after-effects in 24-48 hours.

Such fumes can arise from PTFE particles picked up on the end of a cigarette. Therefore smoking should be prohibited where DU is being machined.

DU® and DU®B are trademarks of GGB.

Visit us on the internet:
www.ggbearings.com



an EnPro Industries company

The Global Leader in High Performance Bearing Solutions

GGB Heilbronn GmbH

Postfach 18 62 • D-74008 Heilbronn
Ochsenbrunnenstraße 9 • D-74078 Heilbronn
Industriegebiet Böllinger Höfe
Tel. +49 7131 269 0 • Fax +49 7131 269 500
eMail: germany@ggbearings.com • www.ggbearings.de



HB103ENG11-15HN